


COMBINED STATE BINDER GROUP ROUND ROBIN SUMMARY B 2015-2
PG 64-34

	Rot. Visc.	ODSR	RTFO DSR	PAVDSR	Mass Loss	S-value	m-value	Jnr @ 100 Pa	% Rec. 100 Pa	Jnr @ 3200 Pa	% Rec. @ 3200 Pa
A											
19	0.830	1.37	3.33	1,667	-0.791	277	0.330	0.269	72.10	0.273	69.80
51	0.826	1.37	3.30	1,619	-0.780	270	0.336	0.271	72.30	0.273	70.20
97	0.825	1.37	3.20	1,629	-0.743	277	0.324	0.282	72.10	0.285	69.90
98	0.834	1.40	3.22	1,724	-0.779	269	0.329	0.285	71.80	0.293	69.60
AVERAGE	0.829	1.37	3.26	1,660	-0.773	273	0.330	0.277	72.08	0.281	69.88
B											
01	0.715	1.50	3.96	1,571	-0.690	270	0.322	0.220	73.71	0.227	71.96
17	0.725	1.49	3.86	1,966	-0.644	256	0.316	0.250	70.98	0.244	70.59
45	0.727	1.51	4.03	1,952	-0.715	257	0.310	0.212	74.31	0.212	72.81
AVERAGE	0.722	1.50	3.95	1,830	-0.683	261	0.316	0.227	73.00	0.228	71.79
C											
28	0.897	1.41	3.27	2,037	-0.597	260	0.318	0.305	70.28	0.302	69.49
66	0.879	1.45	3.23	2,083	-0.587	263	0.316	0.279	72.90	0.286	71.09
90	0.878	1.41	3.38	2,048	-0.551	263	0.319	0.263	72.90	0.269	70.94
99	0.882	1.38	3.32	1,824	-0.524	267	0.314	0.289	71.70	0.291	70.22
AVERAGE	0.884	1.41	3.30	1,998	-0.565	263.25	0.317	0.284	71.95	0.287	70.44
E											
15	0.913	1.40	3.58	1,927	-0.649	266	0.324	0.198	78.04	0.241	72.19
89	0.908	1.37	3.61	1,839	-0.772	275	0.320	0.195	78.12	0.236	72.53
AVERAGE	0.911	1.39	3.60	1,883	-0.711	271	0.322	0.197	78.08	0.239	72.36
F											
02	0.913	1.44	3.21	1,697	-0.621	272	0.330	0.234	76.07	0.293	69.09
11	0.913	1.44	3.66	1,729	-0.68	272	0.329	0.210	78.18	0.262	71.81
34	0.823	1.48	3.22	1,663	-0.531	277	0.323	0.286	71.97	0.294	70.03
48	0.825	1.43	3.37	1,627	-0.524	258	0.331	0.268	72.51	0.274	70.71
56	0.863	1.41	3.43	1,780	-0.677	268	0.321	0.217	77.09	0.267	70.75
62	0.874	1.43	3.98	1,610	-0.715	282	0.326	0.166	79.30	0.205	73.52
AVERAGE	0.869	1.44	3.48	1,684	-0.625	271.5	0.327	0.230	75.85	0.266	70.99
J											
05	0.869	1.40	3.65	1,780	-0.705	274	0.320	0.167	80.76	0.223	74.02
08	0.869	1.40	3.74	1,725	-0.722	282	0.315	0.190	79.22	0.250	72.25
10	0.863	1.40	3.39	1,692	-0.801	282	0.317	0.182	80.01	0.252	72.23
22	0.857	1.40	3.34	1,761	-0.718	262	0.316	0.198	78.98	0.246	73.17
31	0.868	1.59	3.53	1,868	-0.739	270	0.313	0.187	79.29	0.254	71.86
41	0.876	1.43	3.57	1,910	-0.816	277	0.311	0.177	79.97	0.237	72.97
44	0.865	1.40	3.43	1,809	-0.813	270	0.316	0.188	79.24	0.254	71.81
52	0.857	1.42	3.54	1,716	-0.737	273	0.316	0.171	80.51	0.240	72.73
87	0.864	1.39	3.48	1,803	-0.801	285	0.319	0.180	79.83	0.248	72.16
AVERAGE	0.865	1.43	3.52	1,785	-0.761	275	0.316	0.182	79.76	0.245	72.58
L											
59	0.950	1.38	2.67	1,920	-0.685	273	0.324	0.467	64.50	0.544	58.00
25	0.900	1.41	3.46	1,831	-0.007	267	0.327	0.238	75.29	0.293	68.64
AVERAGE	0.925	1.40	3.07	1,876	-0.346	270	0.326	0.353	69.90	0.419	63.32
M											
04	0.987	1.45	3.39	1,596	-0.684	270	0.331				
47	0.985	1.44	3.38	1,474	-0.677	271	0.336				
57	0.999	1.44	3.38	1,475	-0.694	270	0.333				
AVERAGE	0.990	1.44	3.38	1,515	-0.685	270	0.333				
O											
85	0.830	1.35	3.14	1,780	-0.698	277	0.320	0.292	72.40	0.299	70.47
76	0.828	1.38	3.18	2,000	-0.664	272	0.324	0.285	72.78	0.287	71.09
AVERAGE	0.829	1.37	3.16	1,890	-0.681	274.5	0.322	0.289	72.59	0.293	70.78
Q											
23	0.898	1.42	3.68	1,927	-0.722	279	0.325	0.193	77.60	0.237	71.59
93	0.888	1.50	3.71	1,816	-0.867	267	0.322	0.195	77.92	0.237	72.06
AVERAGE	0.893	1.46	3.70	1,872	-0.795	273	0.324	0.194	77.76	0.237	71.83
S											
53	0.801	1.37	3.42	1,740	-0.009	251	0.326	0.258	72.94	0.261	71.29
64	0.814	1.38	3.42	1,750	-0.00864	252	0.328	0.259	72.99	0.263	71.22
AVERAGE	0.808	1.38	3.42	1,745	-0.00865	252	0.327	0.259	72.97	0.262	71.26
U											
13	0.880	1.38	4.22	2,050	-0.647	262	0.318	0.146	79.18	0.179	73.80
24	0.863	1.48	3.39	2,070	-0.663	277	0.320	0.197	79.29	0.255	72.79
AVERAGE	0.872	1.43	3.81	2,060	-0.655	269.5	0.319	0.172	79.24	0.217	73.30


COMBINED STATE BINDER GROUP ROUND ROBIN
 SUMMARY B 2015-2
 PG 64-34

ROTATIONAL VISCOSITY

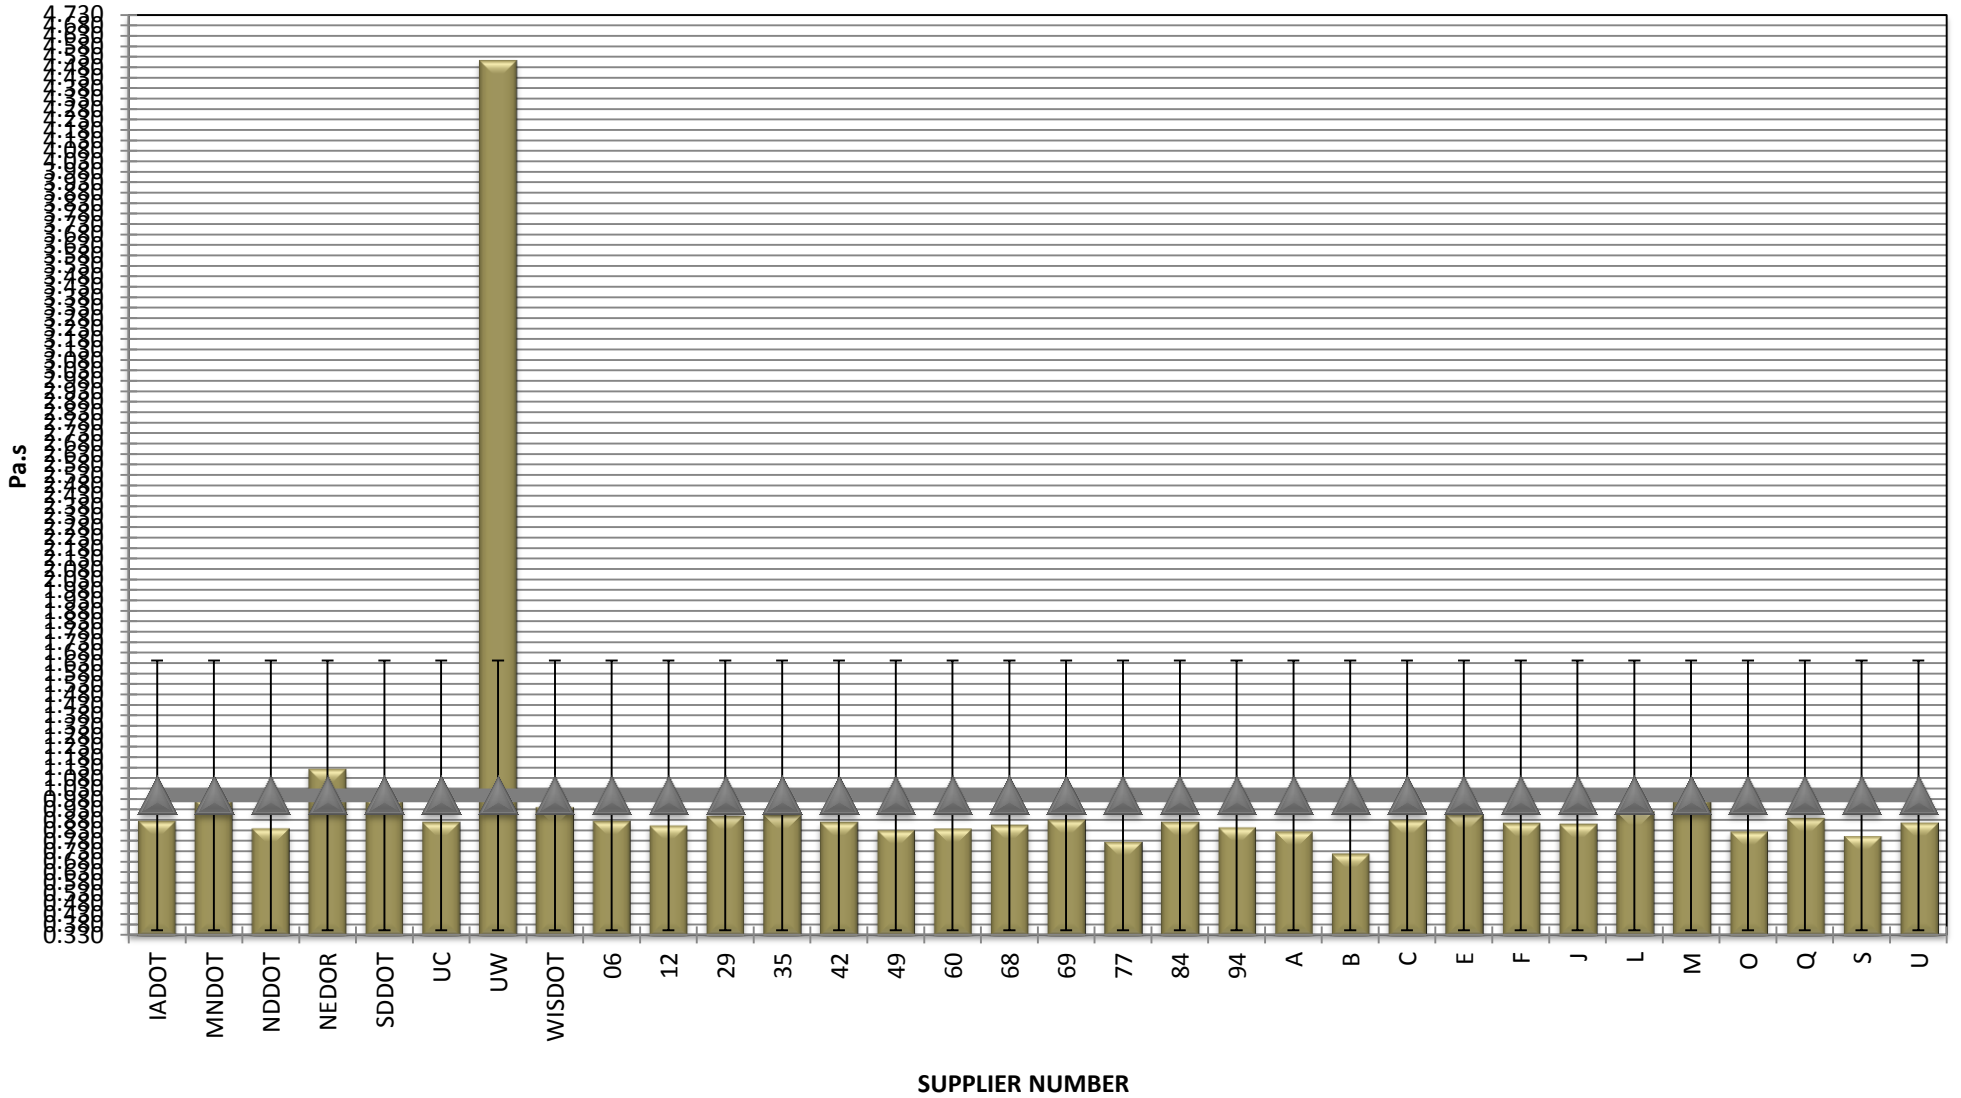


COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2015-2
PG 64-34

DSR - ORIGINAL

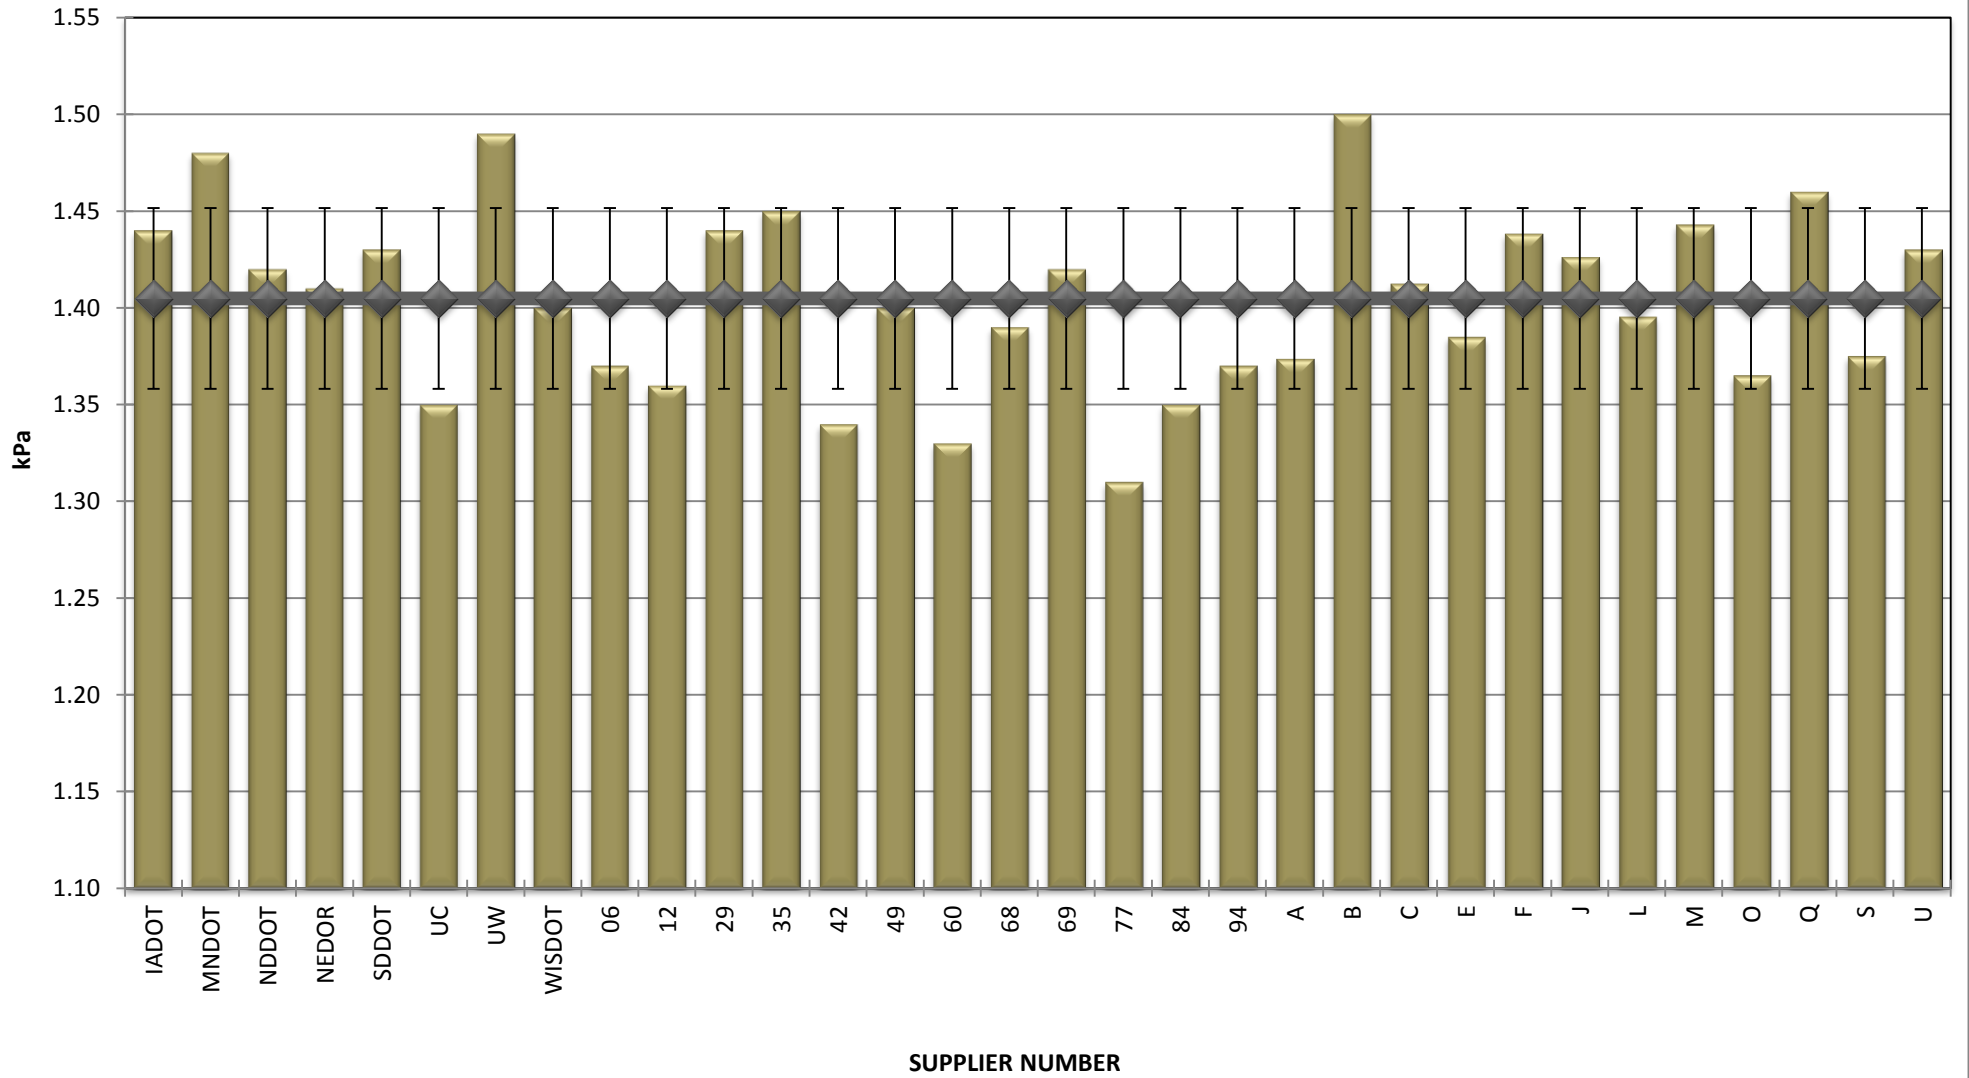


COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2015-2
PG 64-34

DSR - RTFO

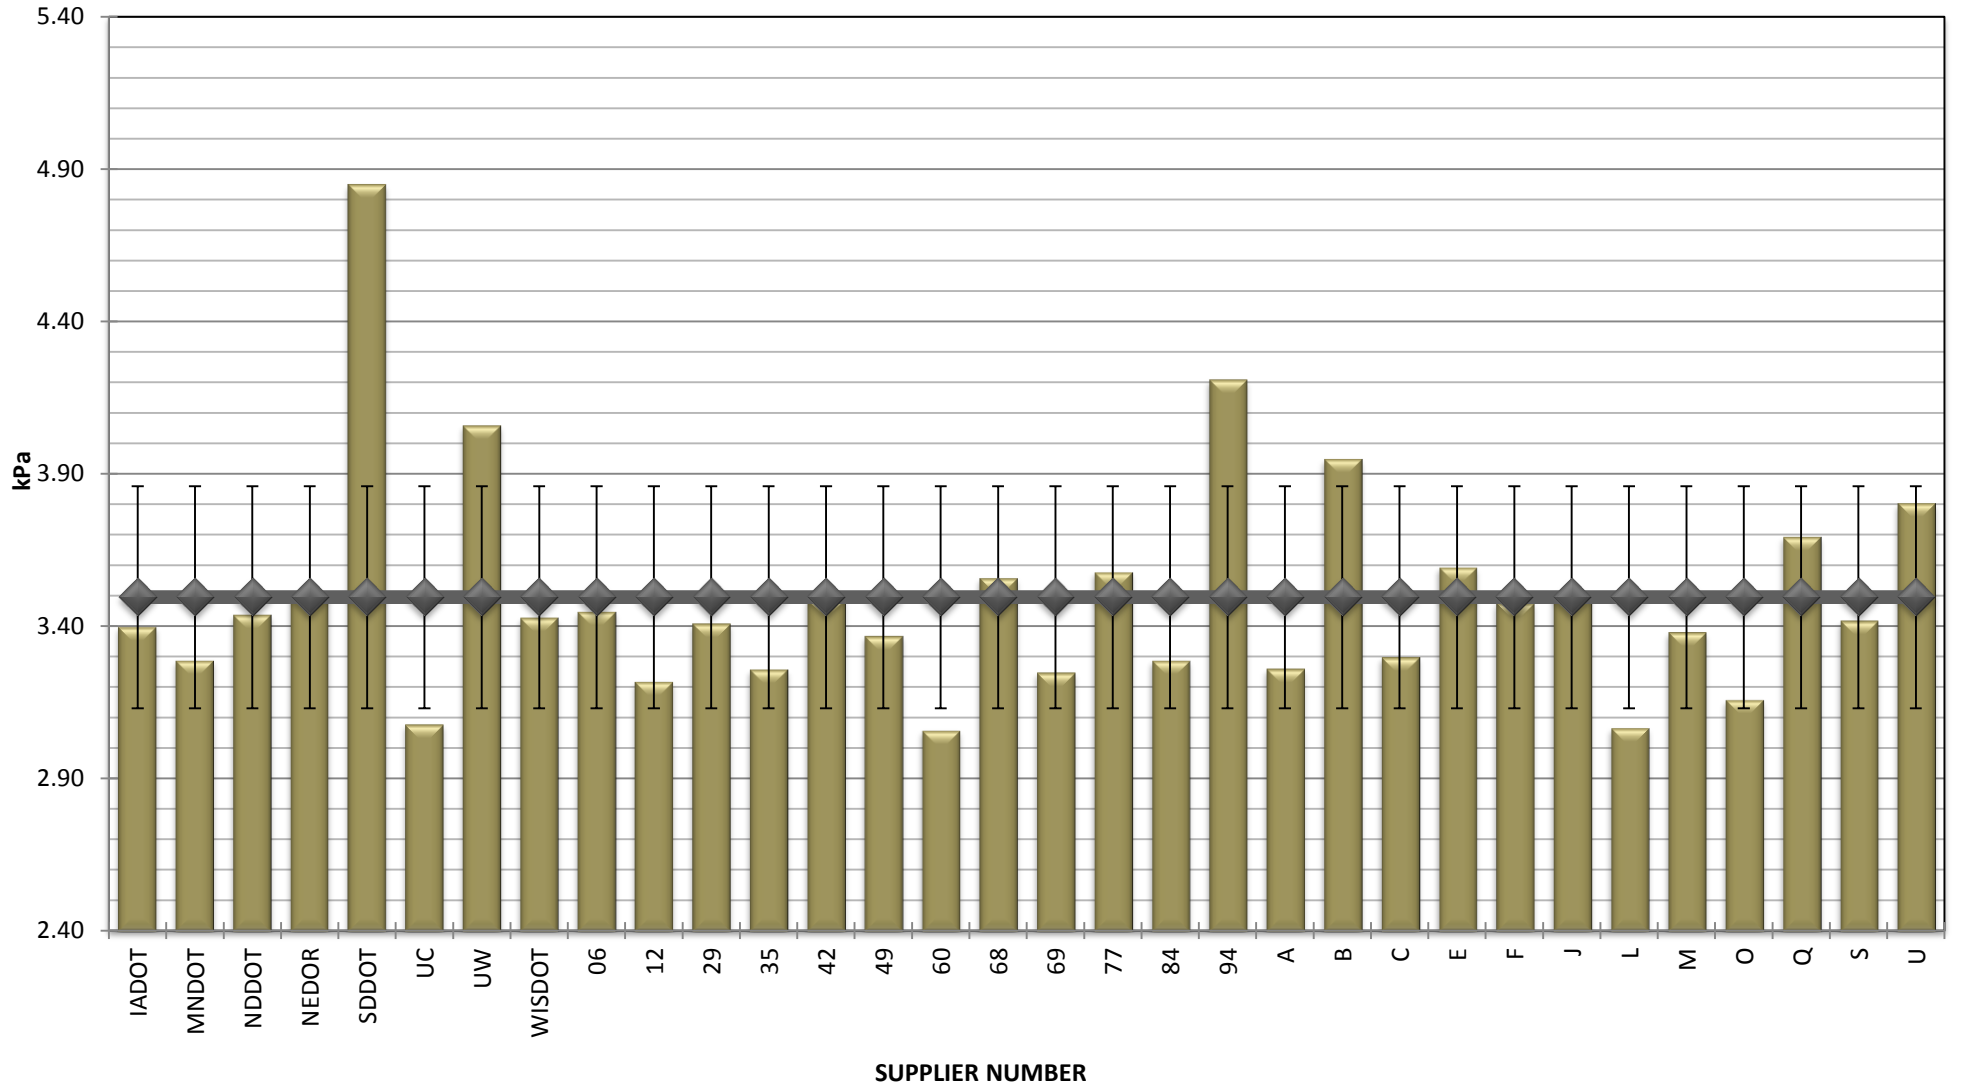


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2015-2
PG 64-34**

DSR - PAV

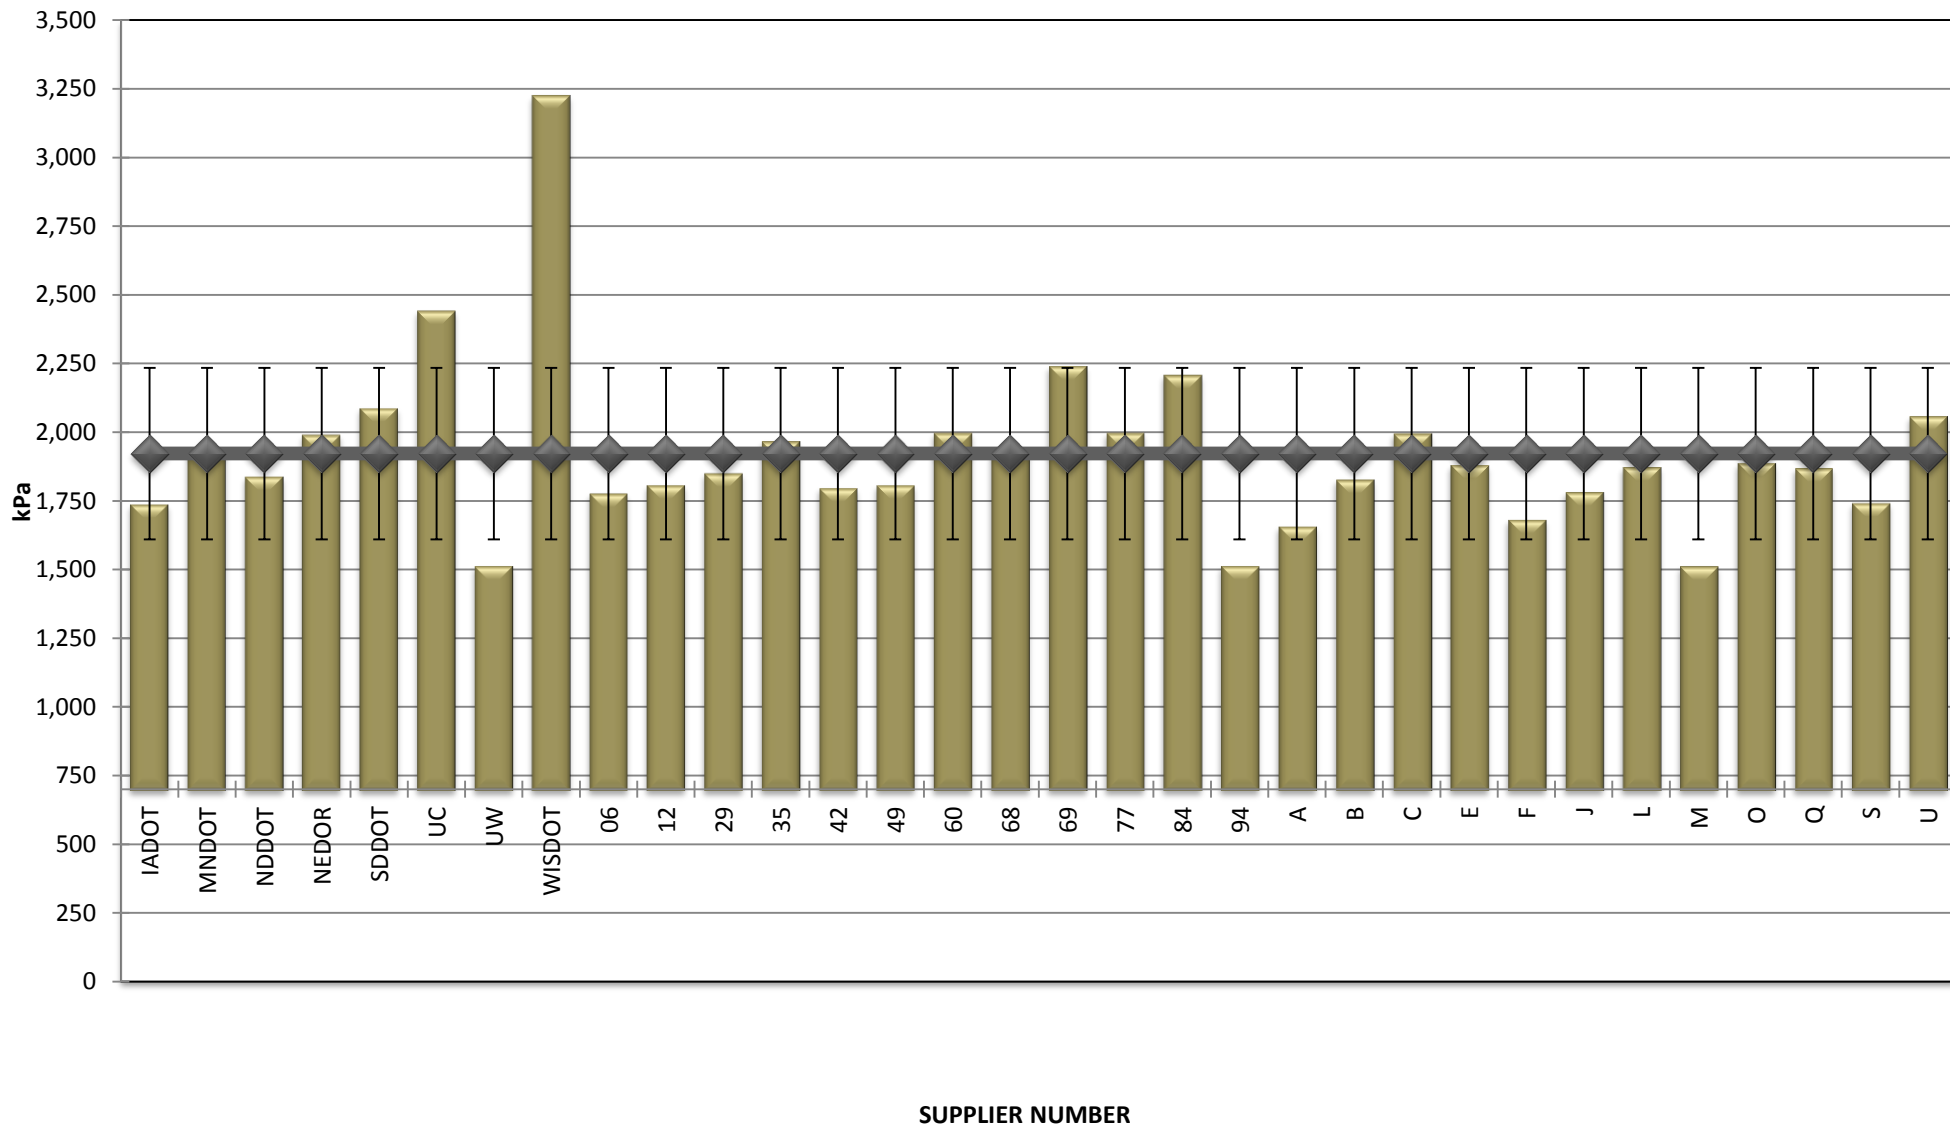


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2015-2
PG 64-34**

RTFO MASS LOSS

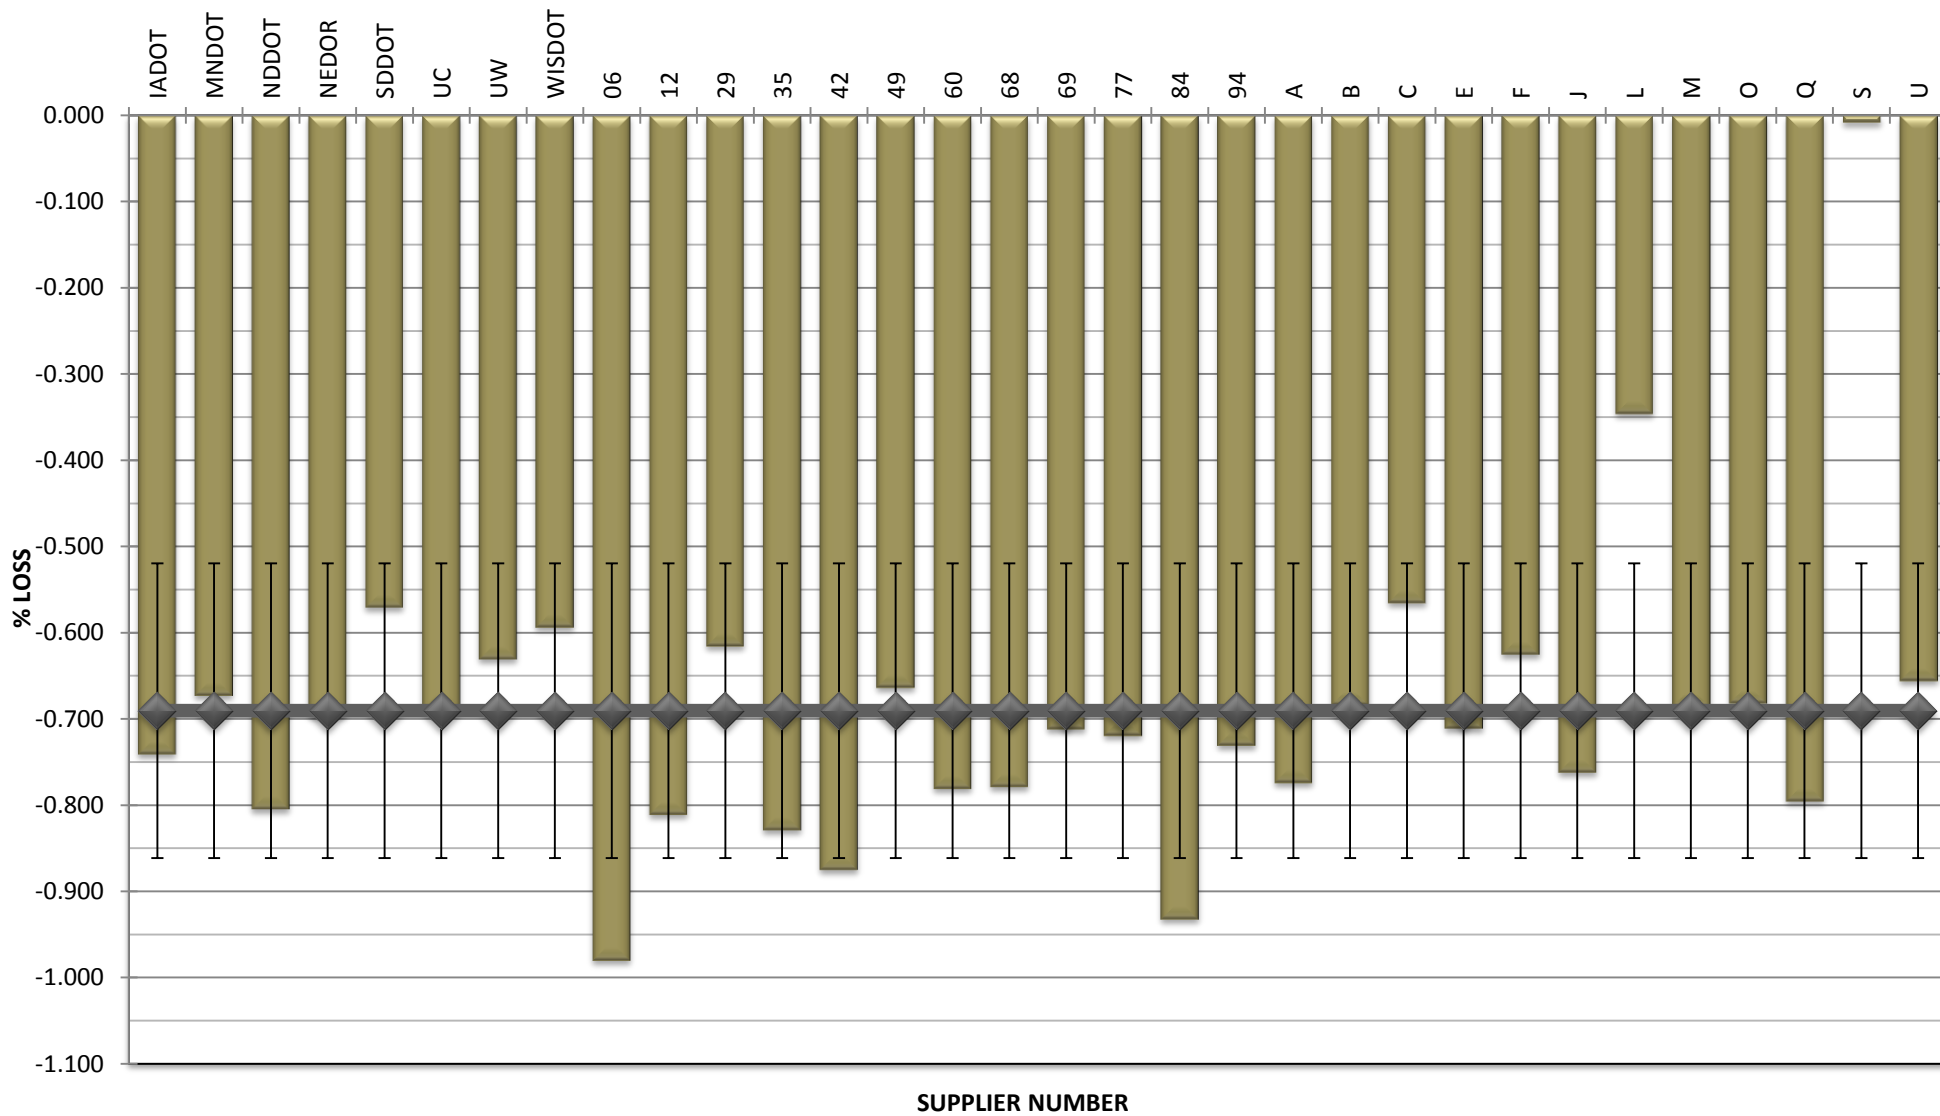


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2015-2
PG 64-34**

BBR STIFFNESS

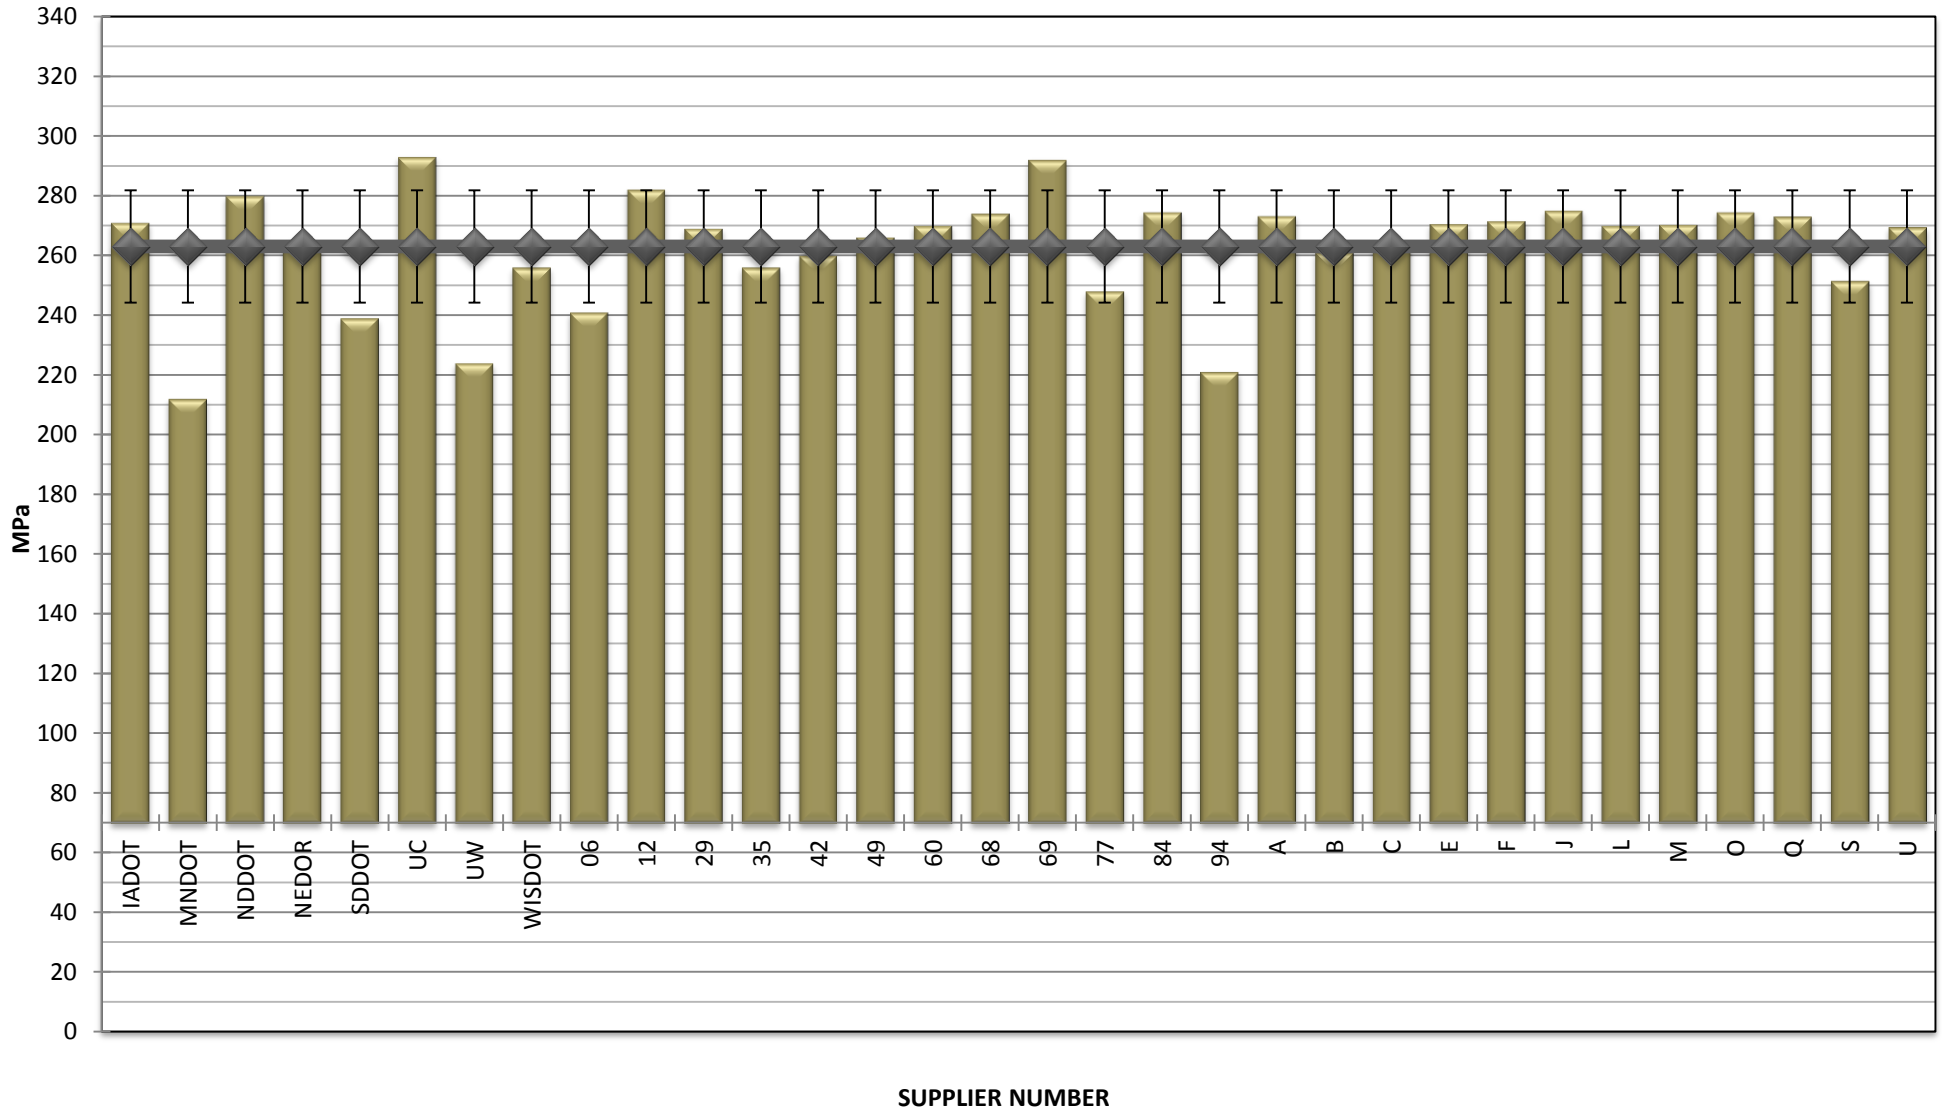


COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2015-2
PG 64-34

BBR m-VALUE

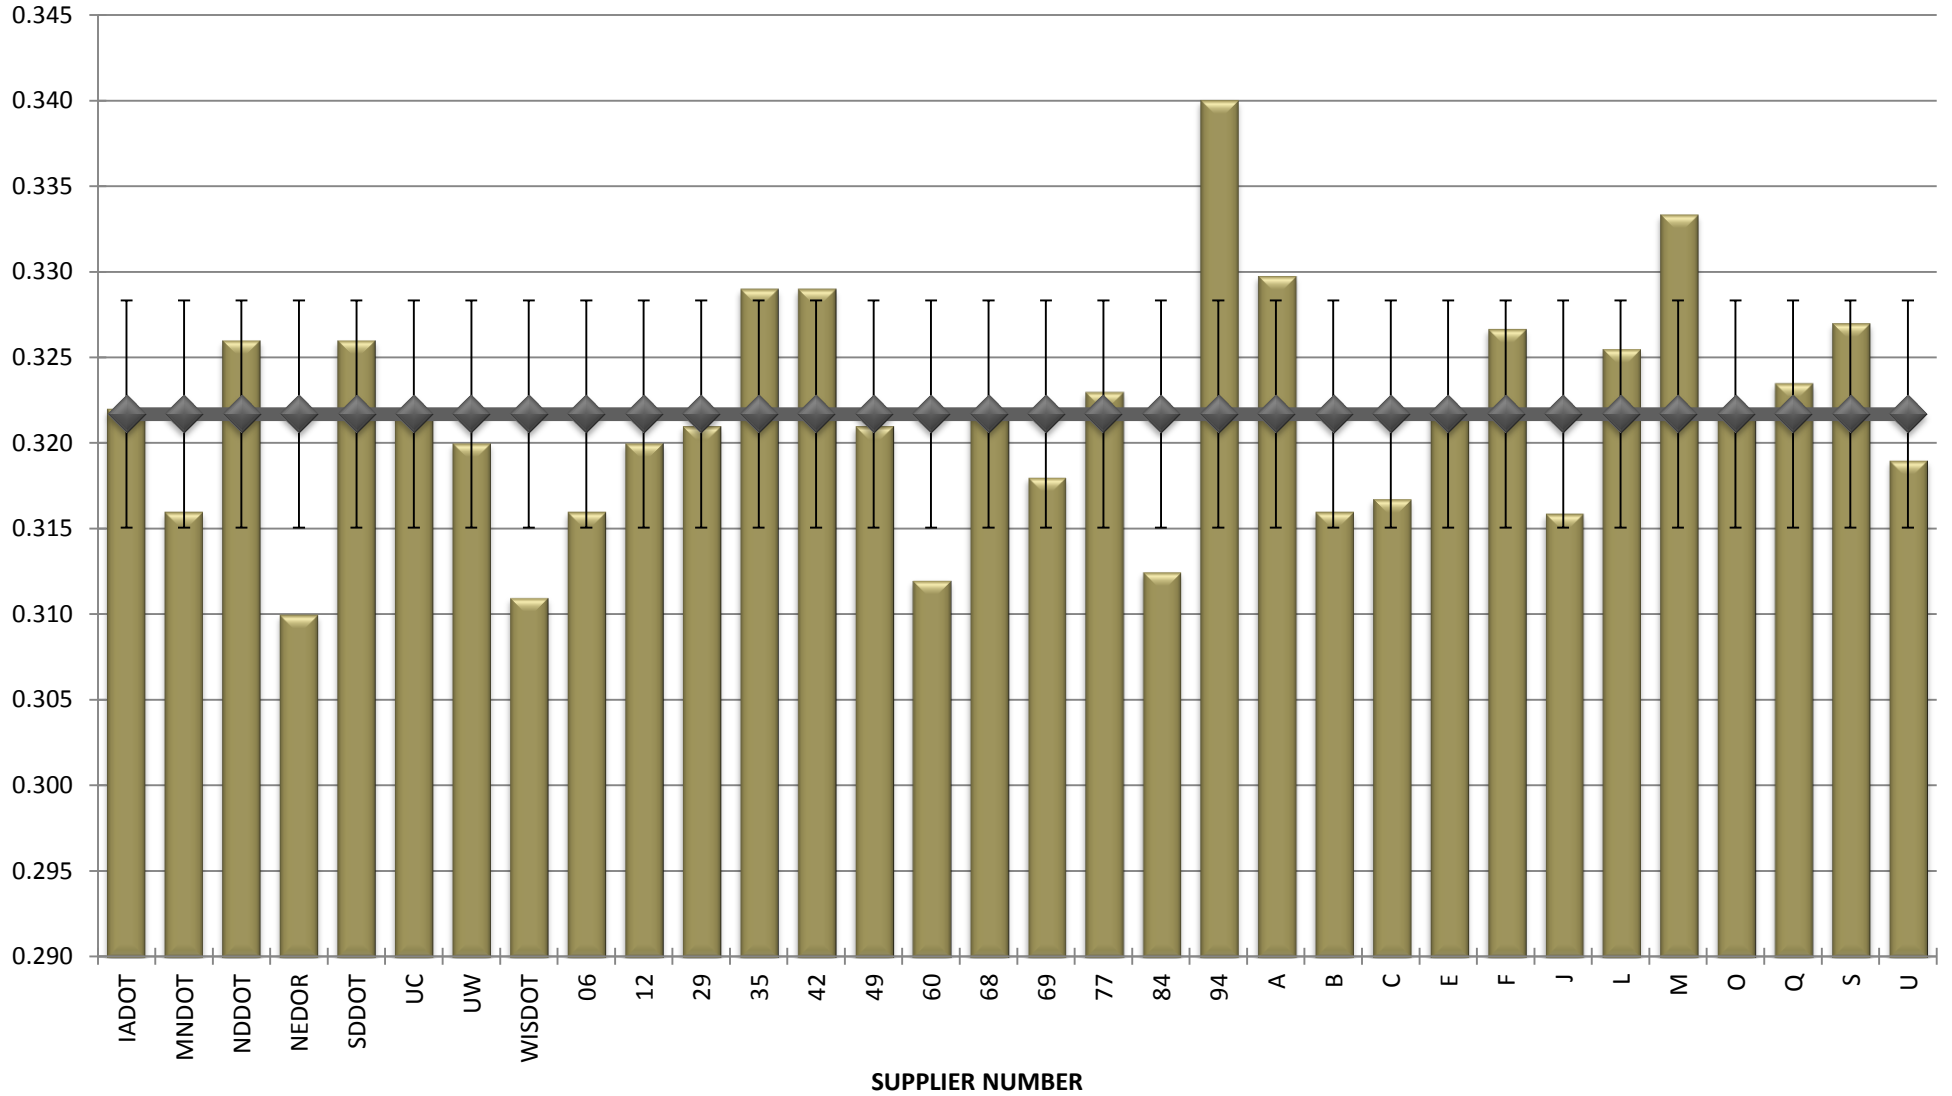


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2015-2
PG 64-34**

Jnr @ 100 Pa

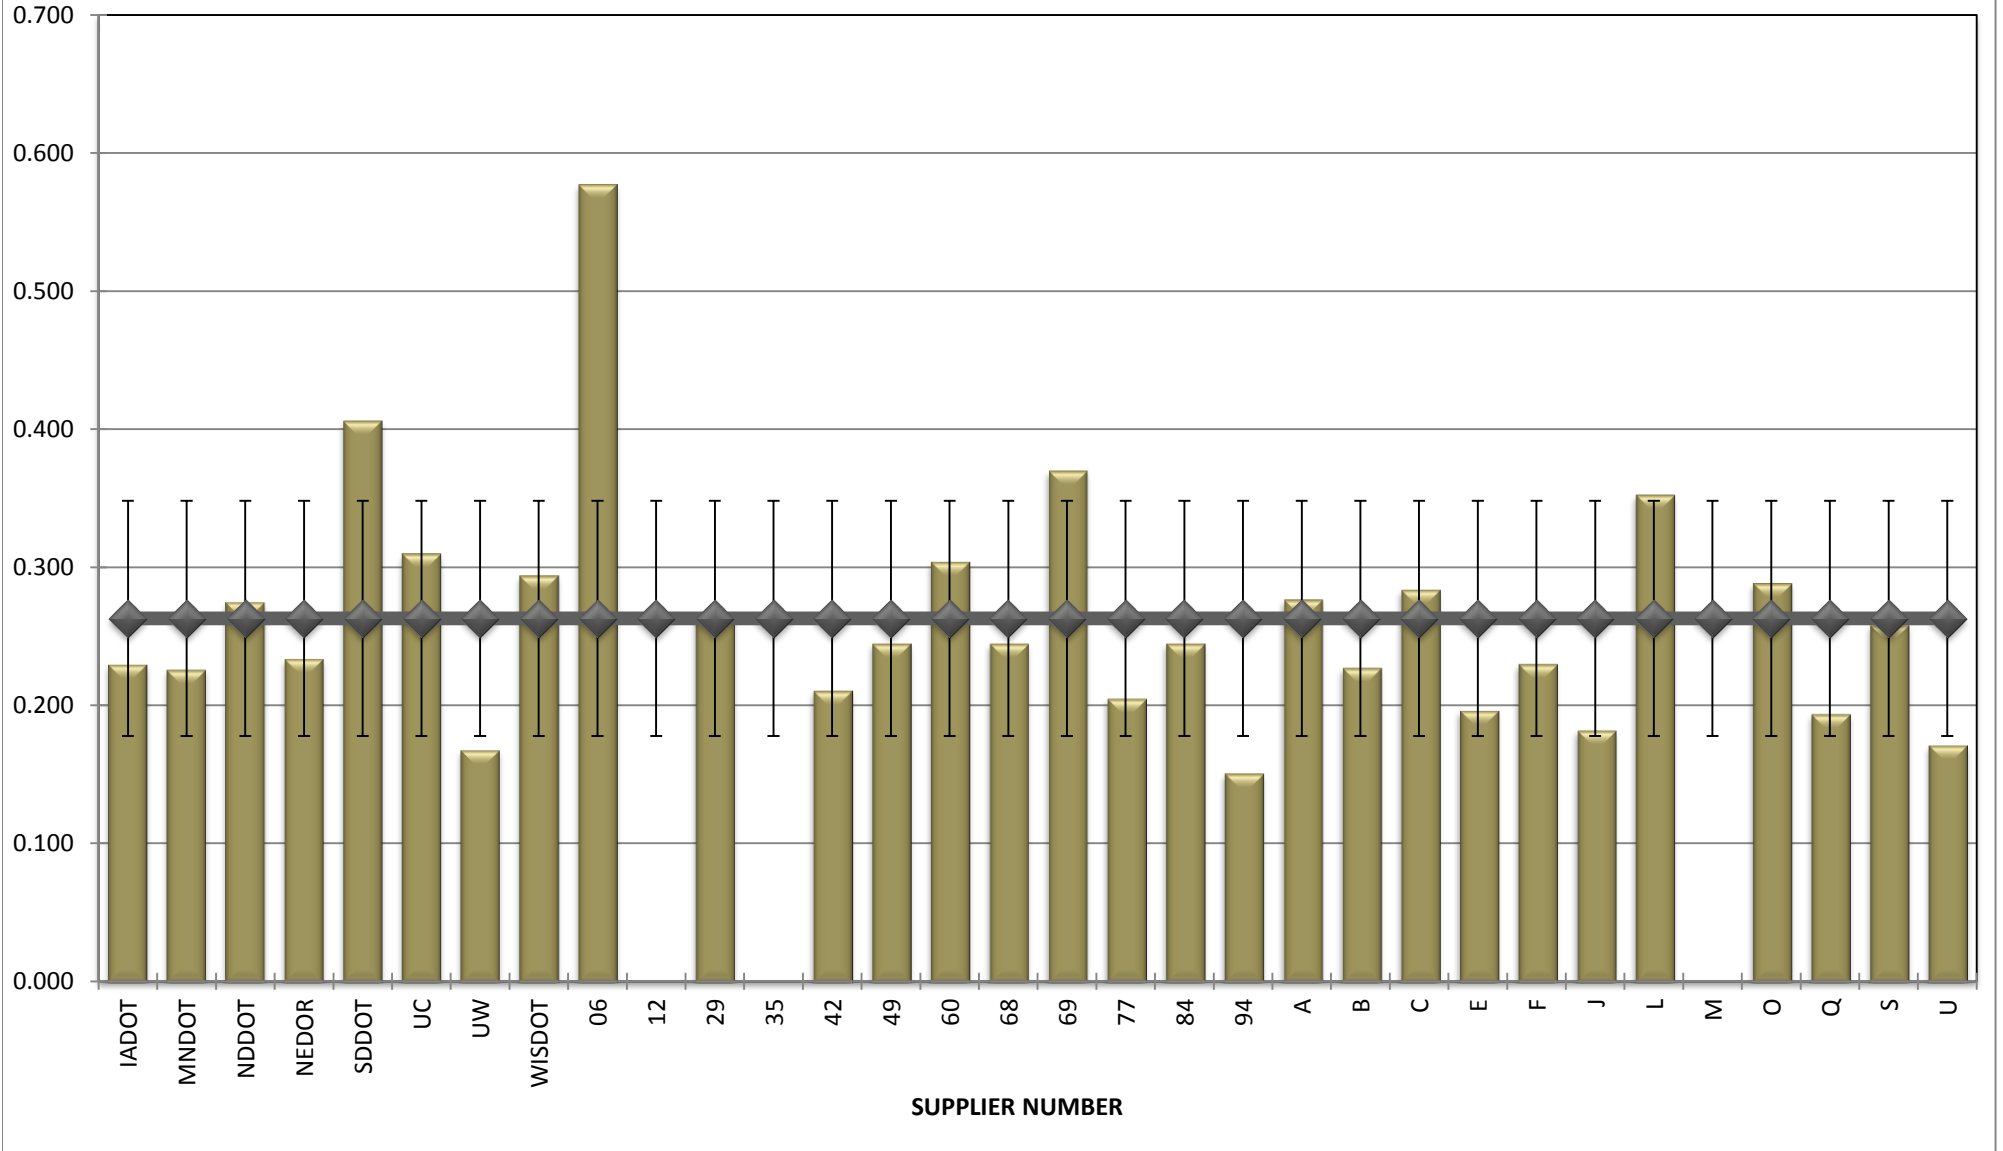


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2015-2
PG 64-34**

% Recovery @ 100 Pa

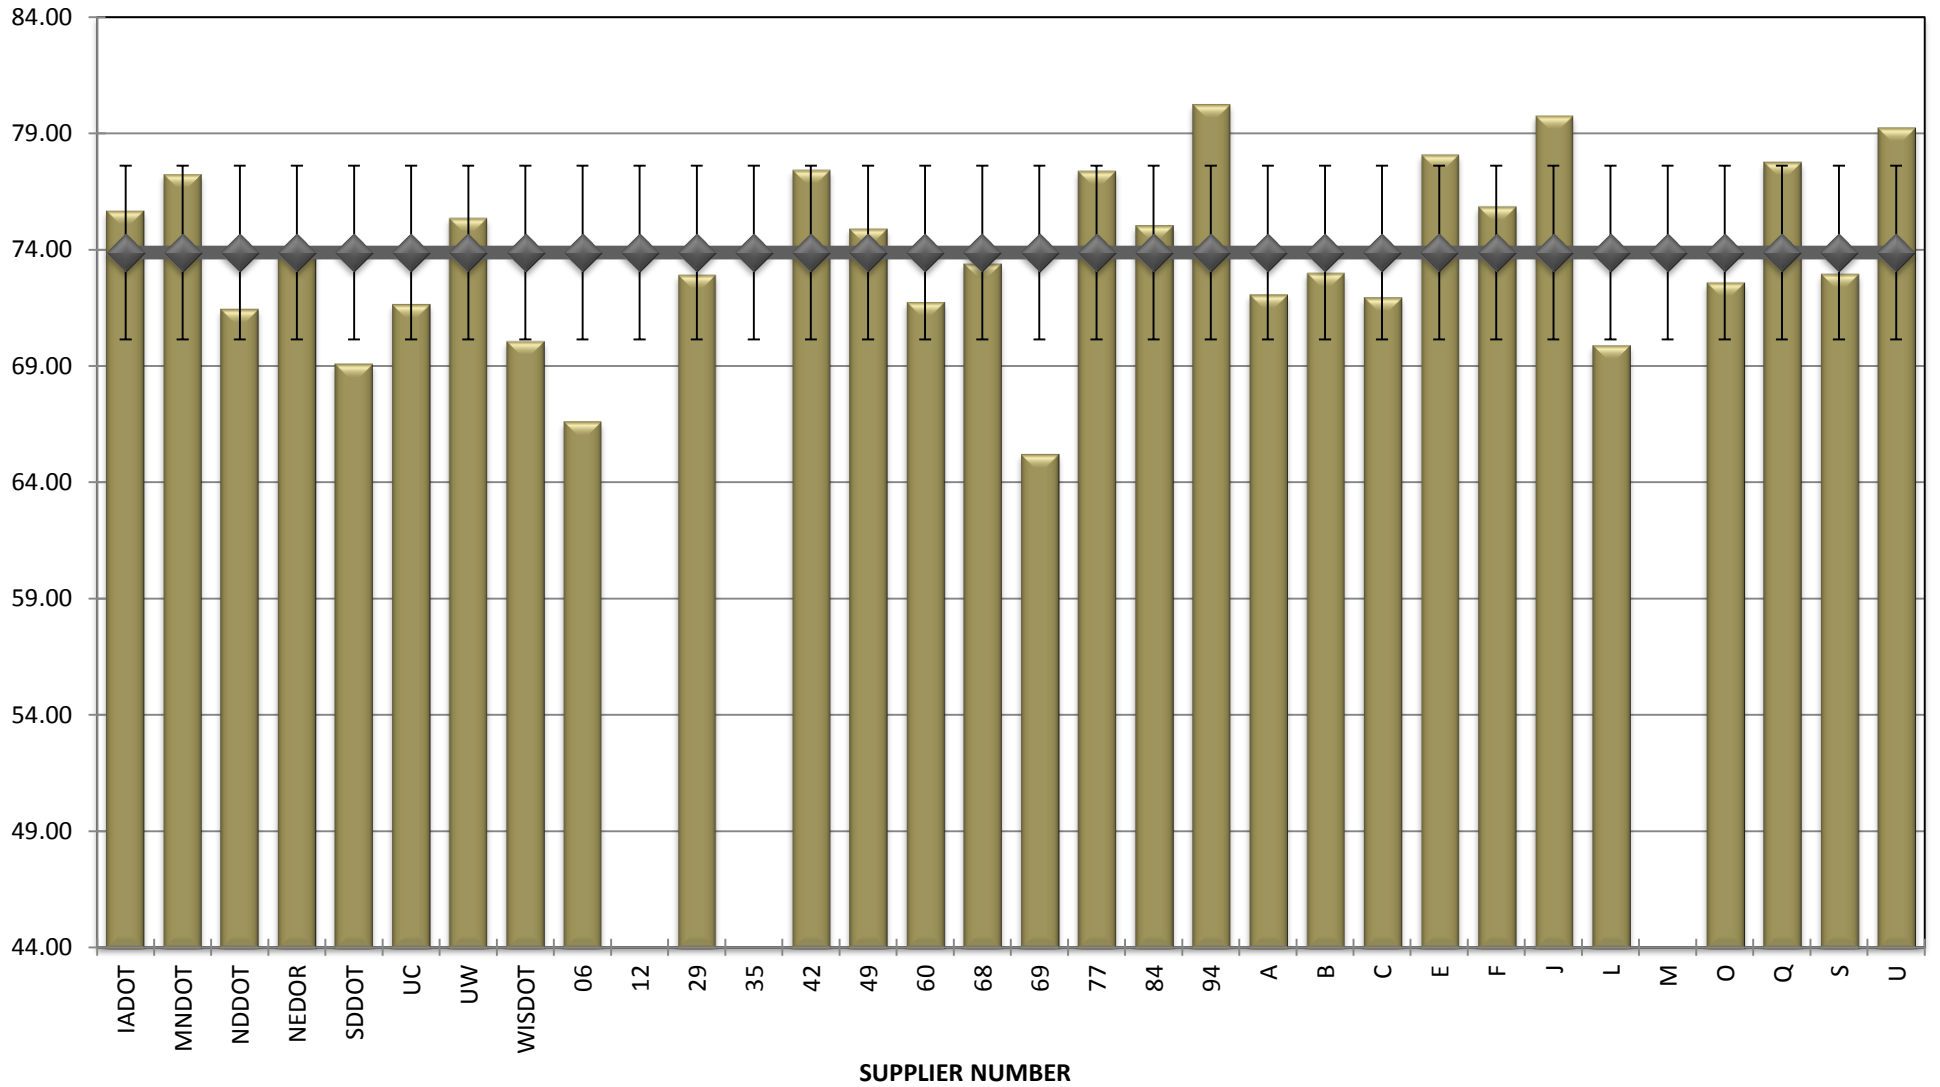

**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2015-2
PG 64-34**

Jnr @ 3200 Pa

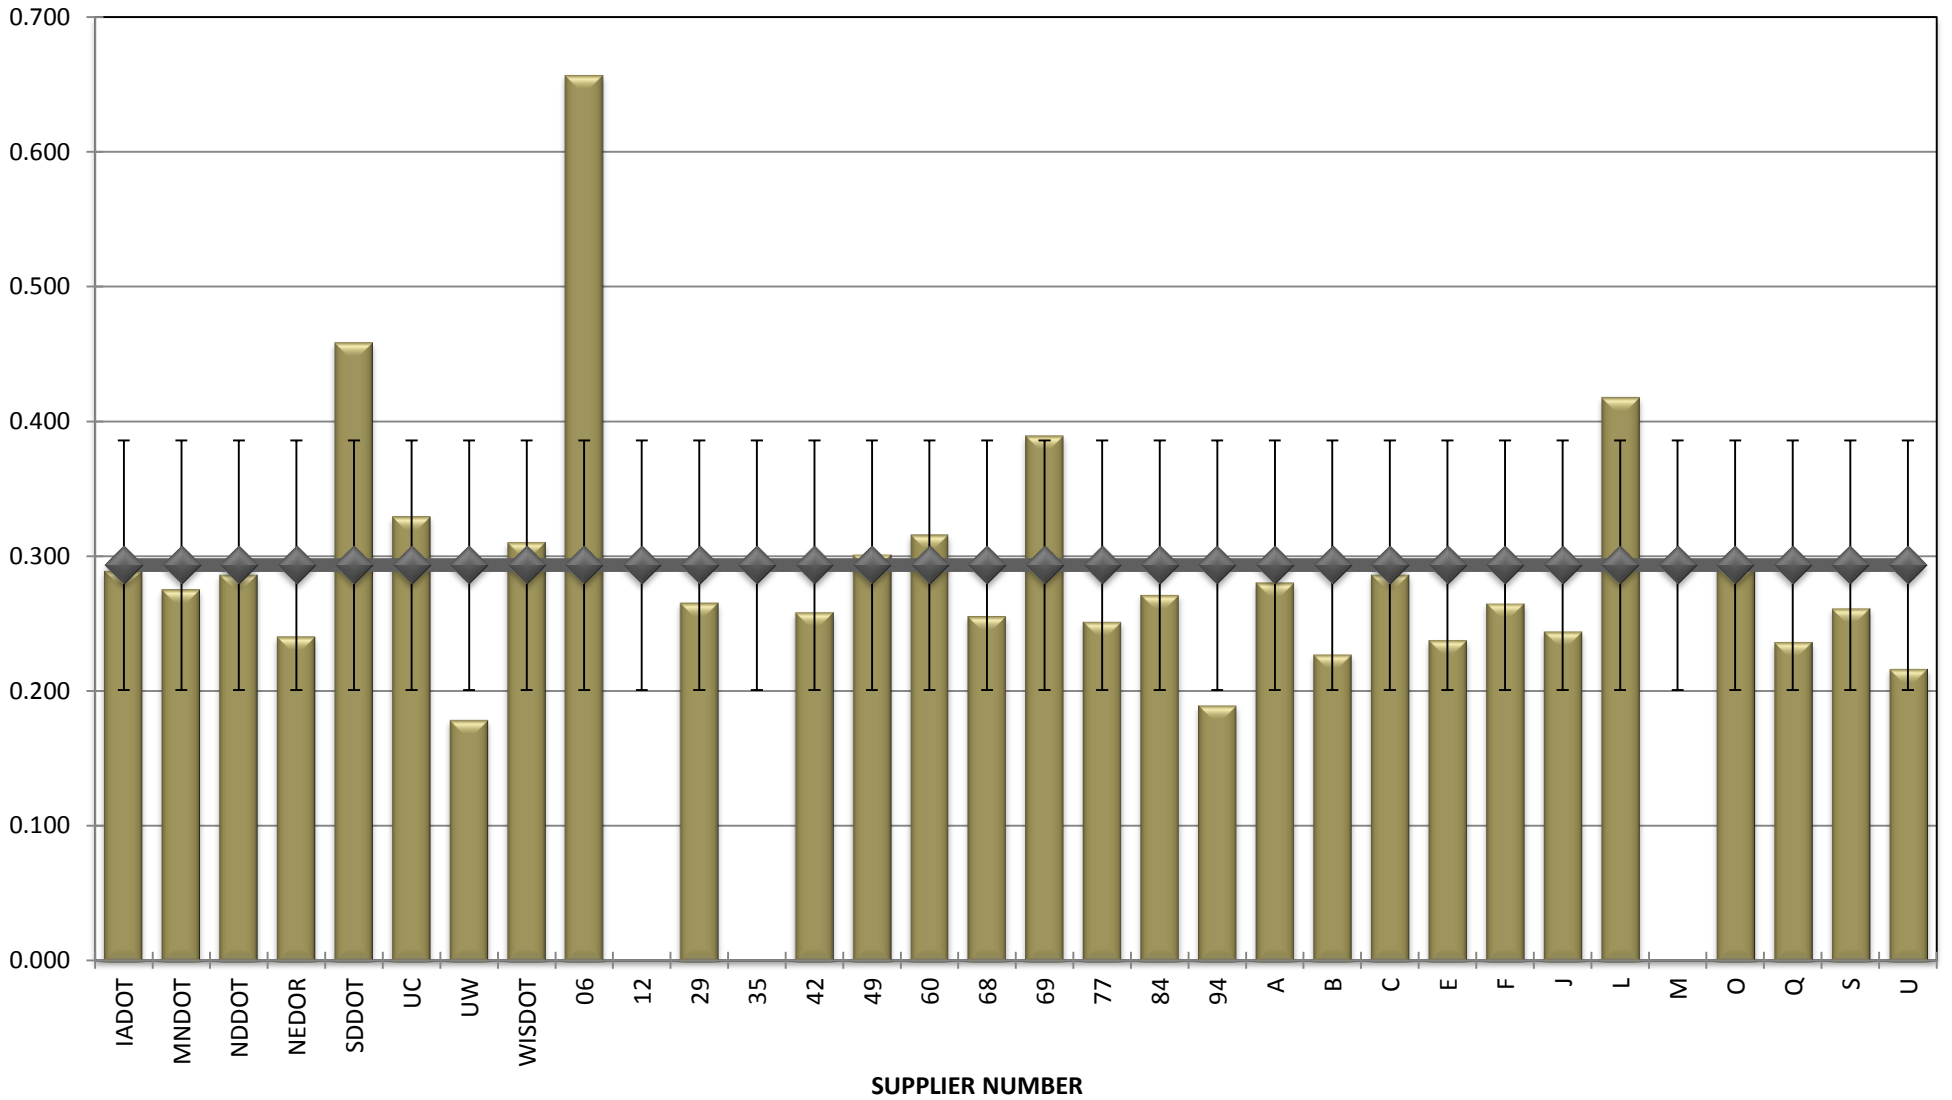

**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2015-2
PG 64-34**

% Recovery @ 3200 Pa

