


COMBINED STATE BINDER GROUP ROUND ROBIN SUMMARY B 2016-2
PG 58S-28

	Rot. Visc.	ODSR	RTFO DSR	PAVDSR	Mass Loss	S-value	m-value	Jnr @ 100 Pa	% Rec. 100 Pa	Jnr @ 3200 Pa	% Rec. @ 3200 Pa
A											
19	0.353	1.82	4.85	4,820	0.546	239	0.342	1.807	6.50	1.990	2.30
51	0.354	1.82	4.59	4,559	0.526	237	0.338	1.898	6.20	2.082	2.00
97	0.356	1.86	4.75	5,069	0.576	237	0.335	1.858	5.30	2.016	2.10
98	0.354	1.82	4.85	4,917	0.594	249	0.338	1.793	7.10	1.992	2.30
AVERAGE	0.354	1.83	4.76	4,841	0.561	241	0.338	1.839	6.28	2.020	2.18
B											
01	0.360	2.07	5.48	3,830	0.536	245	0.322	1.700	5.80	1.800	2.20
17	0.355	2.16	5.45	4,280	0.522	242	0.322	1.600	6.30	1.800	2.40
45	0.380	2.18	5.36	4,050	0.538	224	0.321	1.500	6.30	1.600	2.60
AVERAGE	0.365	2.14	5.43	4,053	0.532	237	0.322	1.600	6.13	1.733	2.40
C											
28	0.348	1.82	4.42	3,725	0.415	285	0.316	1.971	5.51	2.165	1.84
66	0.344	1.84	4.70	4,014	0.415	270	0.320	1.818	4.79	1.973	2.13
90	0.333	1.83	4.58	4,196	0.405	316	0.318	1.891	5.82	2.092	1.94
99	0.359	1.84	4.85	3,006	0.407	313	0.324	1.793	5.48	1.966	2.08
AVERAGE	0.346	1.83	4.64	3,735	0.411	296	0.320	1.868	5.40	2.049	2.00
E											
15	0.343	1.89	4.79	4,680	0.509	254	0.335	1.811	4.69	1.967	1.53
89	0.341	1.87	4.55	4,120	0.516	242	0.331	1.851	7.80	2.103	1.35
AVERAGE	0.342	1.88	4.67	4,400	0.513	248	0.333	1.831	6.25	2.035	1.44
F											
02	0.361	1.87	4.66	4,665	0.465	265	0.323	1.870	4.96	2.038	1.97
11	0.357	1.87	4.93	4,332	0.455	271	0.323	1.752	5.41	1.906	2.16
34	0.344	1.91	4.26	4,561	0.479	258	0.328	2.075	4.22	2.258	1.72
48	0.342	1.92	4.42	4,852	0.480	270	0.325	2.025	4.09	2.197	1.76
56	0.357	1.85	4.71	4,490	0.533	285	0.323	1.852	5.04	2.030	1.30
62	0.357	1.87	4.61	4,610	0.487	283	0.323	1.907	4.55	2.088	1.23
AVERAGE	0.353	1.88	4.60	4,585	0.483	271.9167	0.324	1.913	4.71	2.086	1.69
J											
05	0.351	1.88	4.73	4,514	0.566	251	0.320	1.794	5.17	2.022	1.07
08	0.353	1.88	4.78	4,412	0.530	240	0.321	1.803	4.67	2.017	1.18
10	0.353	1.88	4.85	4,505	0.591	243	0.318	1.741	5.02	1.956	1.45
22	0.353	1.89	4.73	4,286	0.547	244	0.320	1.802	4.27	1.997	1.44
31	0.352	1.88	4.71	4,351	0.585	251	0.323	1.819	4.25	2.029	1.11
41	0.353	1.89	4.72	4,323	0.536	248	0.330	1.819	4.66	2.028	1.25
44	0.351	1.91	4.81	4,123	0.584	246	0.323	1.779	4.67	1.988	1.19
52	0.352	1.87	4.76	4,430	0.539	248	0.317	1.788	4.76	1.998	1.41
AVERAGE	0.352	1.88	4.76	4,368	0.560	246.375	0.322	1.793	4.68	2.004	1.26
L											
25	0.365	1.83	4.73	4,158	0.460	246.5	0.338	1.919	6.02	1.842	2.02
59	0.375	1.93	4.55	4,276	0.441	261	0.326				
AVERAGE	0.370	1.88	4.64	4,217	0.450	253.75	0.332	1.919	6.02	1.842	2.02
M											
04	0.338	1.75	4.01	3,984	0.423	202	0.338				
47	0.333	1.83	4.03	4,236	0.504	243	0.333				
57	0.325	1.77	3.80	3,907	0.422	232	0.334				
AVERAGE	0.332	1.78	3.94	4,042	0.450	226	0.335				
N											
07	0.374	1.91	4.61	4,400	0.471	226	0.344	1.920	5.36	2.120	1.32
43	0.376	1.98	4.77	4,970	0.466	226	0.345	2.030	4.34	2.200	1.20
95	0.370	1.91	4.76	5,160	0.510	250	0.330	1.800	6.60	1.960	2.30
AVERAGE	0.373	1.93	4.71	4,843	0.482	234	0.340	1.917	5.43	2.093	1.61
O											
76	0.348	1.99	5.04	5,960	0.462	244	0.332	1.708	5.34	1.867	1.77
85	0.348	2.02	5.02	5,580	0.474	244	0.330	1.680	7.03	1.900	1.68
AVERAGE	0.348	2.01	5.03	5,770	0.468	244	0.331	1.694	6.19	1.884	1.73
Q											
23	0.340	2.08	4.71	4,492	0.651	253	0.338	1.850	5.15	2.010	2.01
93	0.335	1.93	4.77	4,463	0.646	253	0.334	1.770	5.76	1.940	2.19
AVERAGE	0.338	2.01	4.74	4,478	0.6485	253	0.336	1.810	5.46	1.975	2.10
S											
53	0.325	1.80	3.96	4,191	0.455	241	0.326				
64	0.340	1.80	4.28	4,352	0.510	246	0.334				
AVERAGE	0.333	1.80	4.12	4,272	0.483	243.5	0.330				
U											
13	0.343	1.78	4.23	4,420	0.596	240	0.337	2.050	5.54	2.290	1.27
24	0.356	1.77	4.55	4,540	0.581	233	0.335	1.850	5.48	2.060	1.50
AVERAGE	0.350	1.78	4.39	4,480	0.589	236.5	0.336	1.950	5.51	2.175	1.39
V											
58	0.345	1.83	4.50	4,530	0.675	238	0.334	1.954	4.97	2.151	1.26
78	0.348	1.83	4.80	4,430	0.654	241	0.335	1.806	4.80	1.972	1.45
81	0.345	1.83	4.70	4,880	0.660	250	0.330	1.851	5.05	2.026	1.38
AVERAGE	0.346	1.83	4.67	4,613	0.663	243	0.333	1.870	4.94	2.050	1.36


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2016-2
PG 58S-28**

ROTATIONAL VISCOSITY

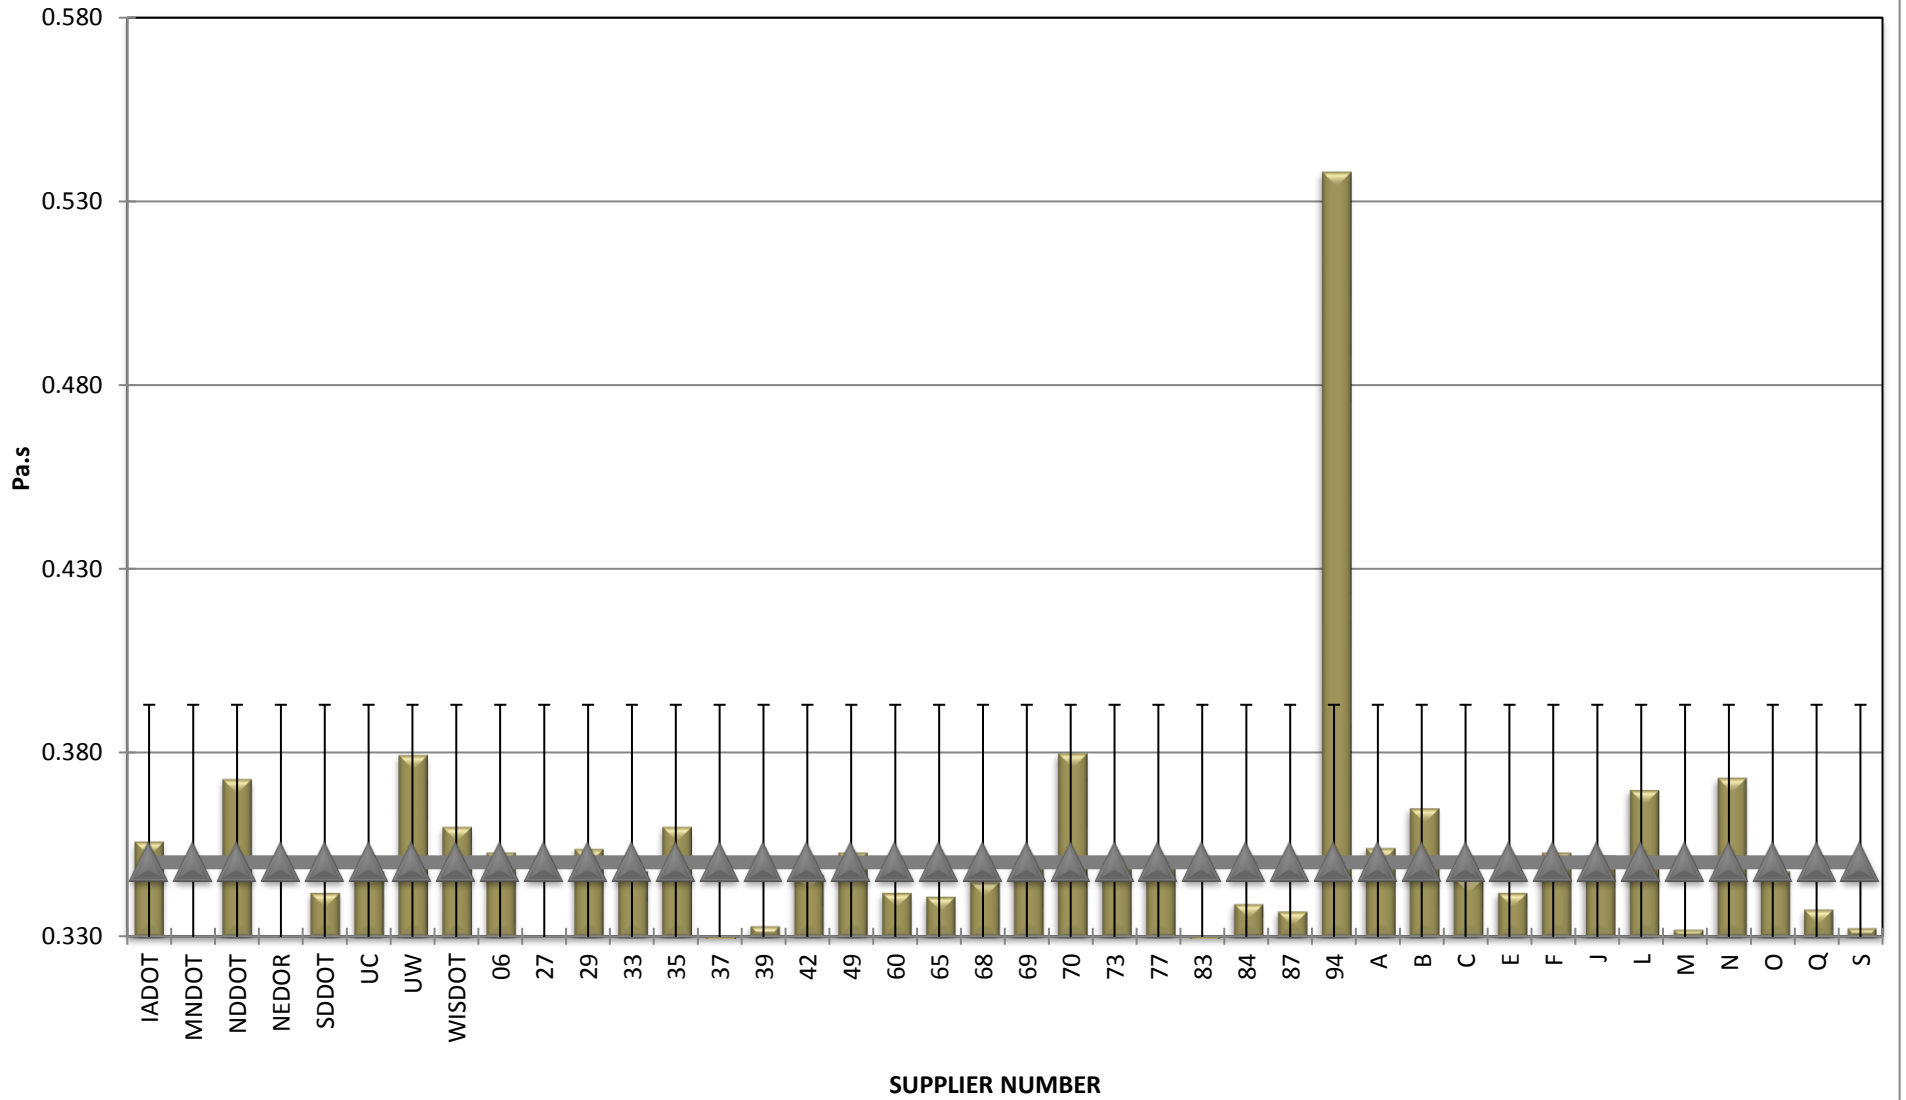


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2016-2
PG 58S-28**

DSR - ORIGINAL

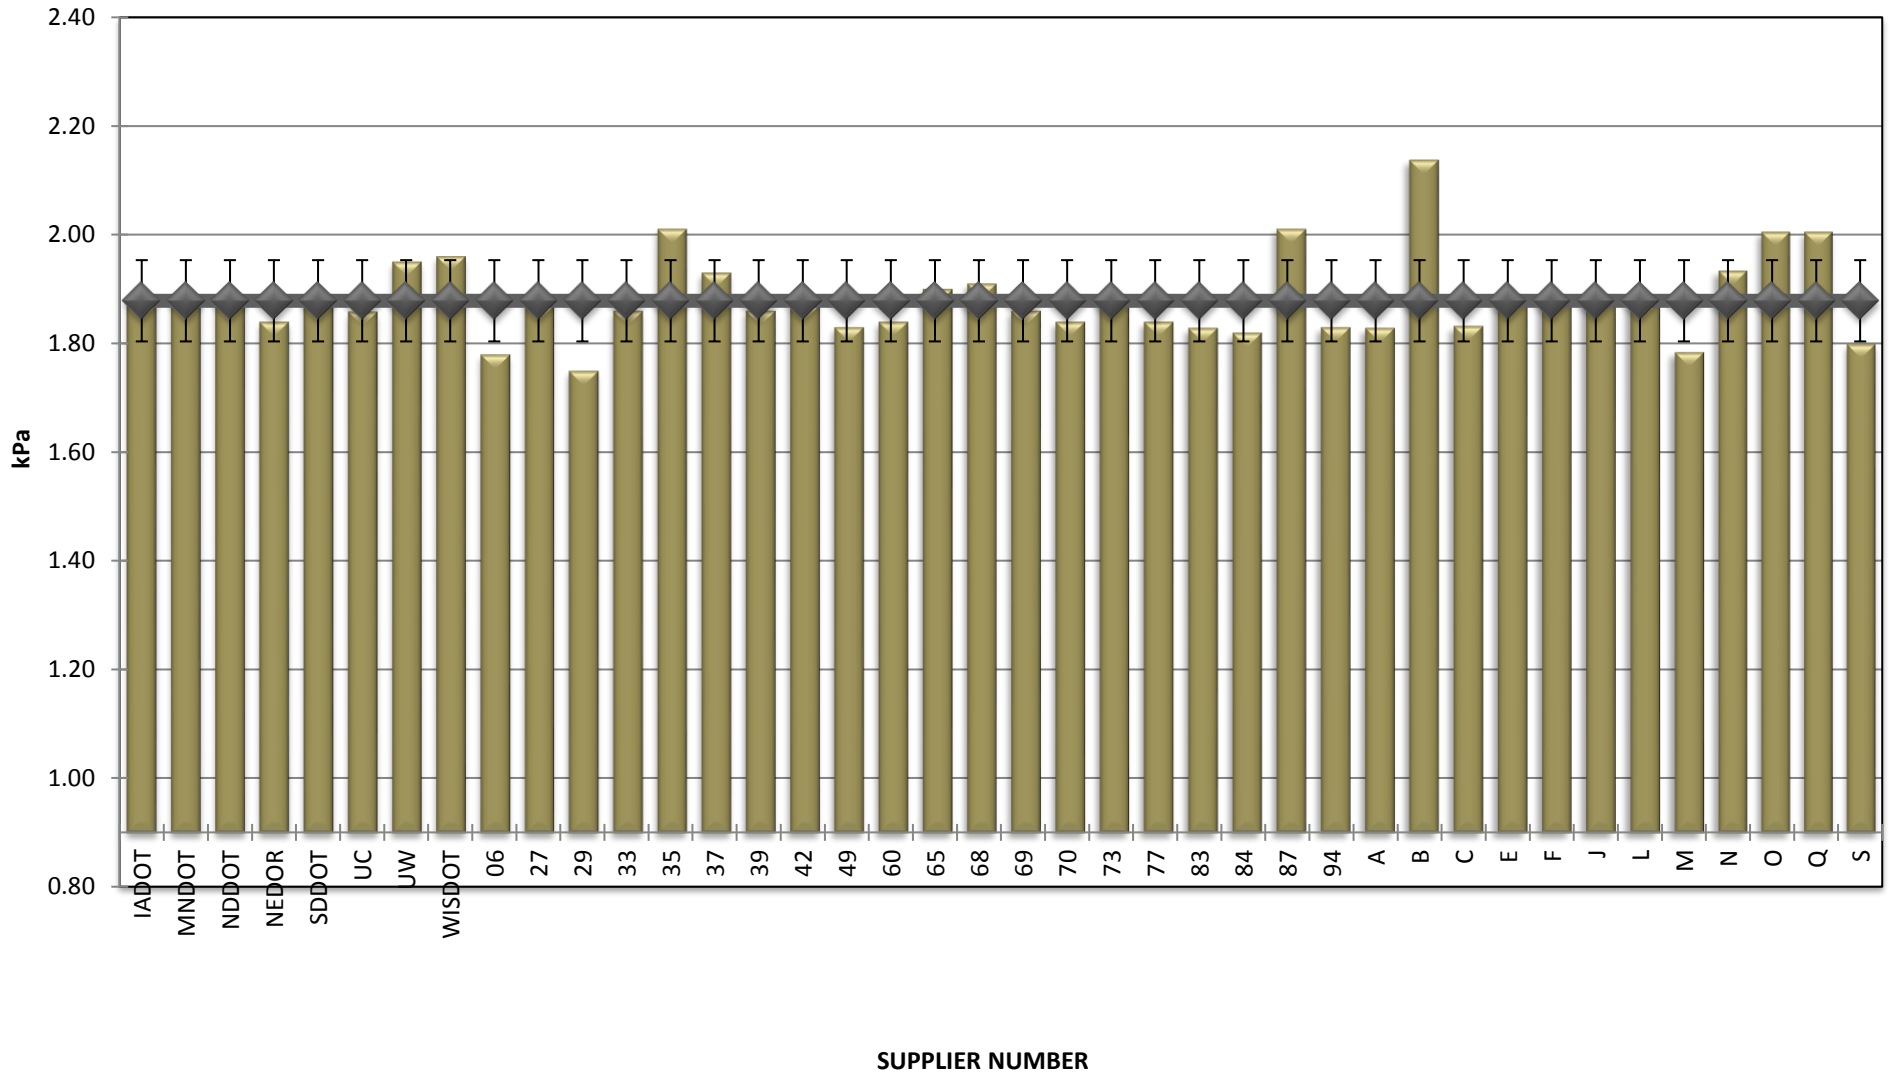


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2016-2
PG 58S-28**

DSR - RTFO

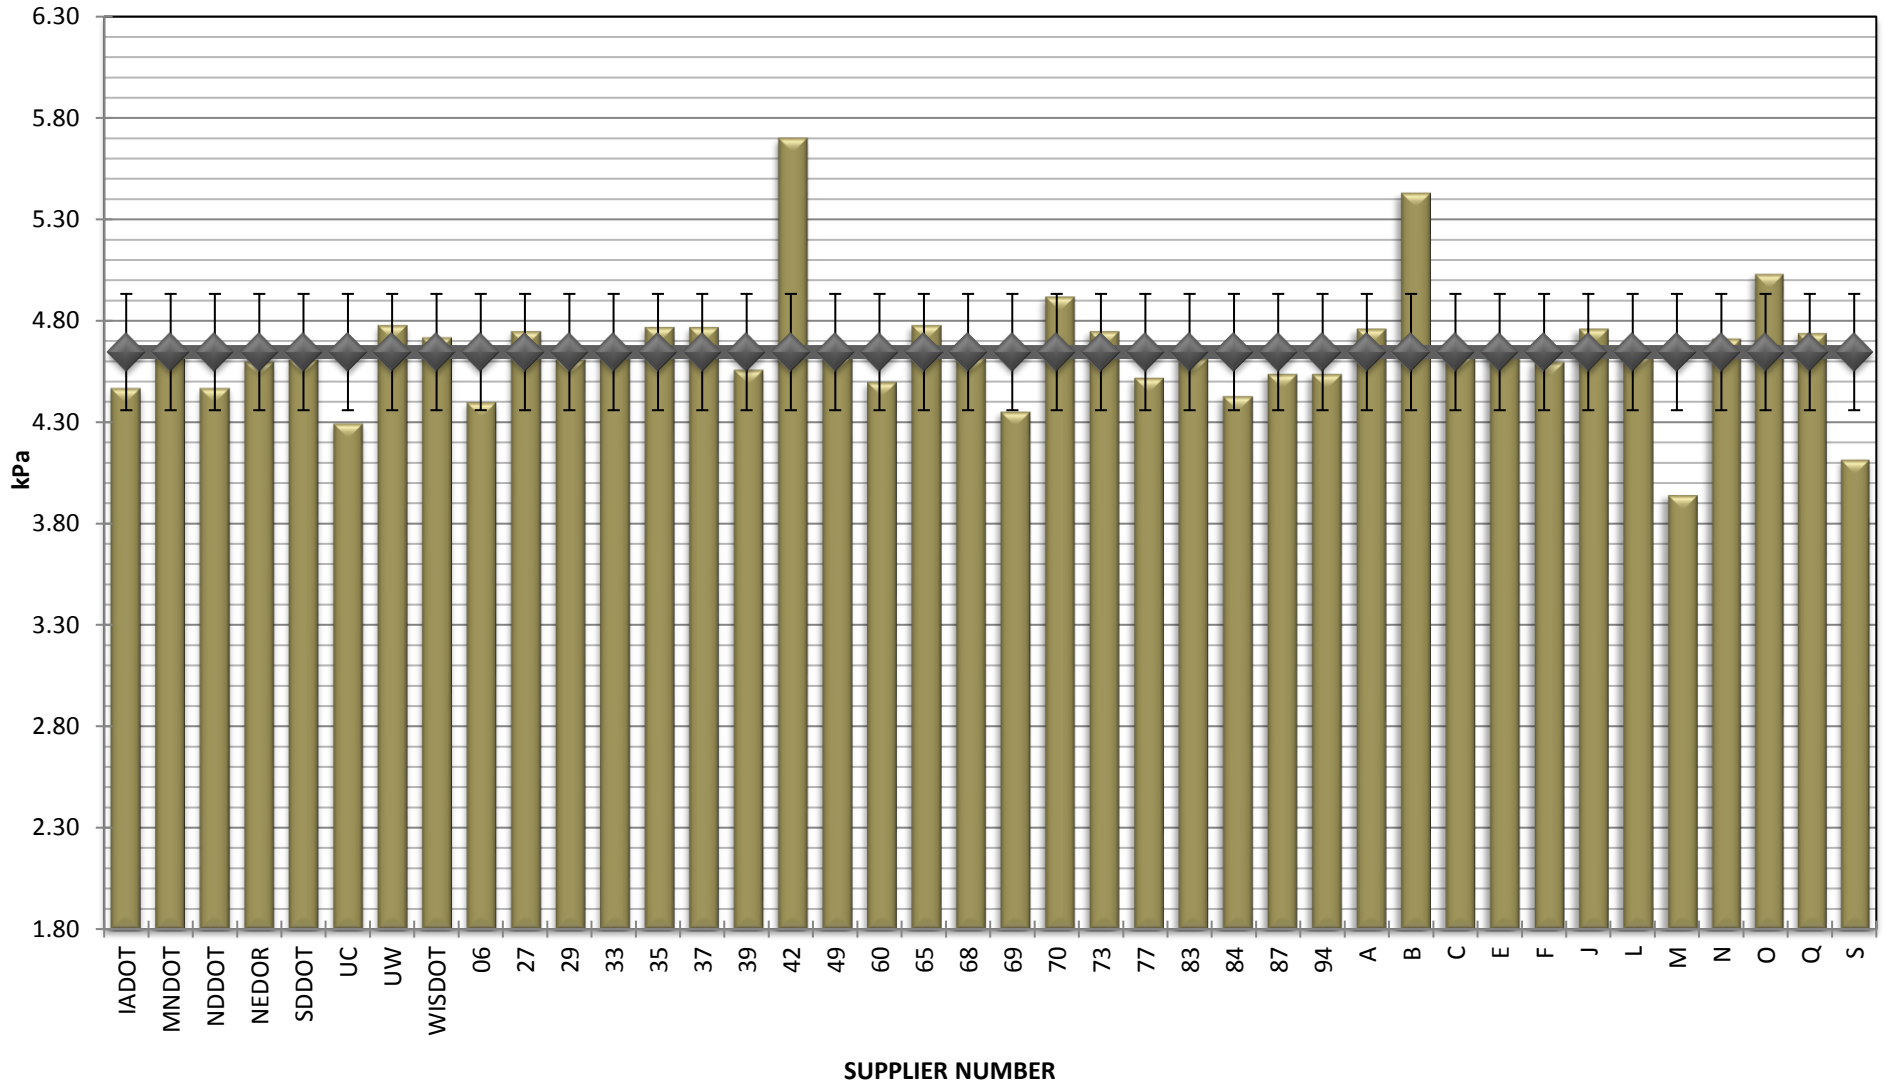


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2016-2
PG 58S-28**

DSR - PAV

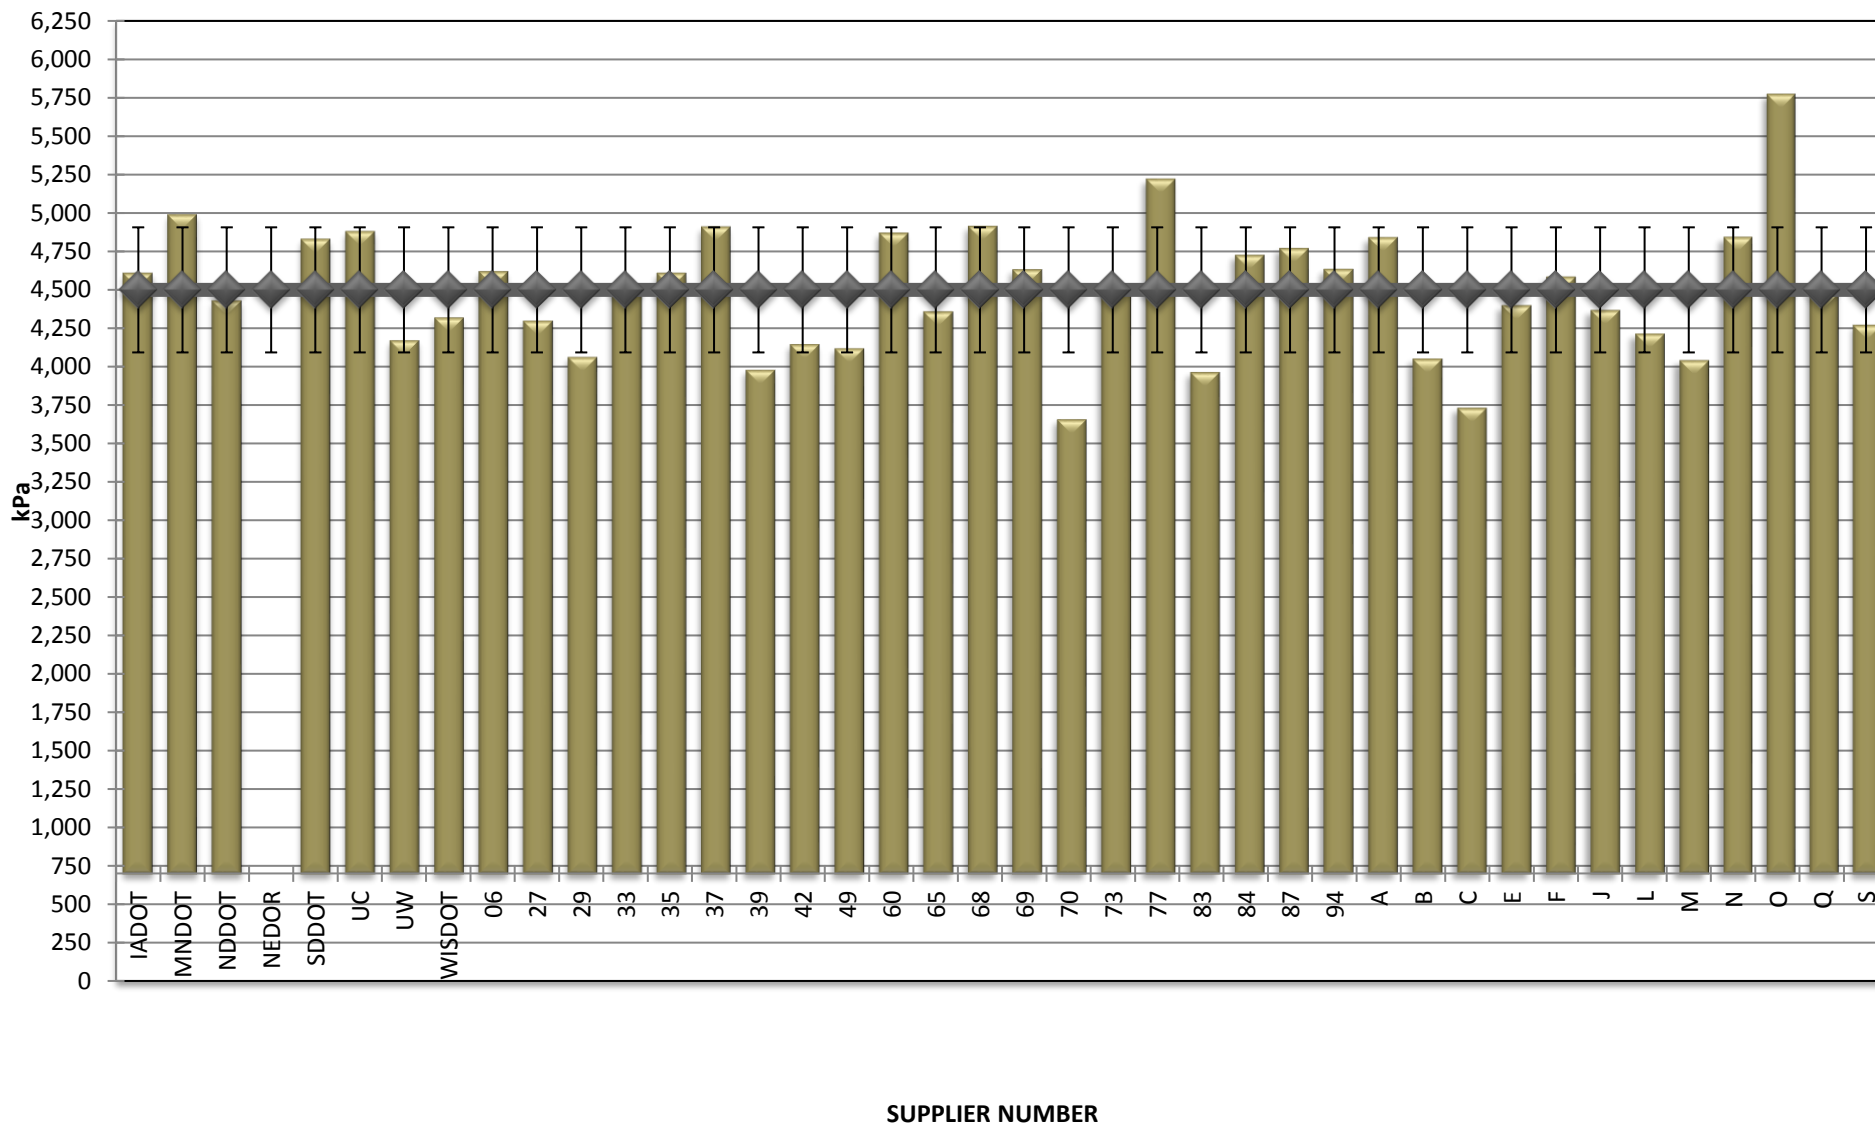


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2016-2
PG 58S-28**

RTFO MASS LOSS

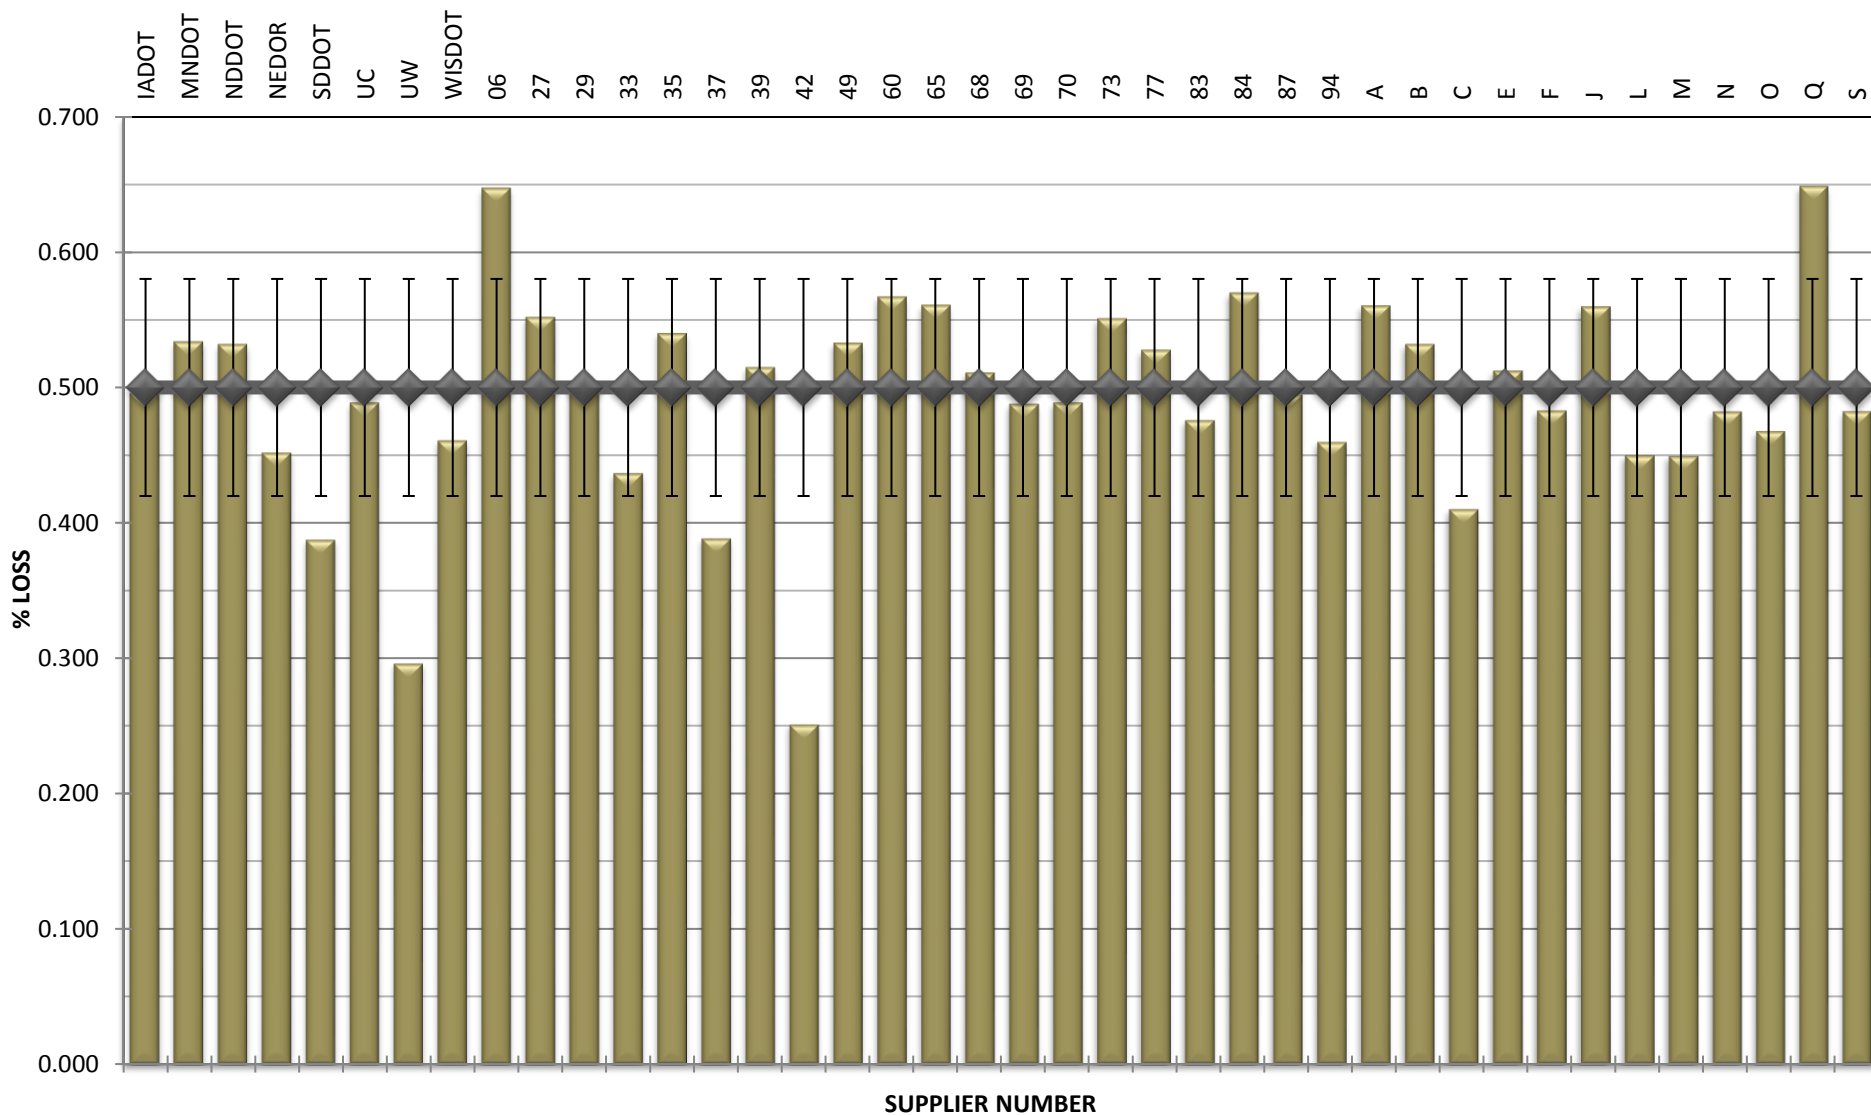


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2016-2
PG 58S-28**

BBR STIFFNESS

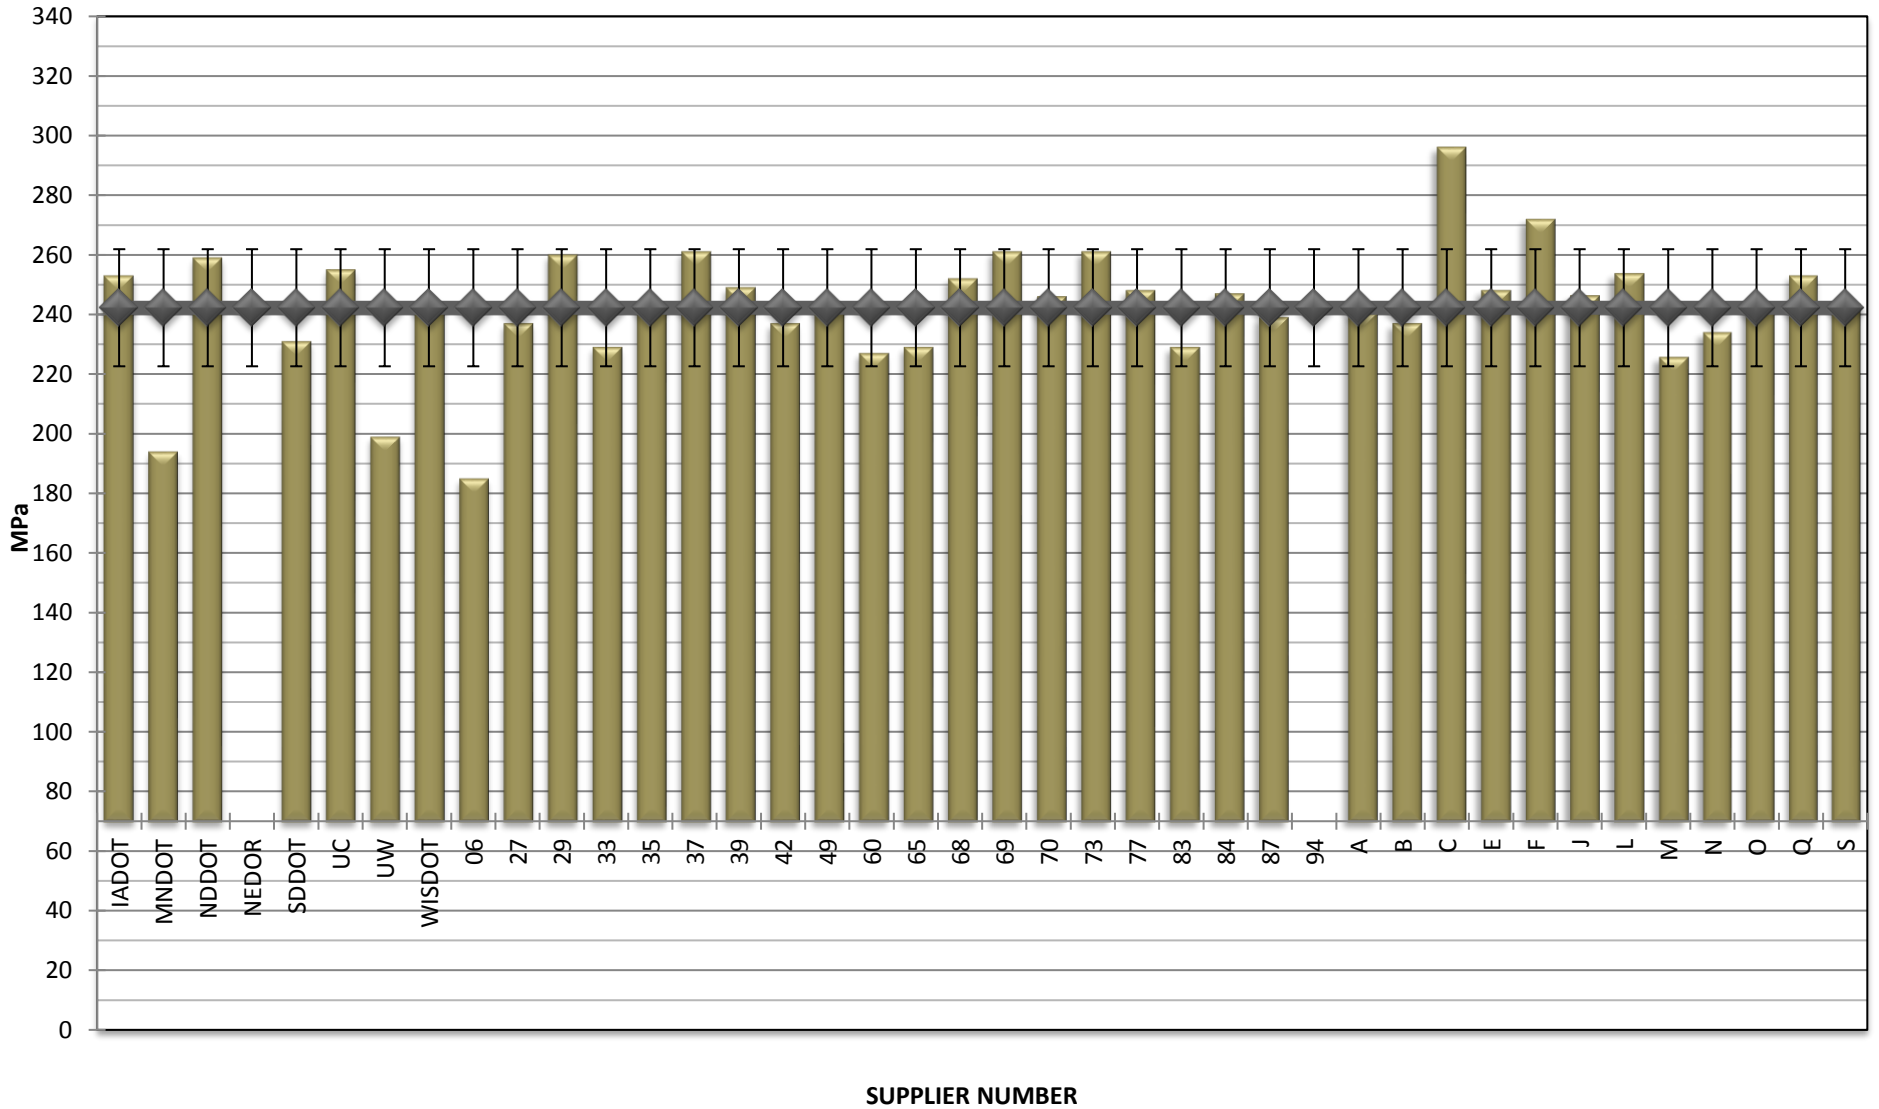


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2016-2
PG 58S-28**

BBR m-VALUE

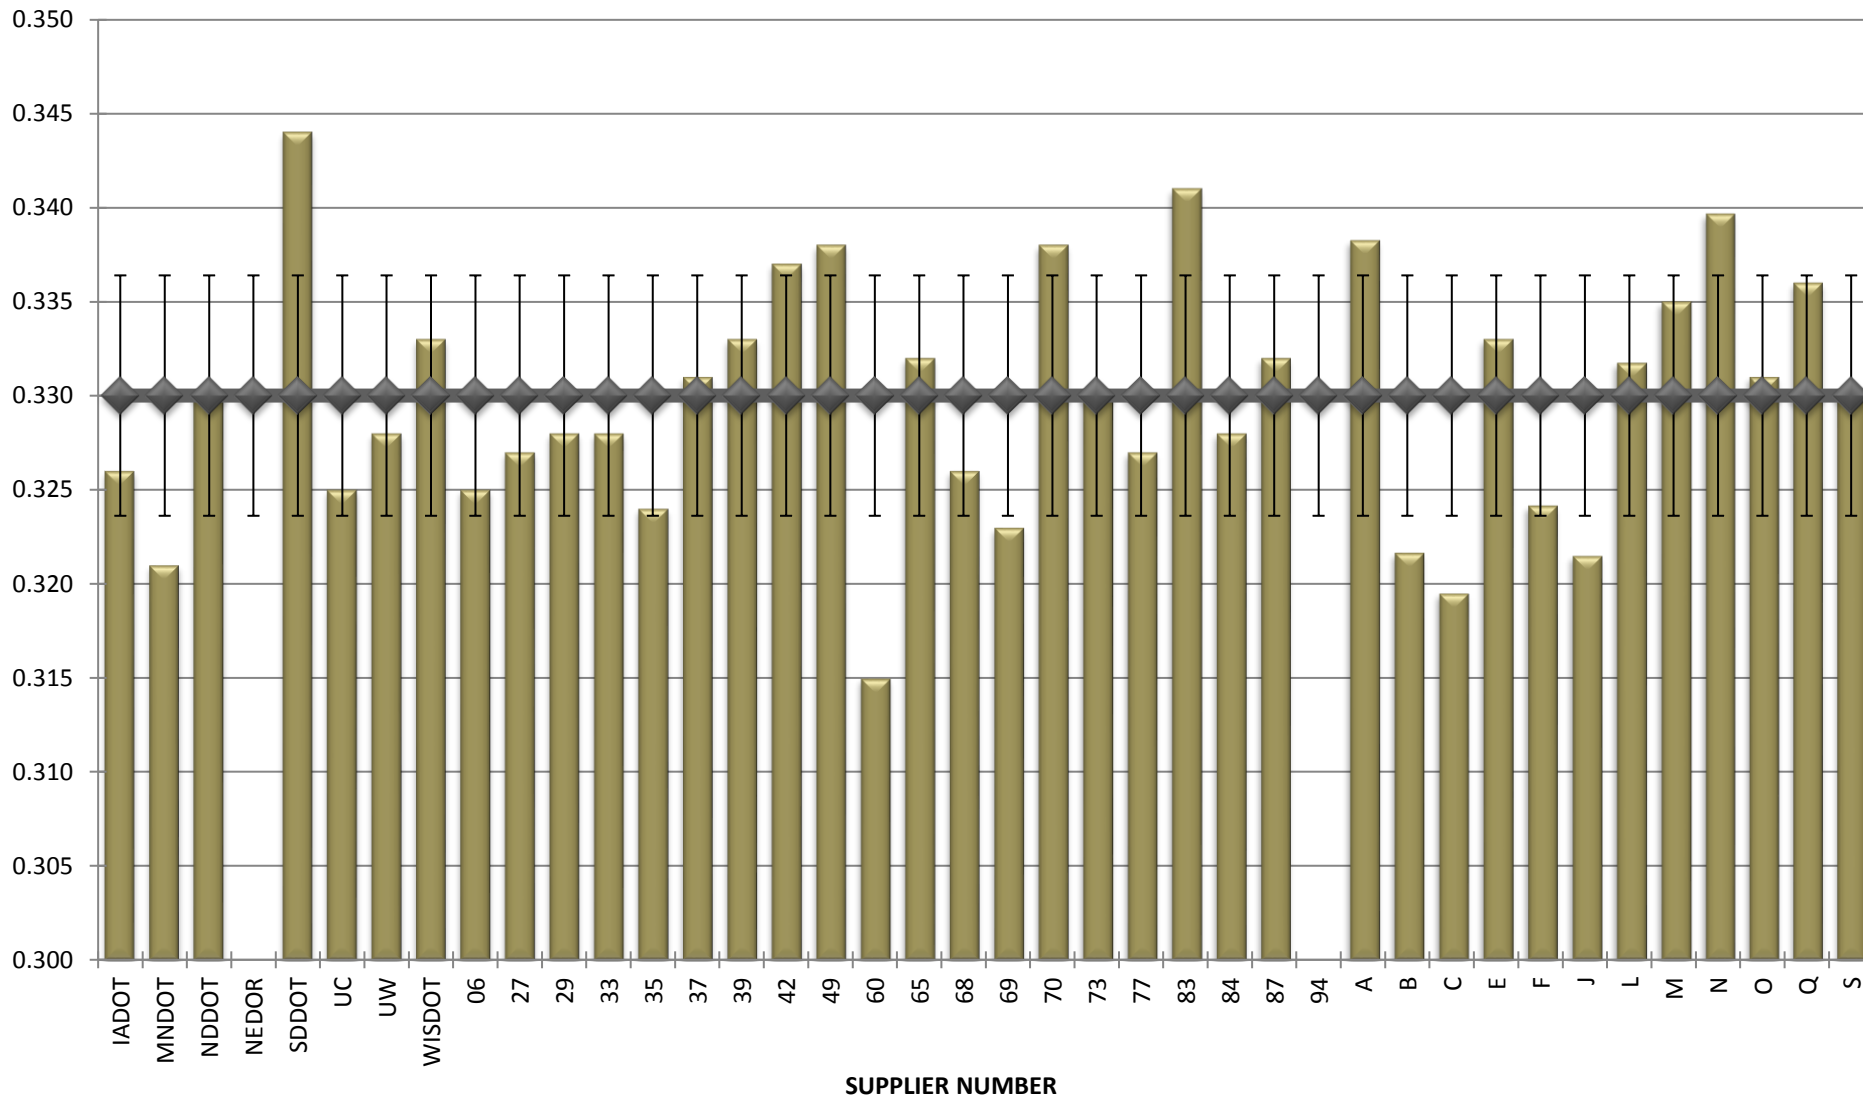


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2016-2
PG 58S-28**

Jnr @ 100 Pa

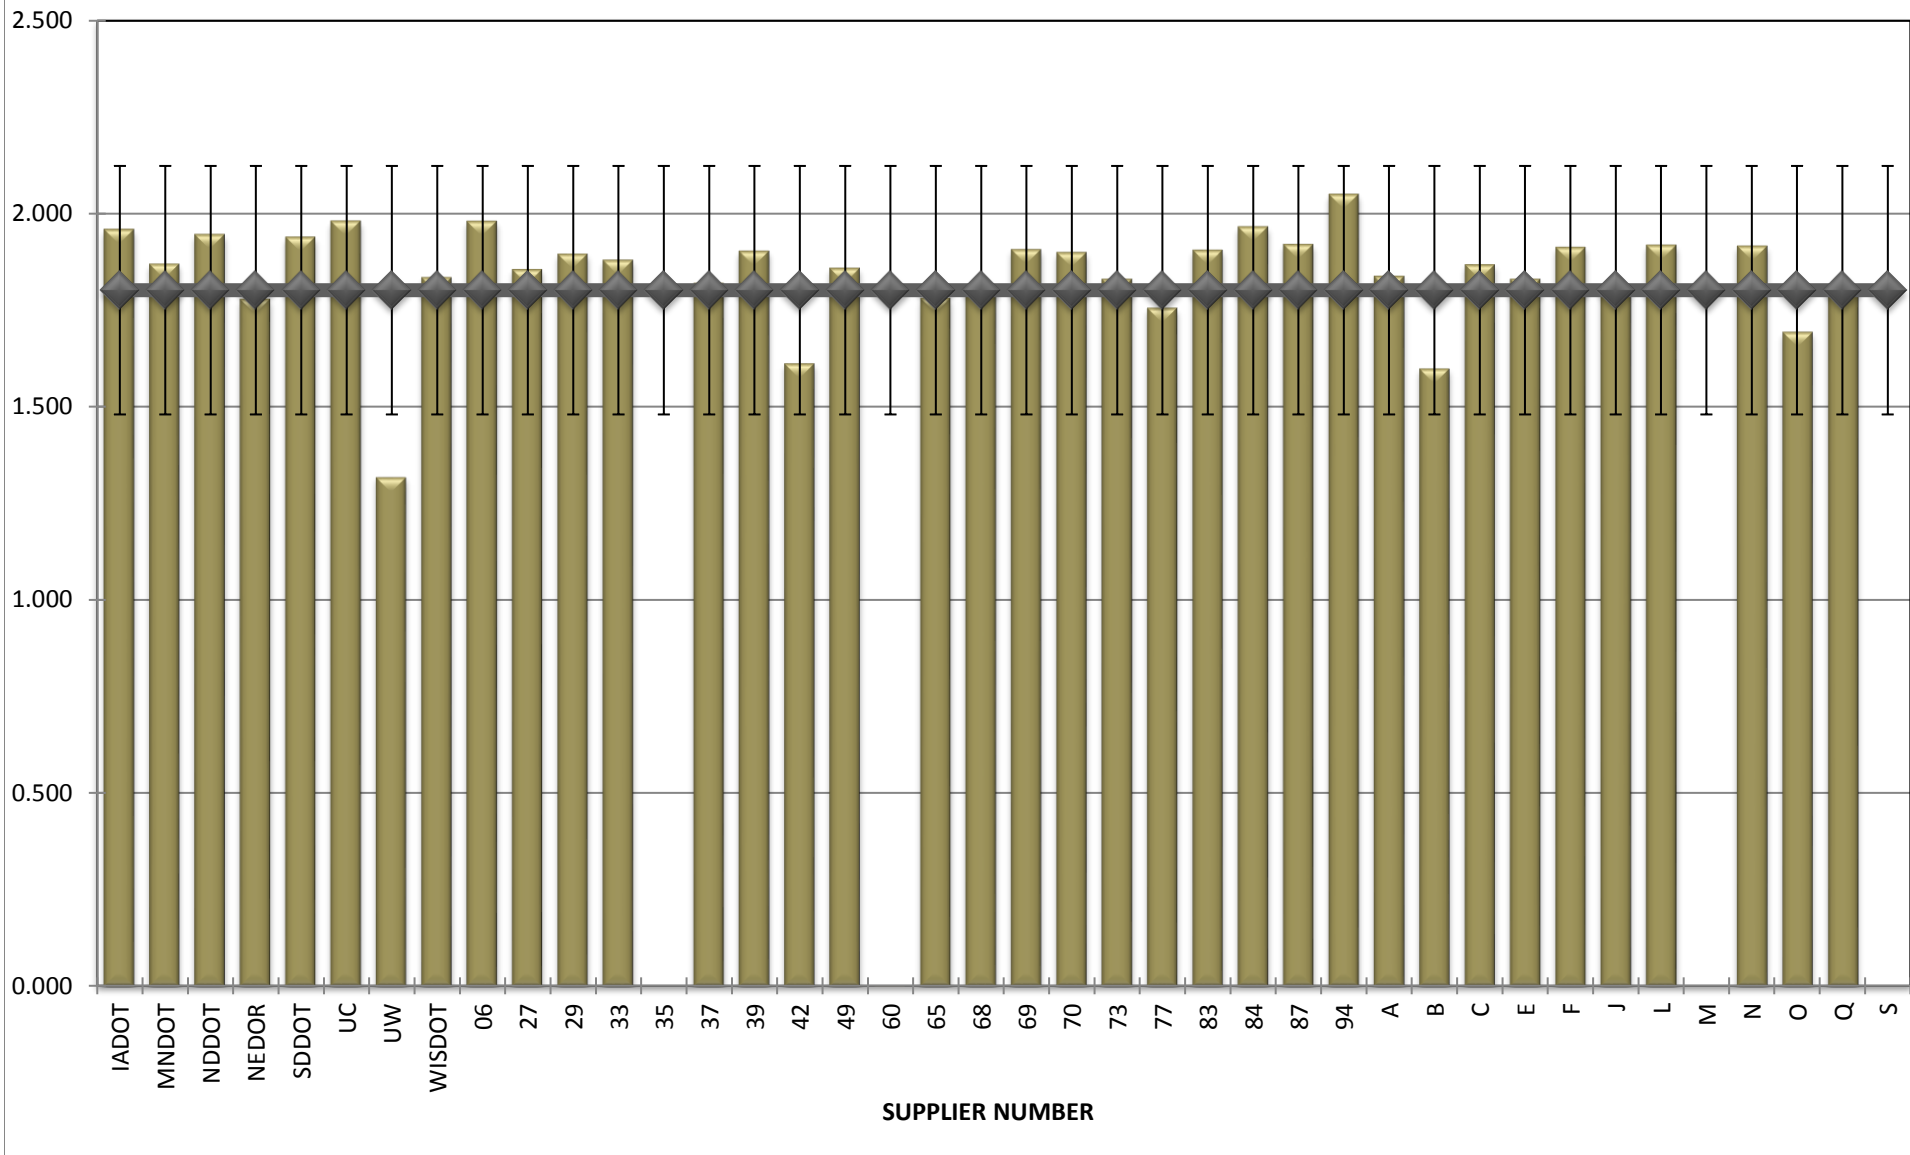


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2016-2
PG 58S-28**

% Recovery @ 100 Pa

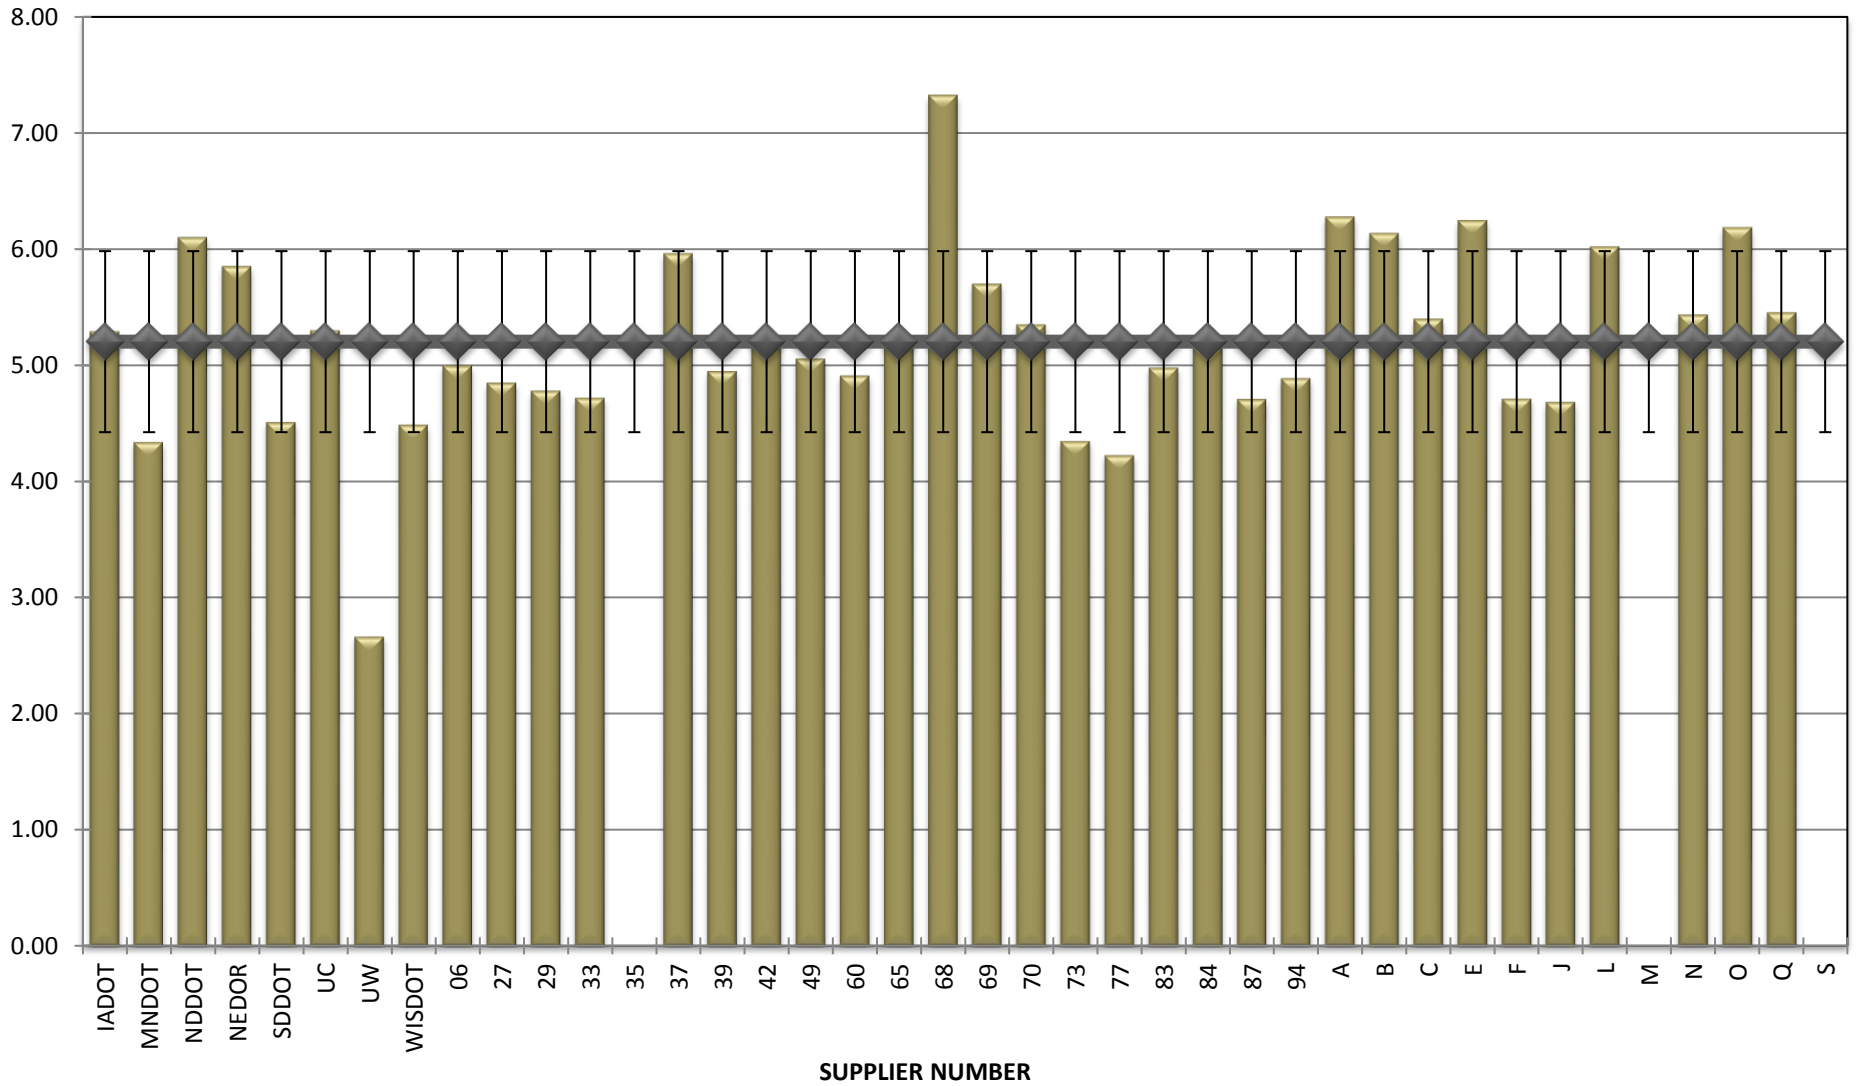

**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2016-2
PG 58S-28**

Jnr @ 3200 Pa

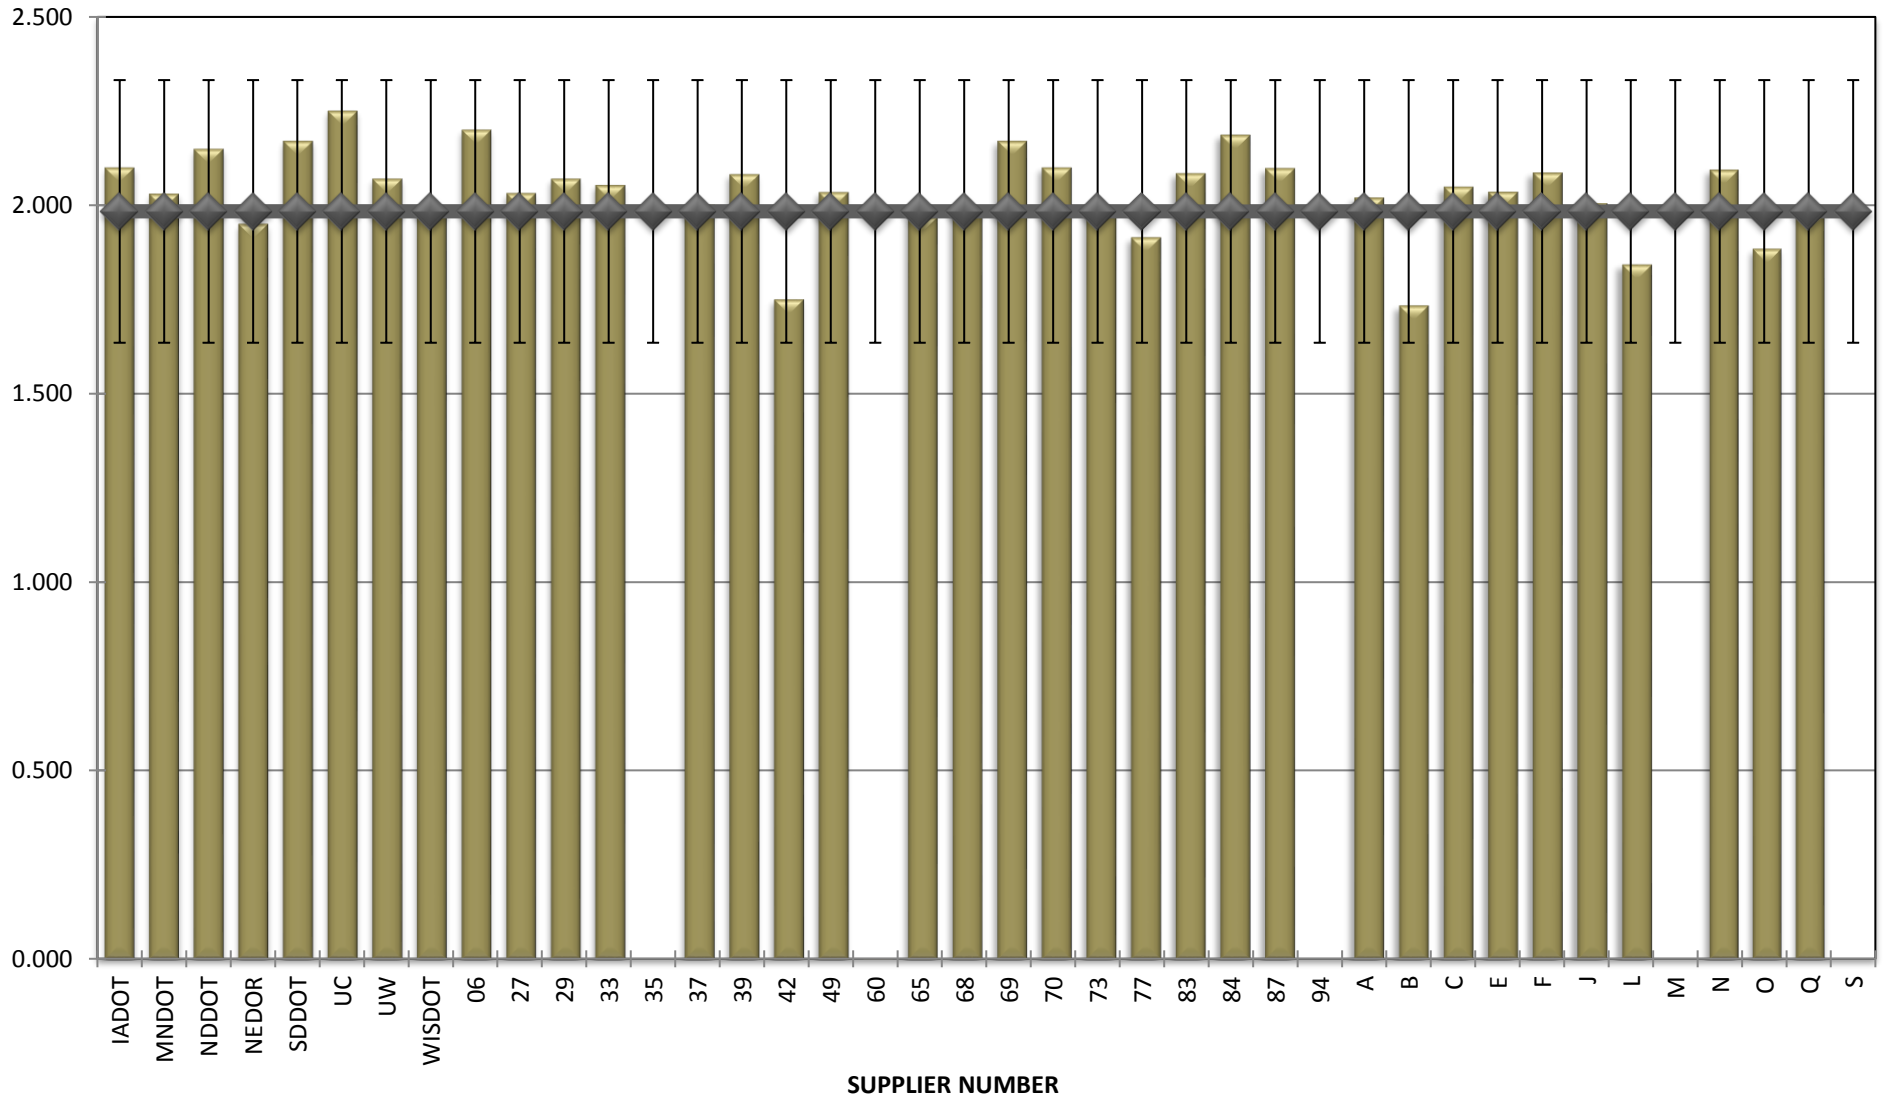

**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2016-2
PG 58S-28**

% Recovery @ 3200 Pa

