


COMBINED STATE BINDER GROUP ROUND ROBIN SUMMARY B 2017-3

	Rot. Visc.	ODSR	RTFO DSR	PAVDSR	Mass Loss	S-value	m-value	Jnr @ 100 Pa %	Rec. 100 Pa	Jnr @ 3200 Pa %	Rec. @ 3200 Pa
A											
19	0.424	1.67	4.43	2,594	0.606	240	0.320	0.357	74.70	0.550	63.20
51	0.424	1.68	4.33	2,488	0.604	246	0.323	0.363	74.80	0.561	63.20
97	0.422	1.68	4.49	2,689	0.651	231	0.317	0.357	74.50	0.546	63.20
98	0.422	1.67	4.37	2,453	0.626	239	0.327	0.356	75.00	0.555	63.20
AVERAGE	0.423	1.67	4.40	2,556	0.622	239	0.322	0.358	74.75	0.553	63.20
B											
01	0.428	1.62	4.35	3,090	0.619	218	0.318	0.330	75.40	0.510	64.10
17	0.458	1.67	4.05	3,540	0.582	216	0.314	0.400	73.30	0.640	60.90
45	0.393	1.64	3.78	3,380	0.536	216	0.311	0.460	71.90	0.720	59.60
AVERAGE	0.426	1.64	4.06	3,337	0.579	216.667	0.314	0.397	73.53	0.623	61.53
C											
28	0.393	1.67	3.95	2,835	0.538	270	0.298	0.420	72.95	0.652	61.61
66	0.407	1.71	4.20	2,827	0.545	258	0.300	0.378	74.18	0.601	62.10
90	0.391	1.67	3.96	2,913	0.612	266	0.309	0.407	73.91	0.648	61.57
99	0.407	1.64	4.10	2,995	0.540	266	0.303	0.387	72.95	0.588	61.40
AVERAGE	0.400	1.67	4.05	2,893	0.559	265	0.303	0.398	73.50	0.622	61.67
E											
15	0.413	1.67	4.36	2,430	0.641	202	0.320	0.362	74.15	0.575	61.58
89	0.400	1.65	4.23	1,500	0.662	203	0.322	0.374	74.14	0.600	61.22
AVERAGE	0.407	1.66	4.30	1,965	0.652	203	0.321	0.368	74.15	0.588	61.40
F											
02	0.434	1.73	4.50	2,854	0.512	260	0.317	0.326	75.90	0.506	64.86
11	0.412	1.69	4.29	2,918	0.524	264	0.318	0.347	75.71	0.555	63.55
34	0.408	1.72	4.28	2,800	0.591	259	0.305	0.355	75.14	0.549	63.66
48	0.410	1.75	4.27	2,890	0.597	261	0.313	0.353	74.92	0.541	63.72
56	0.418	1.68	4.00	2,820	0.583	261	0.317	0.376	75.30	0.607	62.67
62	0.432	1.73	4.07	2,968	0.638	266	0.312	0.369	75.47	0.597	62.88
AVERAGE	0.419	1.72	4.24	2,875	0.574	261.833	0.314	0.354	75.41	0.559	63.56
J											
05	0.416	1.72	4.32	2,820	0.614	245	0.327	0.393	73.18	0.642	59.36
08	0.414	1.62	4.51	2,730	0.609	241	0.325	0.370	73.70	0.607	60.10
10	0.426	1.70	4.24	2,727	0.654	241	0.316	0.309	77.51	0.564	63.14
22	0.419	1.69	4.28	2,702	0.667	241	0.312	0.329	76.65	0.604	61.92
31	0.414	1.73	4.58	3,030	0.607	218	0.320	0.331	75.55	0.524	63.80
41	0.417	1.69	4.31	2,690	0.603	201	0.321	0.369	74.51	0.599	61.52
44	0.419	1.70	4.24	2,857	0.638	244	0.313	0.323	76.68	0.557	63.42
52	0.422	1.70	4.29	2,645	0.678	242	0.313	0.310	77.26	0.569	62.63
AVERAGE	0.418	1.69	4.35	2,775	0.634	234.125	0.318	0.342	75.63	0.583	61.99
L											
25	0.450	1.58	3.94	3,229	0.610	235	0.332	0.379	72.93	0.592	60.32
59	0.462	1.77	4.35	1,697	0.528	237	0.324	0.418	69.70	0.551	62.50
AVERAGE	0.456	1.67	4.14	2,463	0.569	236	0.328	0.399	71.32	0.571	61.41
M											
04	0.333	1.66	3.85	2,060	0.333	219	0.330				
47	0.375	1.66	4.14	2,358	0.529	228	0.323				
57	0.340	1.68	3.82	1,765	0.350	222	0.332	0.317	79.10	0.699	60.20
AVERAGE	0.349	1.67	3.94	2,061	0.404	223	0.328	0.317	79.10	0.699	60.20
N											
43	0.456	1.67	4.22	2,840	0.583	235	0.318	0.480	68.48	0.633	68.61
95	0.449	1.73	4.15	2,680	0.570	241	0.316	0.486	68.11	0.648	60.16
AVERAGE	0.453	1.70	4.19	2,760	0.577	238	0.317	0.463	68.30	0.641	64.39
O											
76	0.398	1.64	4.06	3,050	0.594	237	0.323	0.478	68.66	0.632	61.01
85	0.399	1.65	4.11	2,920	0.601	248	0.322	0.467	68.98	0.614	61.51
AVERAGE	0.399	1.65	4.09	2,985	0.598	243	0.323	0.473	68.82	0.623	61.26
Q											
23	0.425	1.61	4.02	2,839	0.458	242	0.321	0.371	75.02	0.589	62.78
93	0.415	1.60	4.00	2,827	0.540	245	0.319	0.380	75.17	0.603	62.84
AVERAGE	0.420	1.61	4.01	2,833	0.499	244	0.320	0.376	75.10	0.596	62.81
S											
53	0.427	1.64	3.92	1,752	0.667	264	0.314	0.426	73.01	0.831	51.08
64	0.428	1.68	3.87	1,711	0.654	250	0.323	0.427	73.25	0.829	51.70
AVERAGE	0.428	1.66	3.90	1,732	0.661	257	0.319	0.427	73.13	0.830	51.39
U											
13	0.424	1.65	4.40	3,010	0.583	249	0.314	0.343	75.10	0.540	63.48
24	0.428	1.61	4.18	2,880	0.558	254	0.314	0.373	74.45	0.594	61.76
AVERAGE	0.426	1.63	4.29	2,945	0.571	252	0.314	0.358	74.78	0.567	62.62
V											
58	0.417	1.67	4.08	2,840	0.678	250	0.323	0.368	74.38	0.588	62.01
78	0.422	1.69	4.00	2,850	0.702	251	0.318	0.386	74.40	0.626	61.30
81	0.400	1.68	4.27	1,610	0.647	194	0.325	0.368	74.35	0.589	61.54
AVERAGE	0.413	1.68	4.12	2,433	0.676	232	0.322	0.374	74.38	0.601	61.62


COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2017-3

ROTATIONAL VISCOSITY

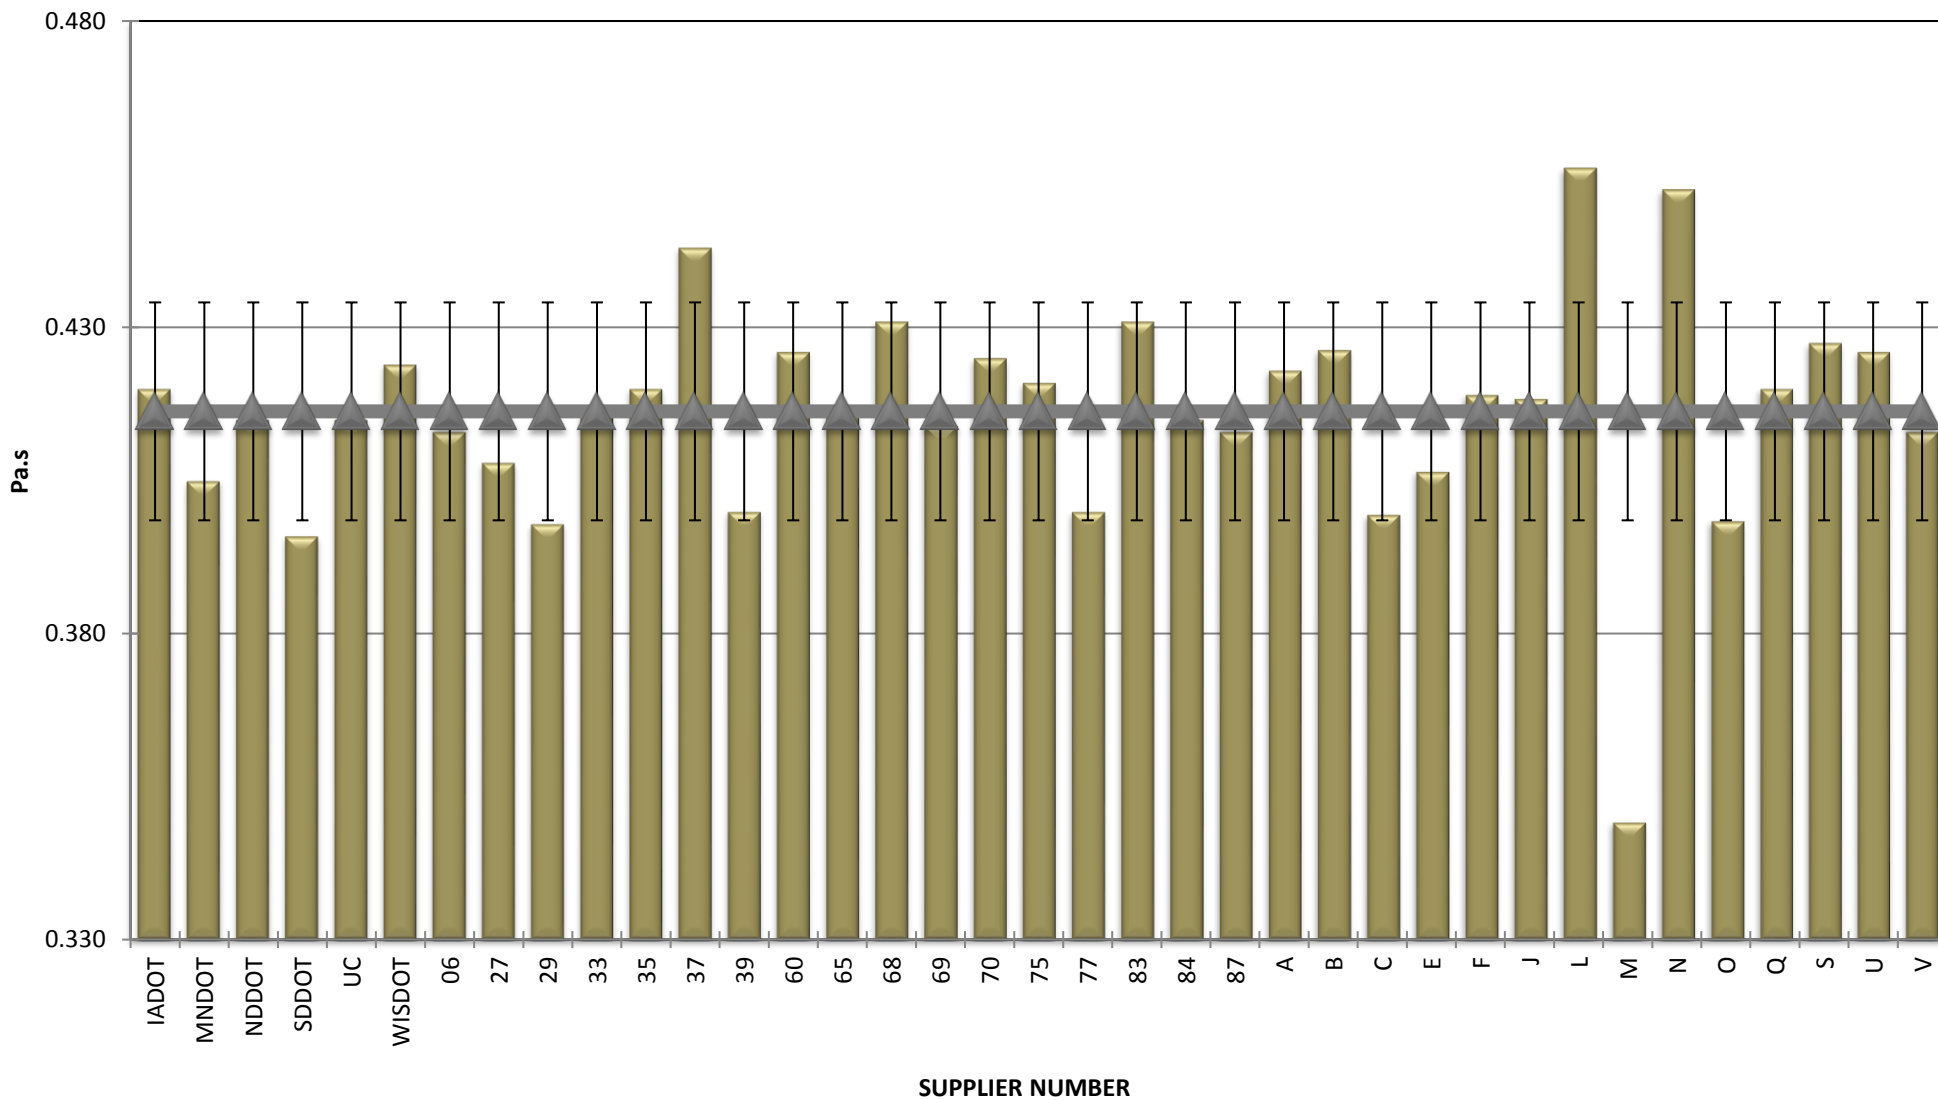


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2017-3**

DSR - ORIGINAL

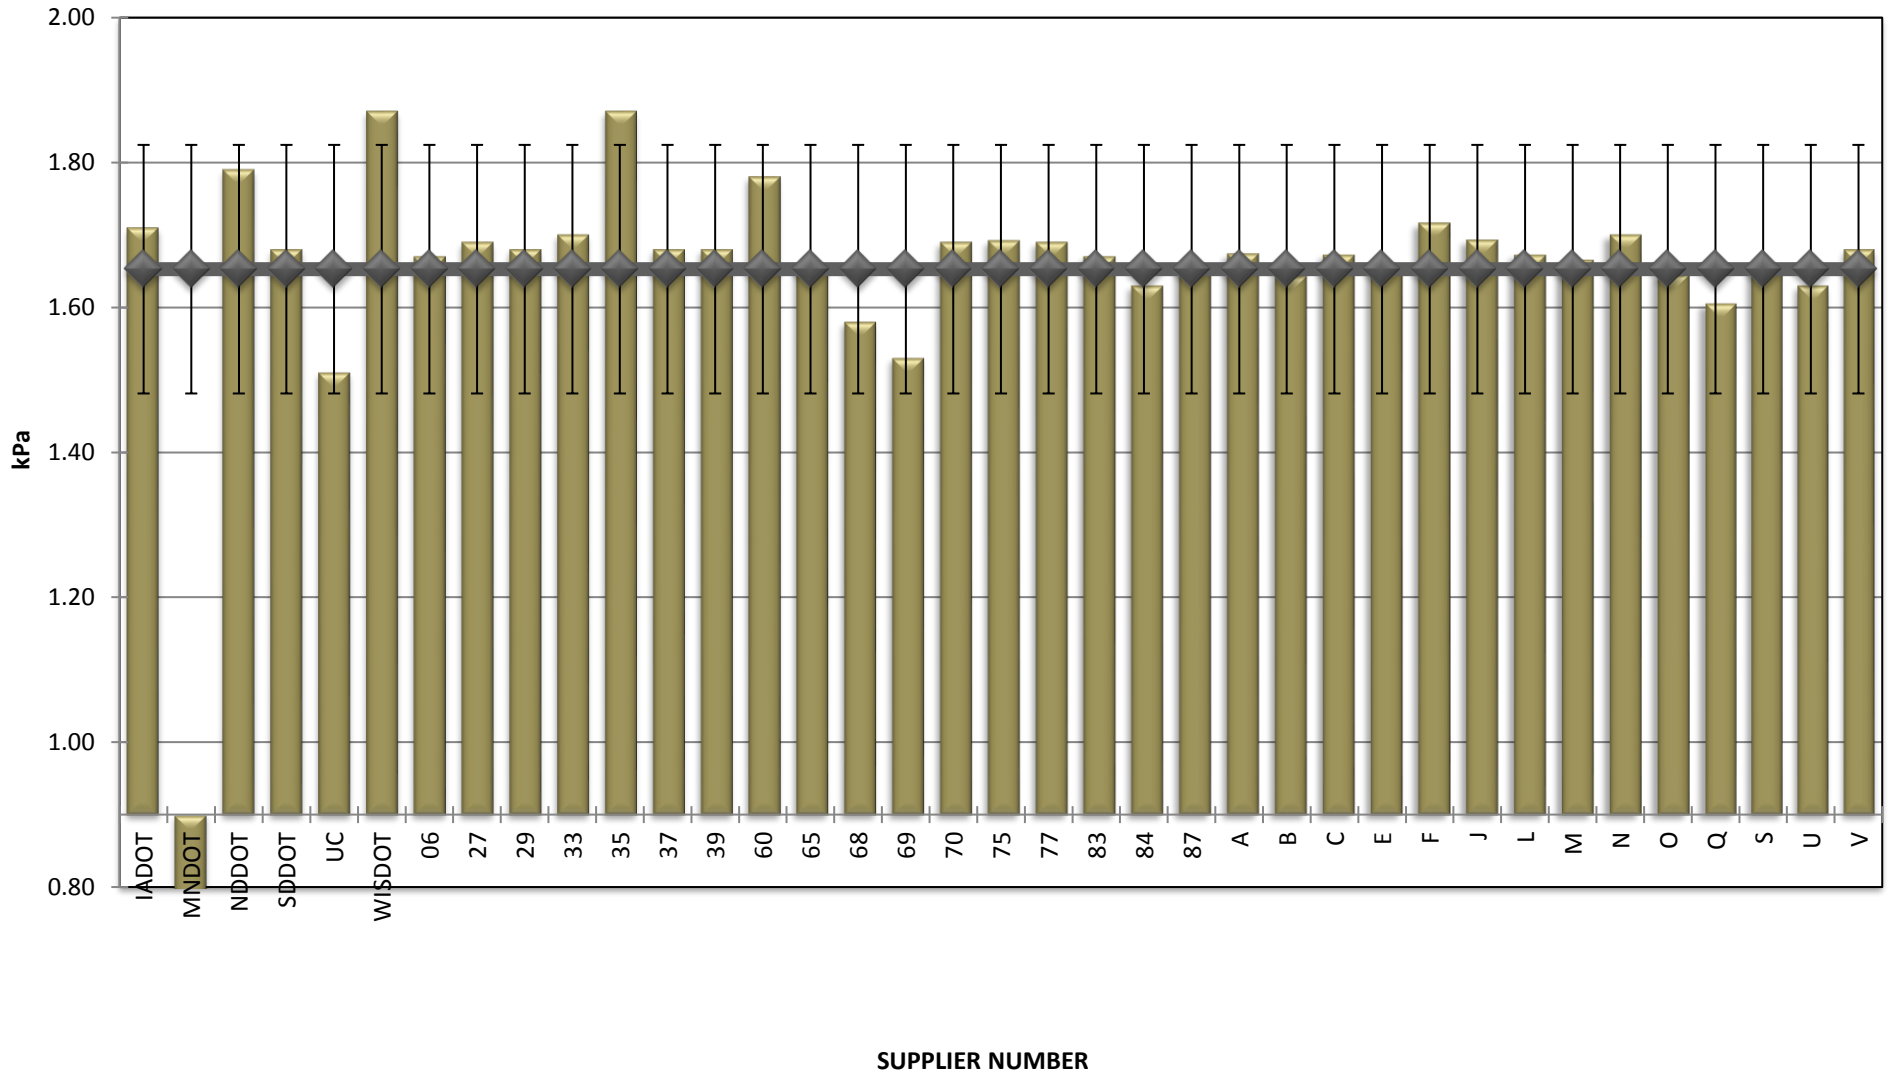


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2017-3**

DSR - RTFO

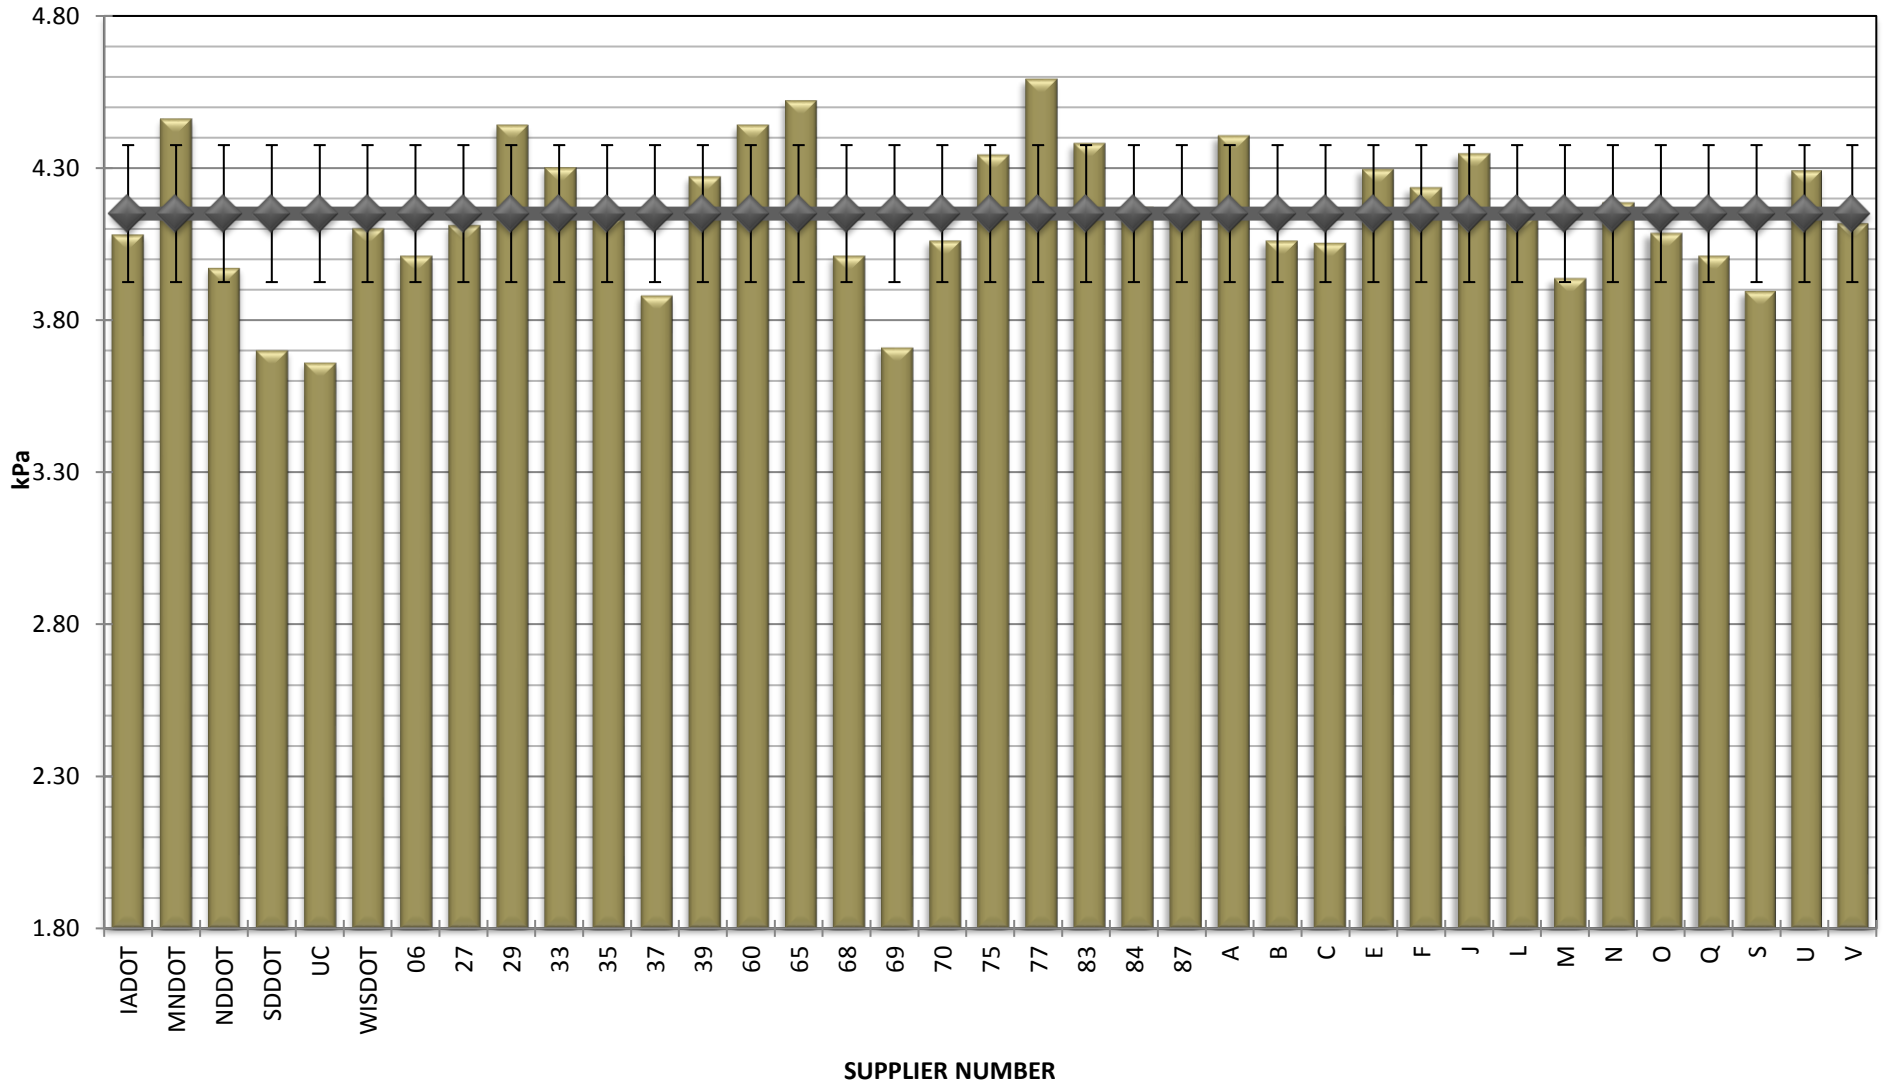


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2017-3**

DSR - PAV

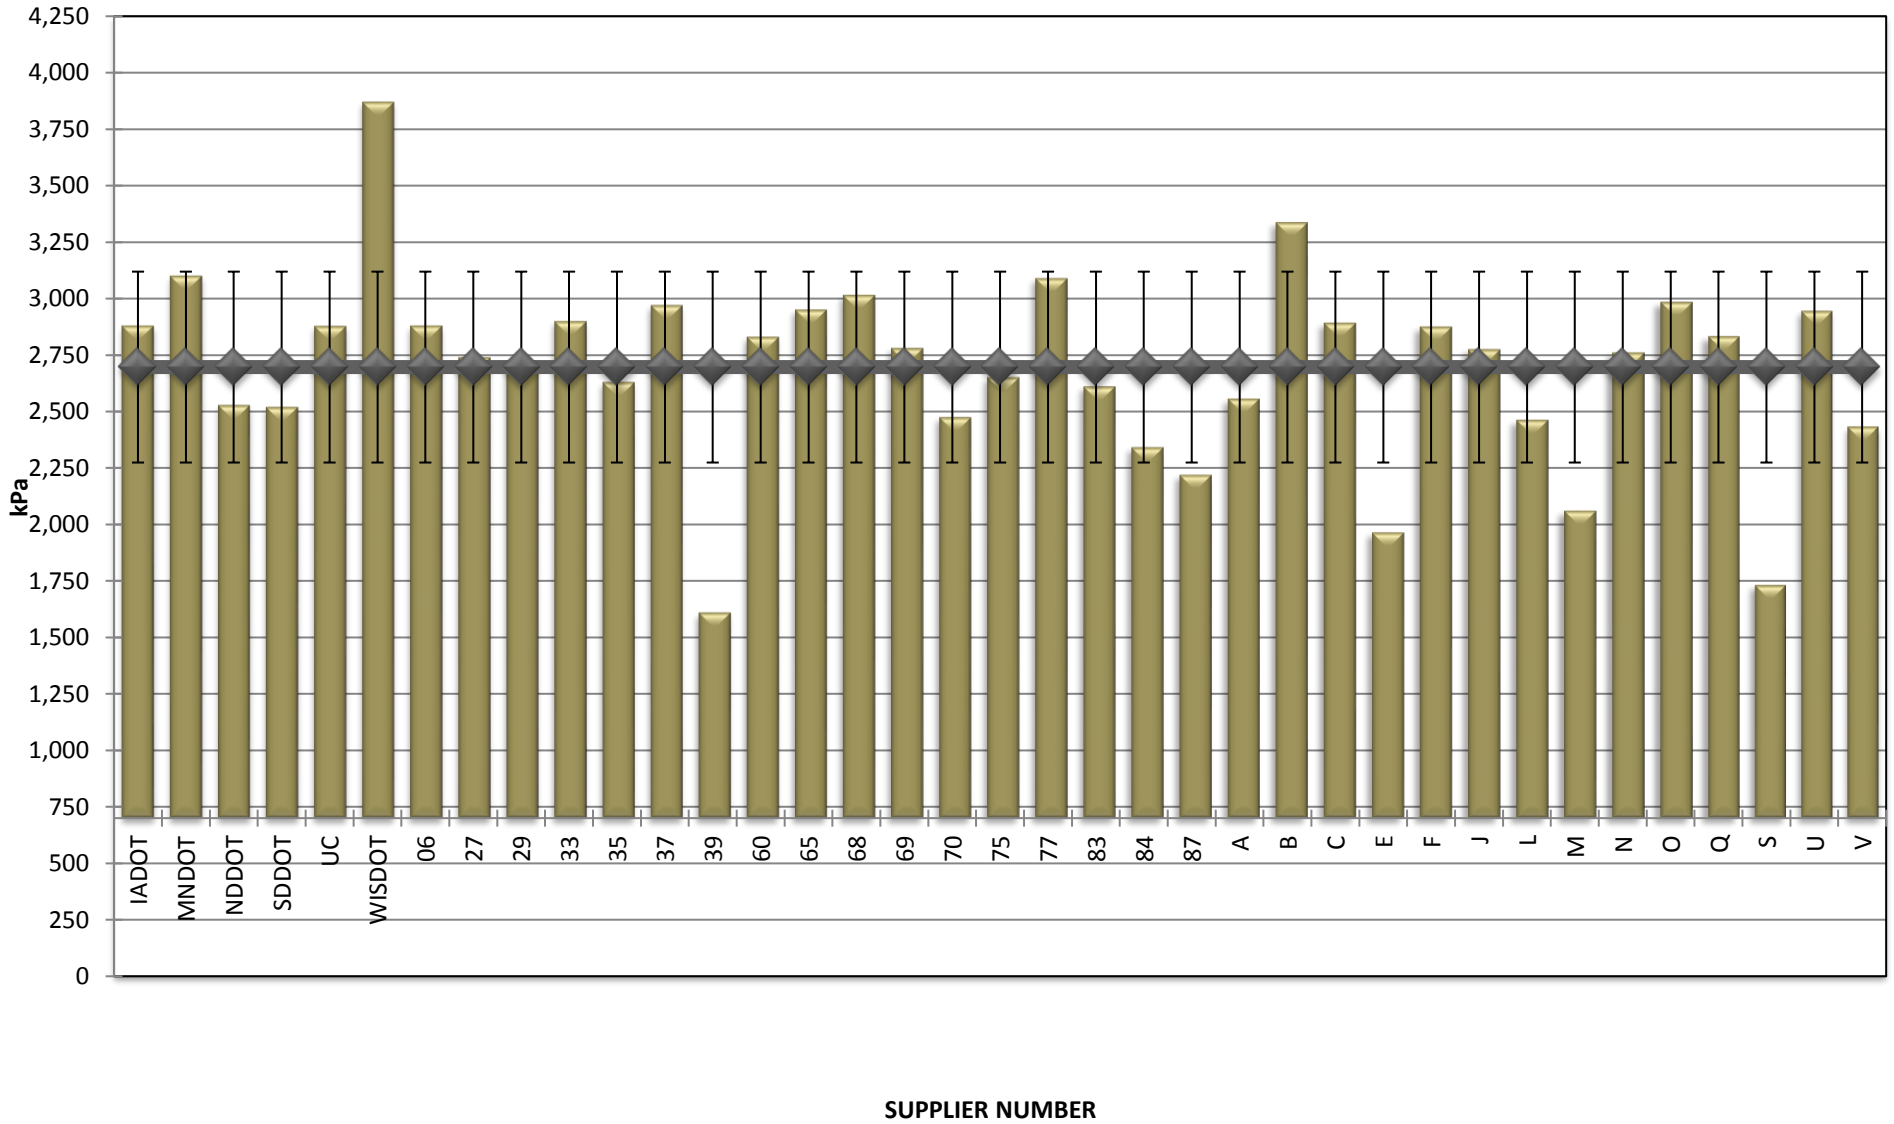


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2017-3**

RTFO MASS LOSS

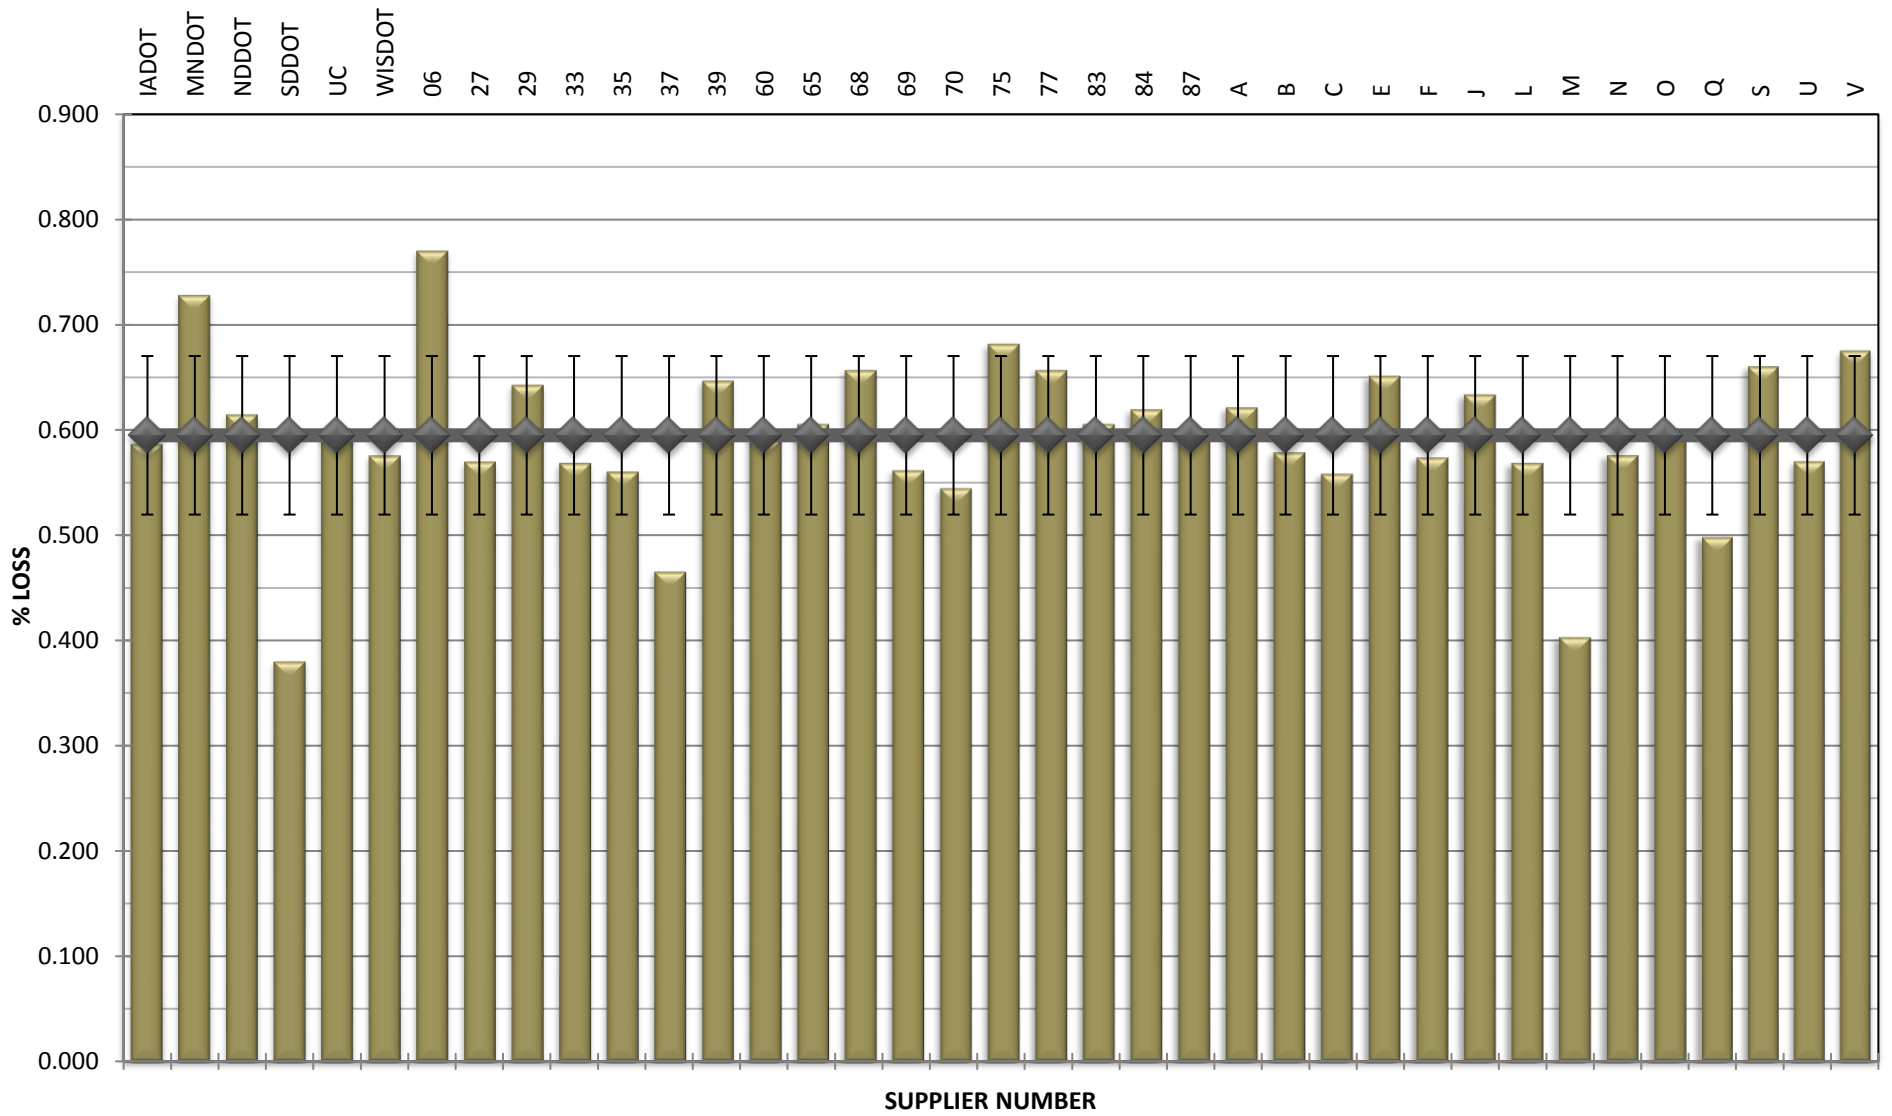


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2017-3**

BBR STIFFNESS

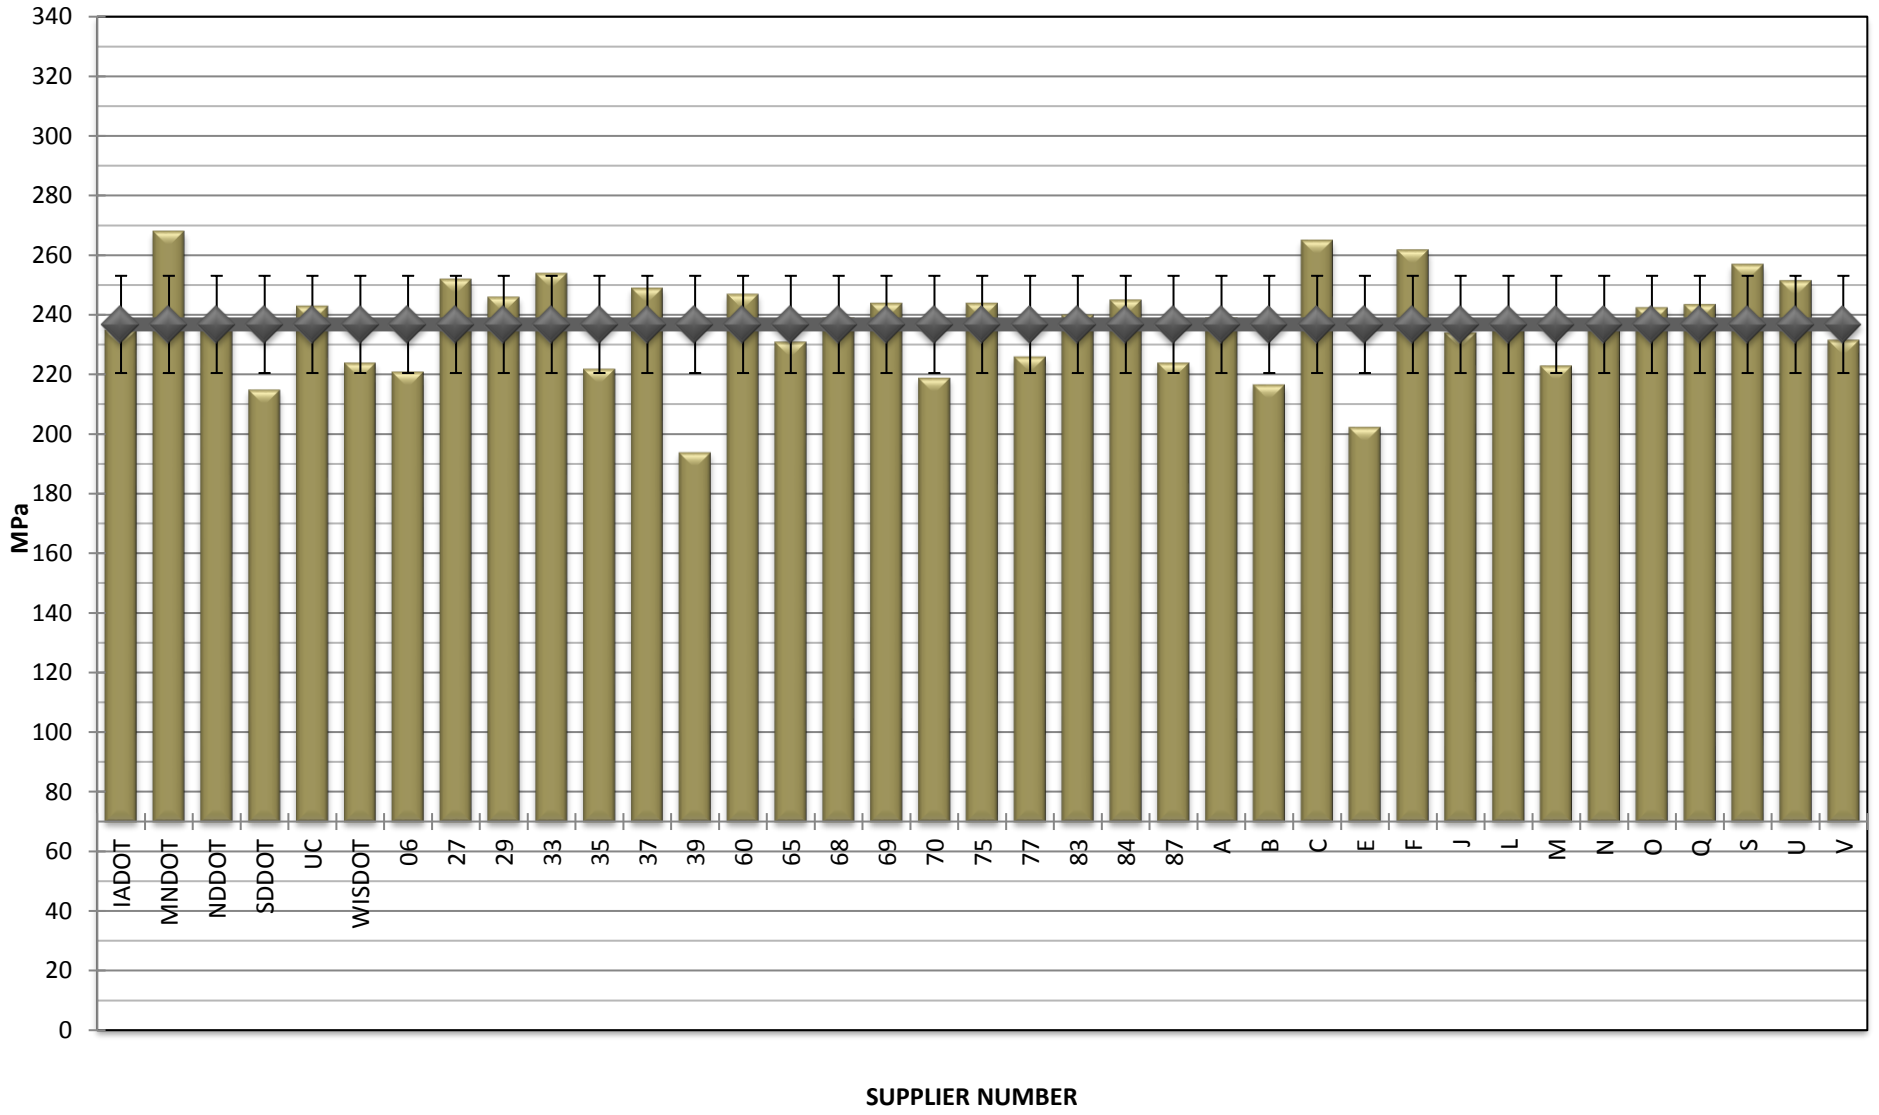


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2017-3**

BBR m-VALUE

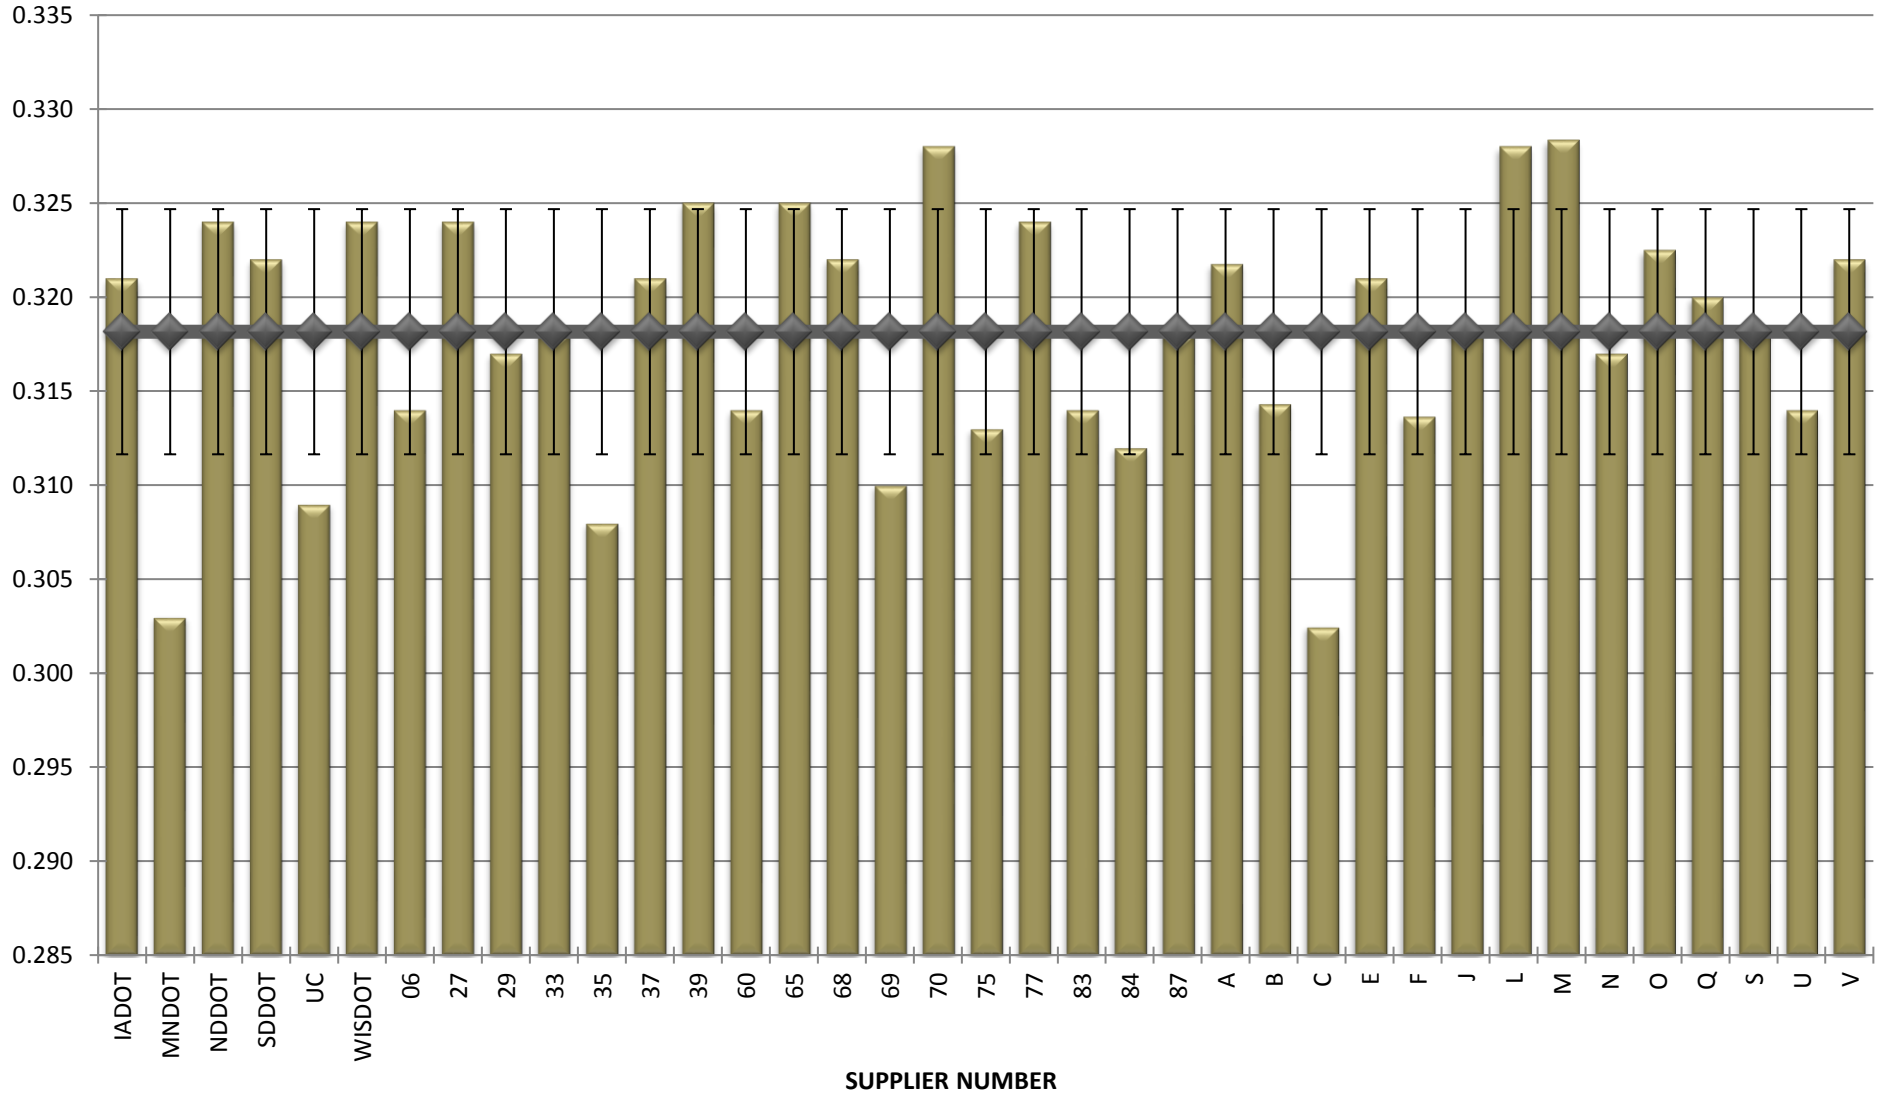


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2017-3**

Jnr @ 100 Pa

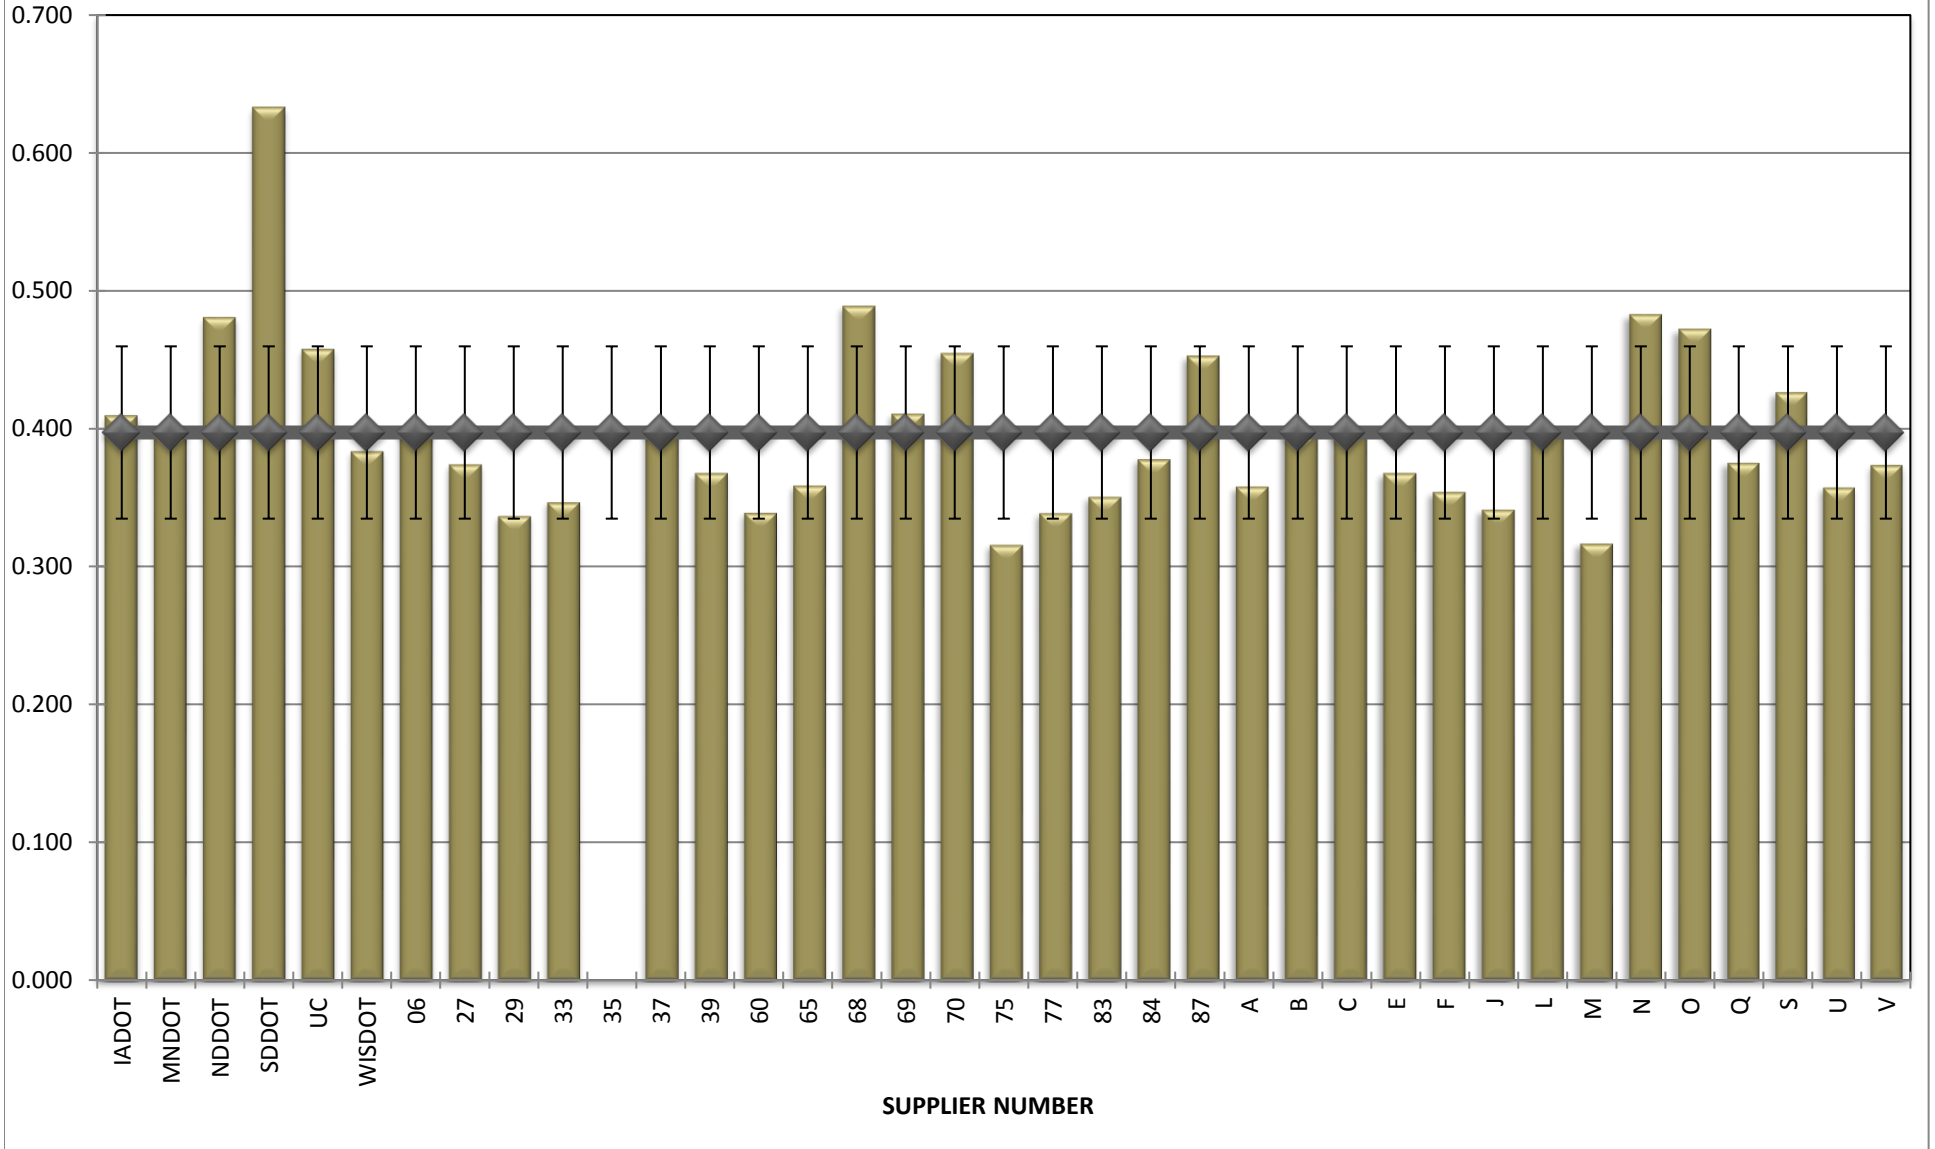


COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2017-3

% Recovery @ 100 Pa

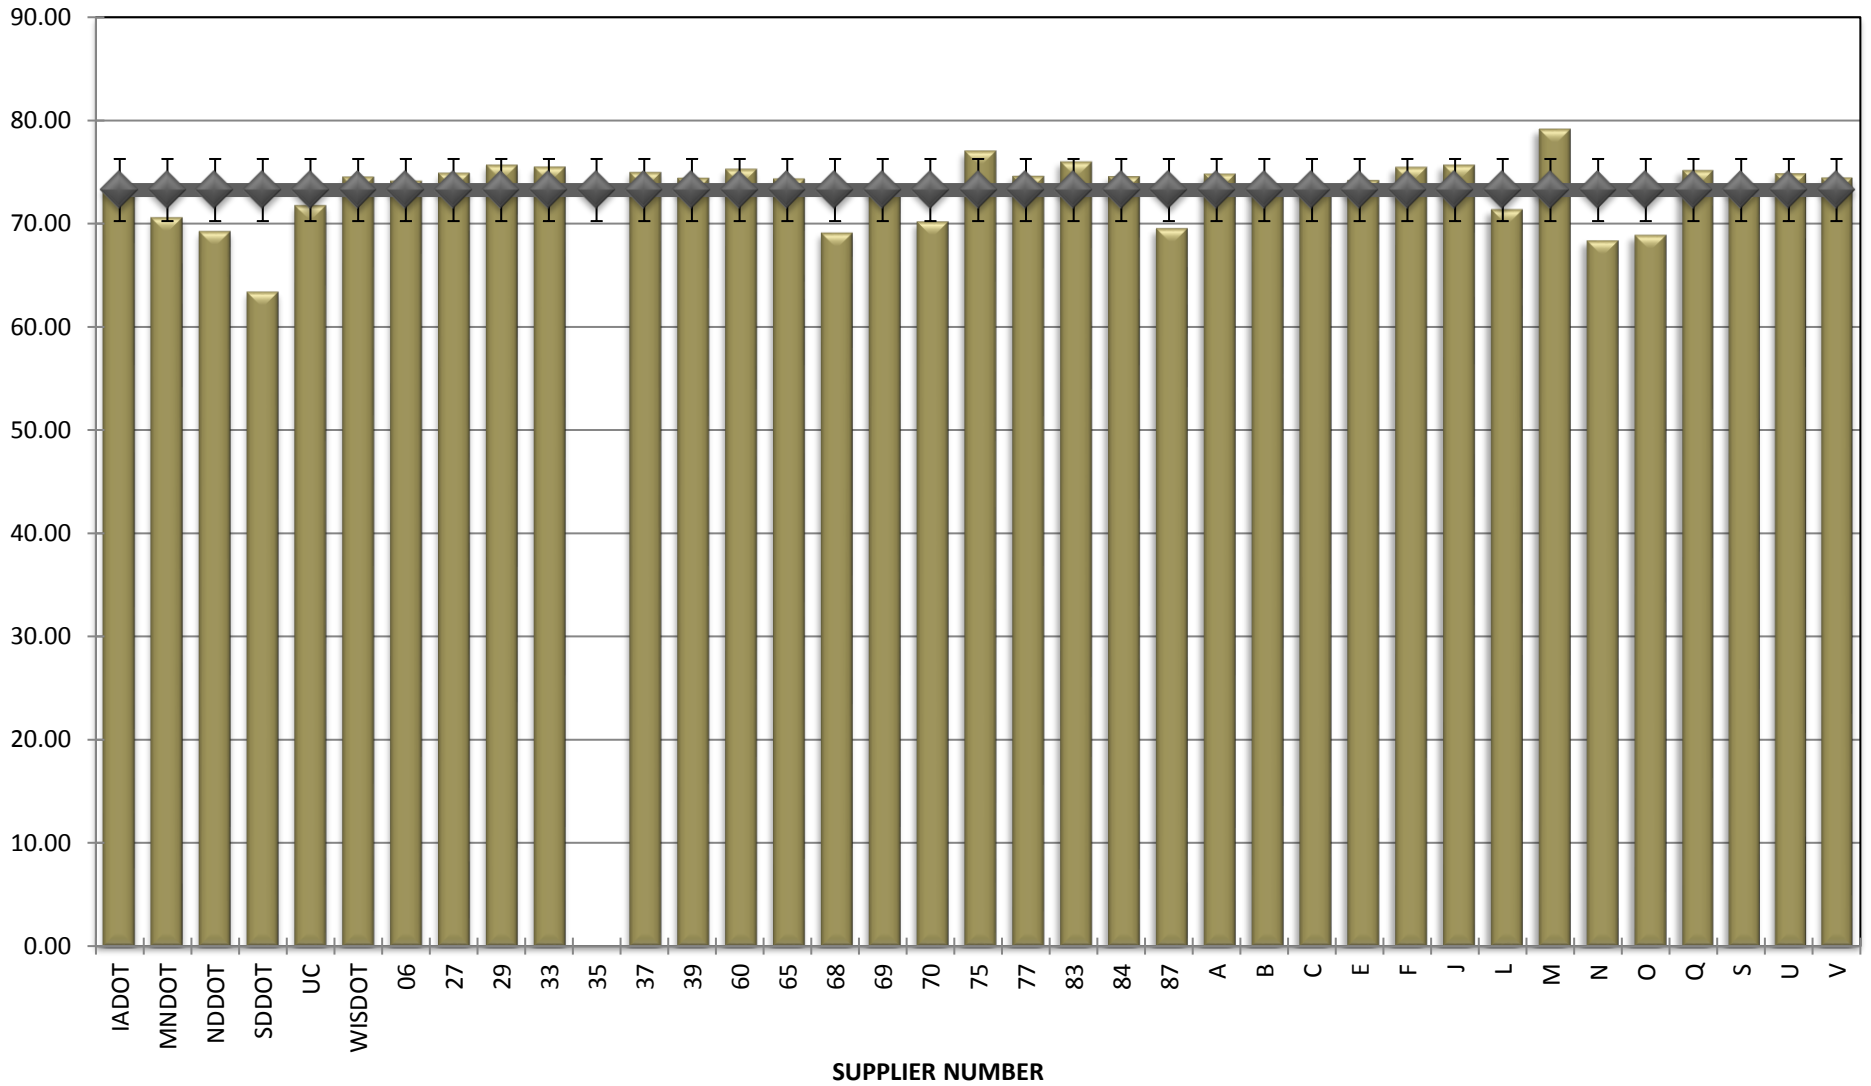

**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2017-3**

Jnr @ 3200 Pa

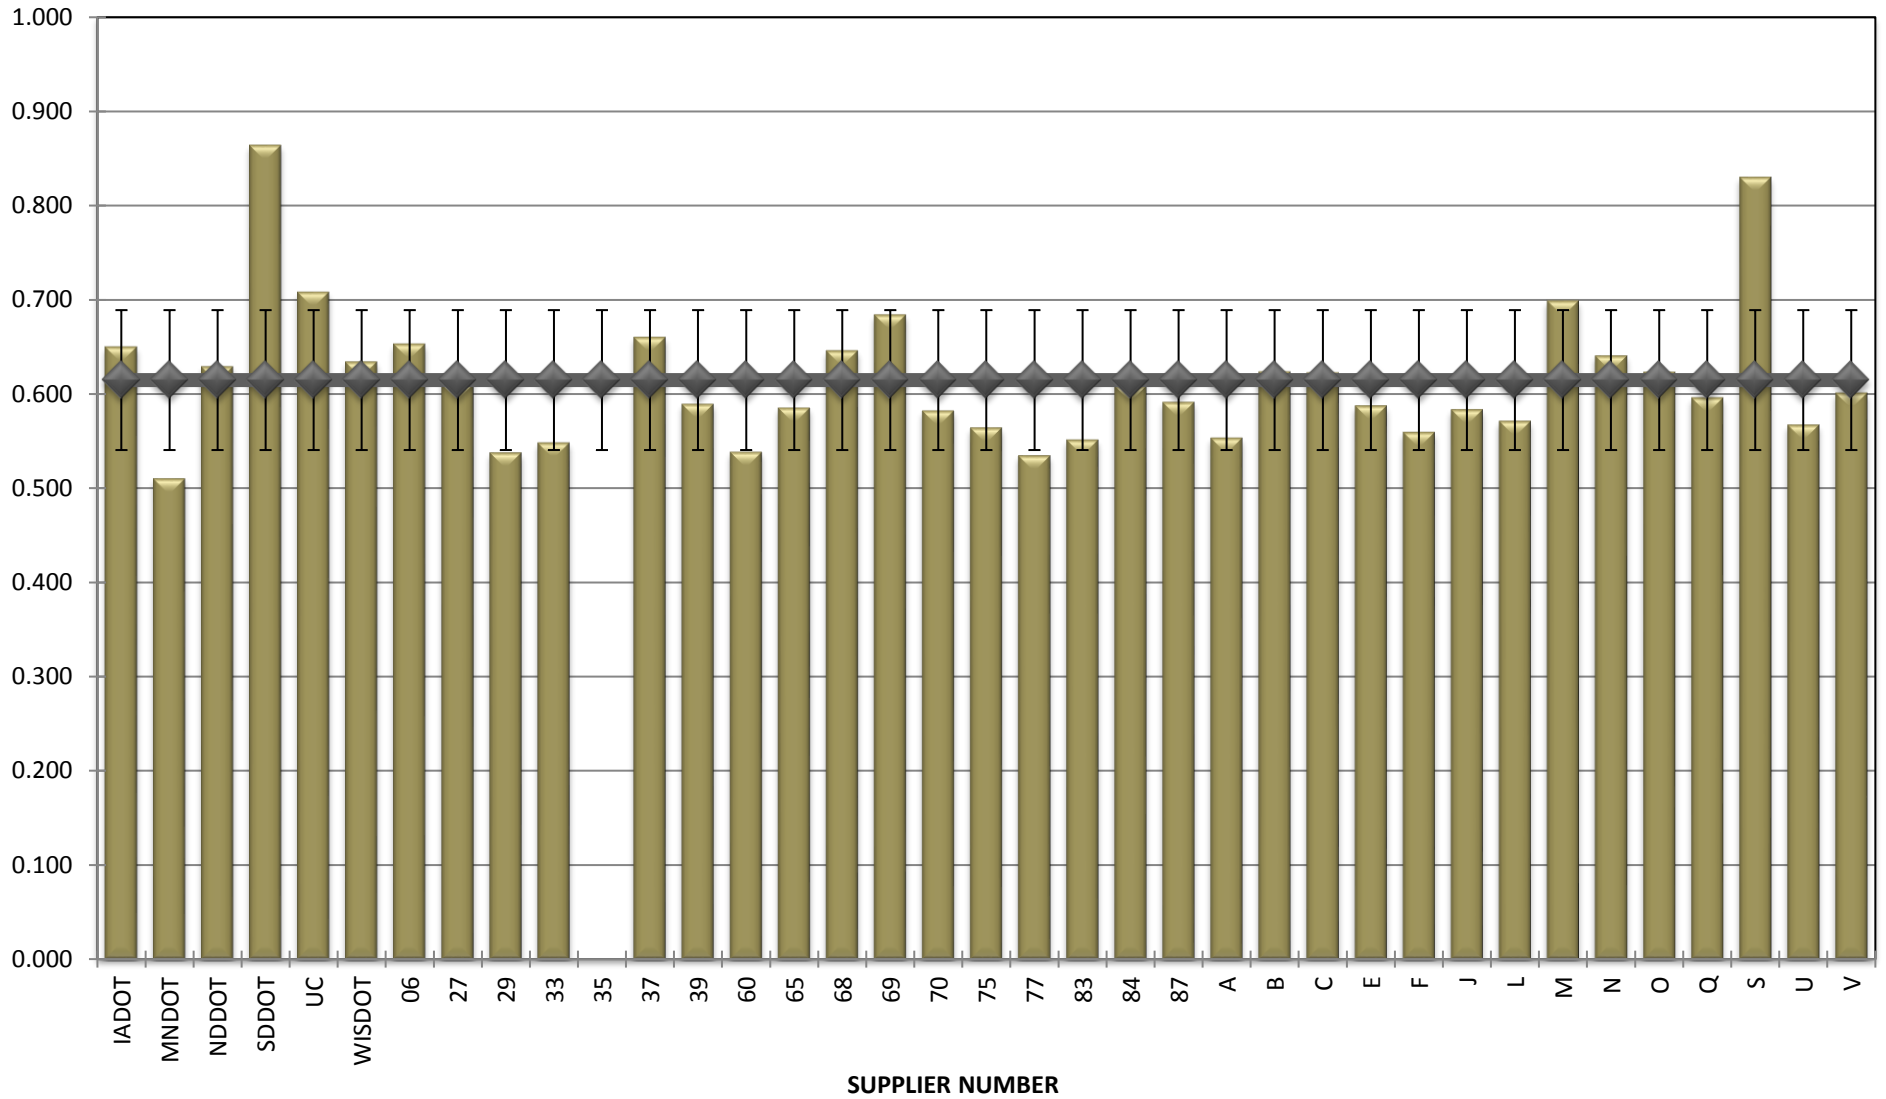

COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2017-3

% Recovery @ 3200 Pa

