


COMBINED STATE BINDER GROUP ROUND ROBIN SUMMARY B 2021-2
PG 58S-28

	Rot. Visc.	ODSR	RTFO DSR	PAVDSR	Mass Loss	S-value	m-value	Jnr @ 100 Pa	% Rec. 100 Pa	Jnr @ 3200 Pa	% Rec. @ 3200 Pa
A											
19	0.272	1.23		4,428	0.613	235	0.325	2,572	4.40	2,835	1.30
51	0.270	1.28		4,668	0.756	234	0.329	2,376	3.70	2,564	1.40
54	0.276	1.33		4,263	0.632	240	0.326	2,537	4.90	2,783	1.30
97	0.270	1.30		4,605	0.784	225	0.324	2,286	5.30	2,514	1.60
AVERAGE	0.272	1.28		4,491	0.696	234	0.326	2,443	4.58	2,674	1.40
B											
01	0.305	1.17		3,330	0.666	235	0.321	2,720	3.70	2,960	1.04
17	0.358	1.20		3,180	0.637	225	0.317	2,630	3.88	2,890	1.05
45	0.336	1.22		3,540	0.653	253	0.314	2,660	3.62	2,920	1.05
AVERAGE	0.333	1.20		3,350	0.652	237.6667	0.317	2,670	3.73	2,923	1.05
E											
15	0.270	1.22		3,889	0.659	245	0.330	2,720	3.98	2,990	0.00
39	0.260	1.17		3,545	0.635	246	0.329	2,800	2.60	3,050	0.00
89	0.260	1.17		3,505	0.648	234	0.330	2,810	3.73	3,090	0.00
AVERAGE	0.263	1.19		3,646	0.647	241.6667	0.330	2,777	3.44	3,043	
F											
02	0.253	1.19		4,583	0.640	240	0.321	2,380	3.30	2,610	0.40
11	0.248	1.21		4,611	0.635	250	0.326	2,680	3.03	2,940	0.10
34	0.249	1.26		4,552	0.635	256	0.317	2,400	4.96	2,640	1.32
48	0.250	1.25		4,753	0.638	243	0.314	2,610	3.87	2,840	1.17
56	0.253	1.24		4,660	0.728	255	0.312	2,440	4.05	2,680	1.25
62	0.245	1.23		4,880	0.649	252	0.316	2,330	3.09	2,520	1.30
66	0.245	1.22		4,650	0.636	253	0.320	2,690	3.48	2,920	1.07
75	0.253	1.23		4,649	0.679	248	0.314	2,220	3.56	2,430	0.55
90	0.250	1.23		4,014	0.656	246	0.319	2,270	5.54	2,520	1.46
99	0.250	1.22		4,557	0.647	247	0.317	2,580	3.41	2,860	0.17
AVERAGE	0.250	1.23		4,591	0.654	249	0.318	2,460	3.83	2,696	0.88
J											
05	0.278	1.27		4,190	0.753	220	0.324	2,356	3.05	2,621	0.58
08	0.285	1.26		4,185	0.719	218	0.328	2,364	3.22	2,647	0.40
10	0.270	1.25		4,125	0.733	225	0.324	2,343	3.30	2,631	0.38
14	0.288	1.27		4,240	0.737	227	0.326	2,396	3.43	2,684	0.43
22	0.272	1.28		4,444	0.740	229	0.323	2,397	3.42	2,677	0.44
31	0.278	1.25		3,930	0.745	218	0.329	2,384	3.30	2,659	0.40
36	0.282	1.24		4,297	0.742	212	0.323	2,466	2.95	2,733	0.41
41	0.272	1.28		4,213	0.737	218	0.328	2,339	3.76	2,636	0.47
44	0.273	1.24		3,767	0.729	226	0.324	2,403	3.43	2,689	0.52
52	0.273	1.22		4,030	0.736	220	0.325	2,455	3.50	2,765	0.33
61	0.281	1.23		4,312	0.744	221	0.329	2,391	3.50	2,691	0.48
AVERAGE	0.277	1.25		4,158	0.738	221.2727	0.326	2,390	3.35	2,676	0.44
Q											
21	0.270	1.23		4,601	0.686	226	0.333	2,631	3.91	2,880	0.81
23	0.272	1.20		4,511	0.678	236	0.332	2,650	3.77	3,140	1.08
73	0.269	1.20		4,326	0.732	238	0.328	2,640	3.51	2,860	1.13
93	0.271	1.22		4,173	0.748	227	0.330	2,770	3.14	3,000	1.05
AVERAGE	0.271	1.21		4,403	0.711	232	0.331	2,673	3.58	2,970	1.02
S											
53	0.269	1.22		3,956	0.728	231	0.329	2,790	2.68	3,055	9.53
64	0.269	1.23		3,933	0.700	228	0.328	2,735	3.05	3,015	-0.09
AVERAGE	0.269	1.23		3,945	0.714	229.5000	0.329	2,762	2.87	3,035	4.72
U											
13	0.273	1.18		4,170	0.688	236	0.332	2,456	3.73	2,689	0.66
24	0.273	1.19		4,180	0.737	220	0.330	2,392	3.79	2,617	0.75
AVERAGE	0.273	1.19		4,175	0.713	228	0.331	2,424	3.76	2,653	0.70
V											
58	0.271	1.18		4,973	0.801	236	0.328	2,590	3.24	2,850	0.30
78	0.269	1.17		4,870	0.815	241	0.323	2,490	3.28	2,730	0.51
81	0.269	1.21		4,760	0.817	242	0.322	2,506	3.35	2,740	0.47
AVERAGE	0.270	1.19		4,868	0.811	239.6667	0.324	2,529	3.29	2,773	0.43
W											
07	0.220	1.25		4,037	0.722	240	0.331	2,595	3.50	2,768	0.10
95	0.240	1.23		4,085	0.726	232	0.330	2,616	3.00	2,804	-0.10
AVERAGE	0.230	1.24		4,061	0.724	236	0.331	2,606	3.25	2,786	
Y											
04	0.272	1.18		3,490	0.665	236	0.332	3,060	2.35	3,330	0.07
47	0.275	1.14		3,730	0.661	236	0.329	2,990	2.41	3,250	0.11
AVERAGE	0.274	1.16		3,610	0.663	236	0.331	3,025	2.38	3,290	0.09


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2021-2
PG 58S-28**

ROTATIONAL VISCOSITY

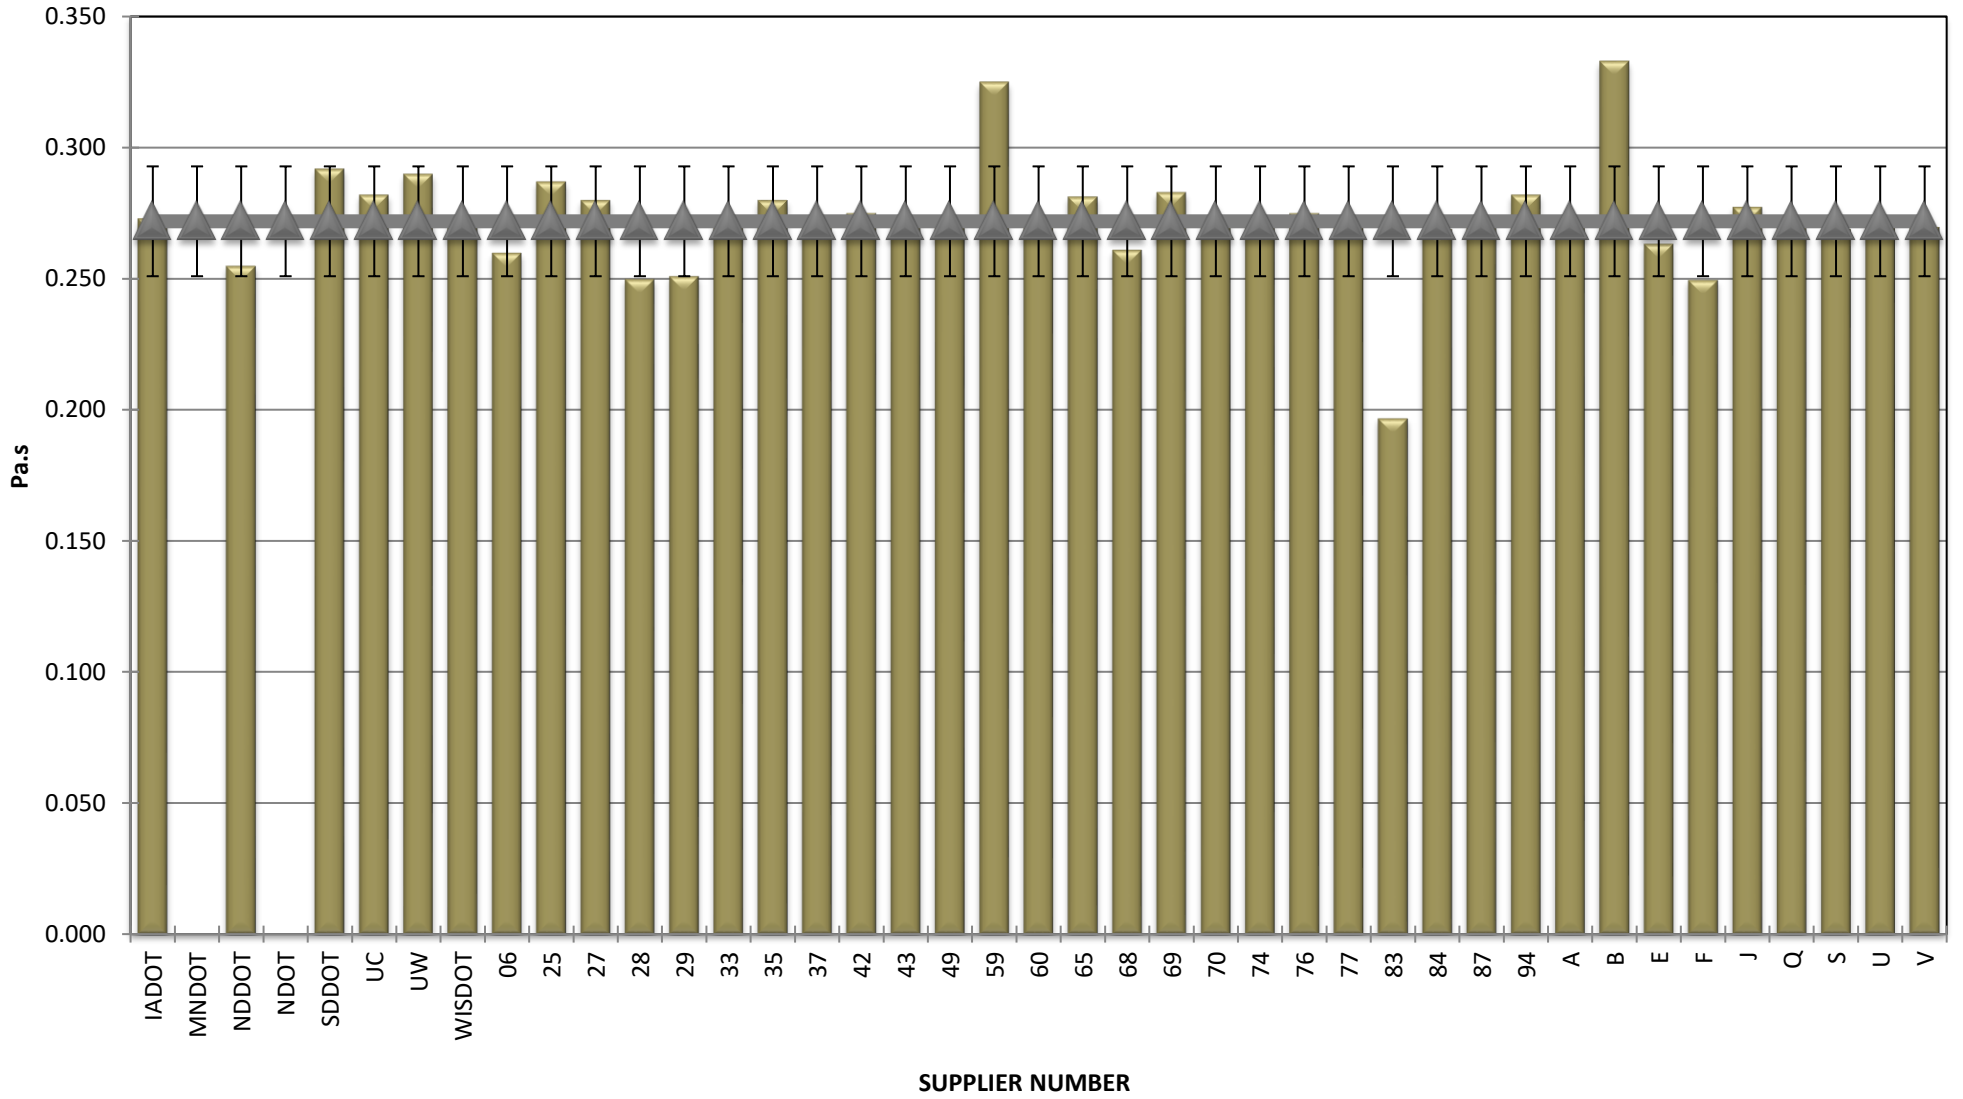


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2021-2
PG 58S-28**

DSR - ORIGINAL

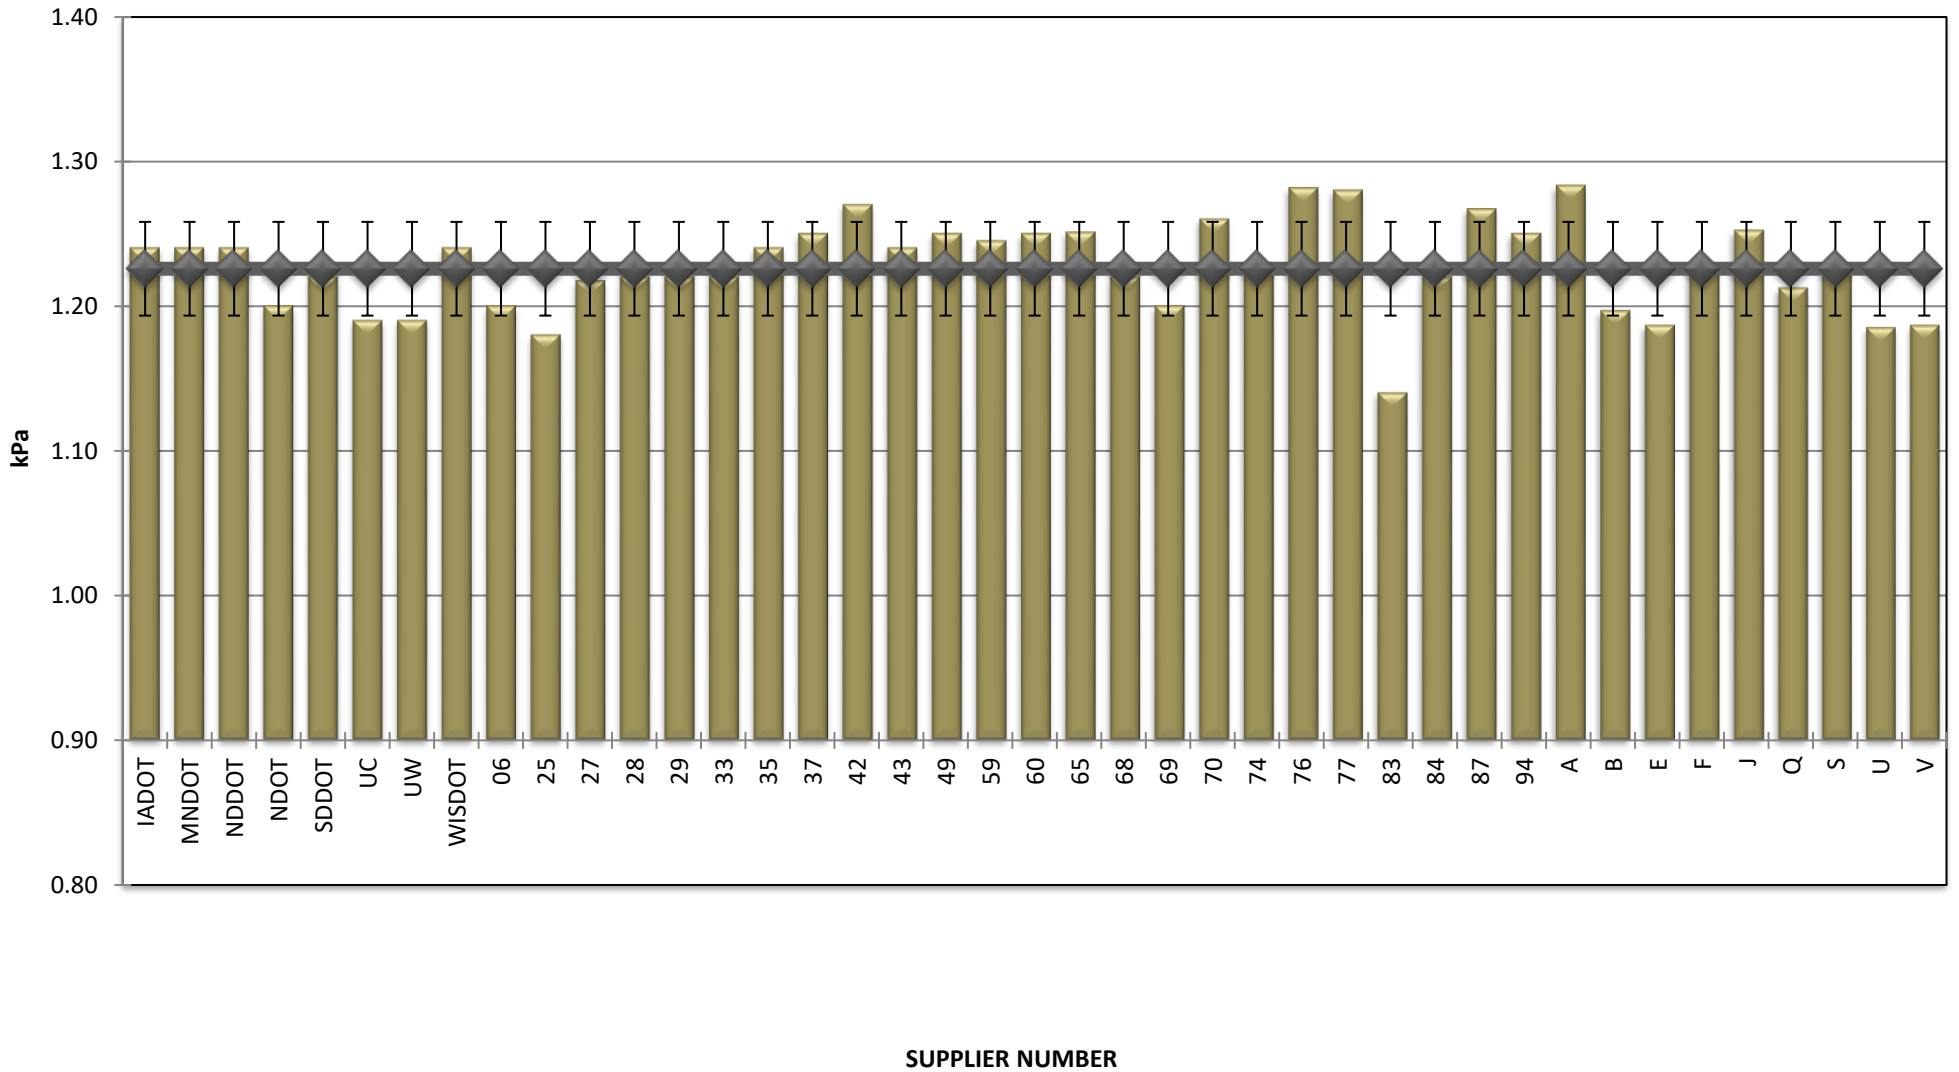


COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2021-2
PG 58S-28

DSR - RTFO

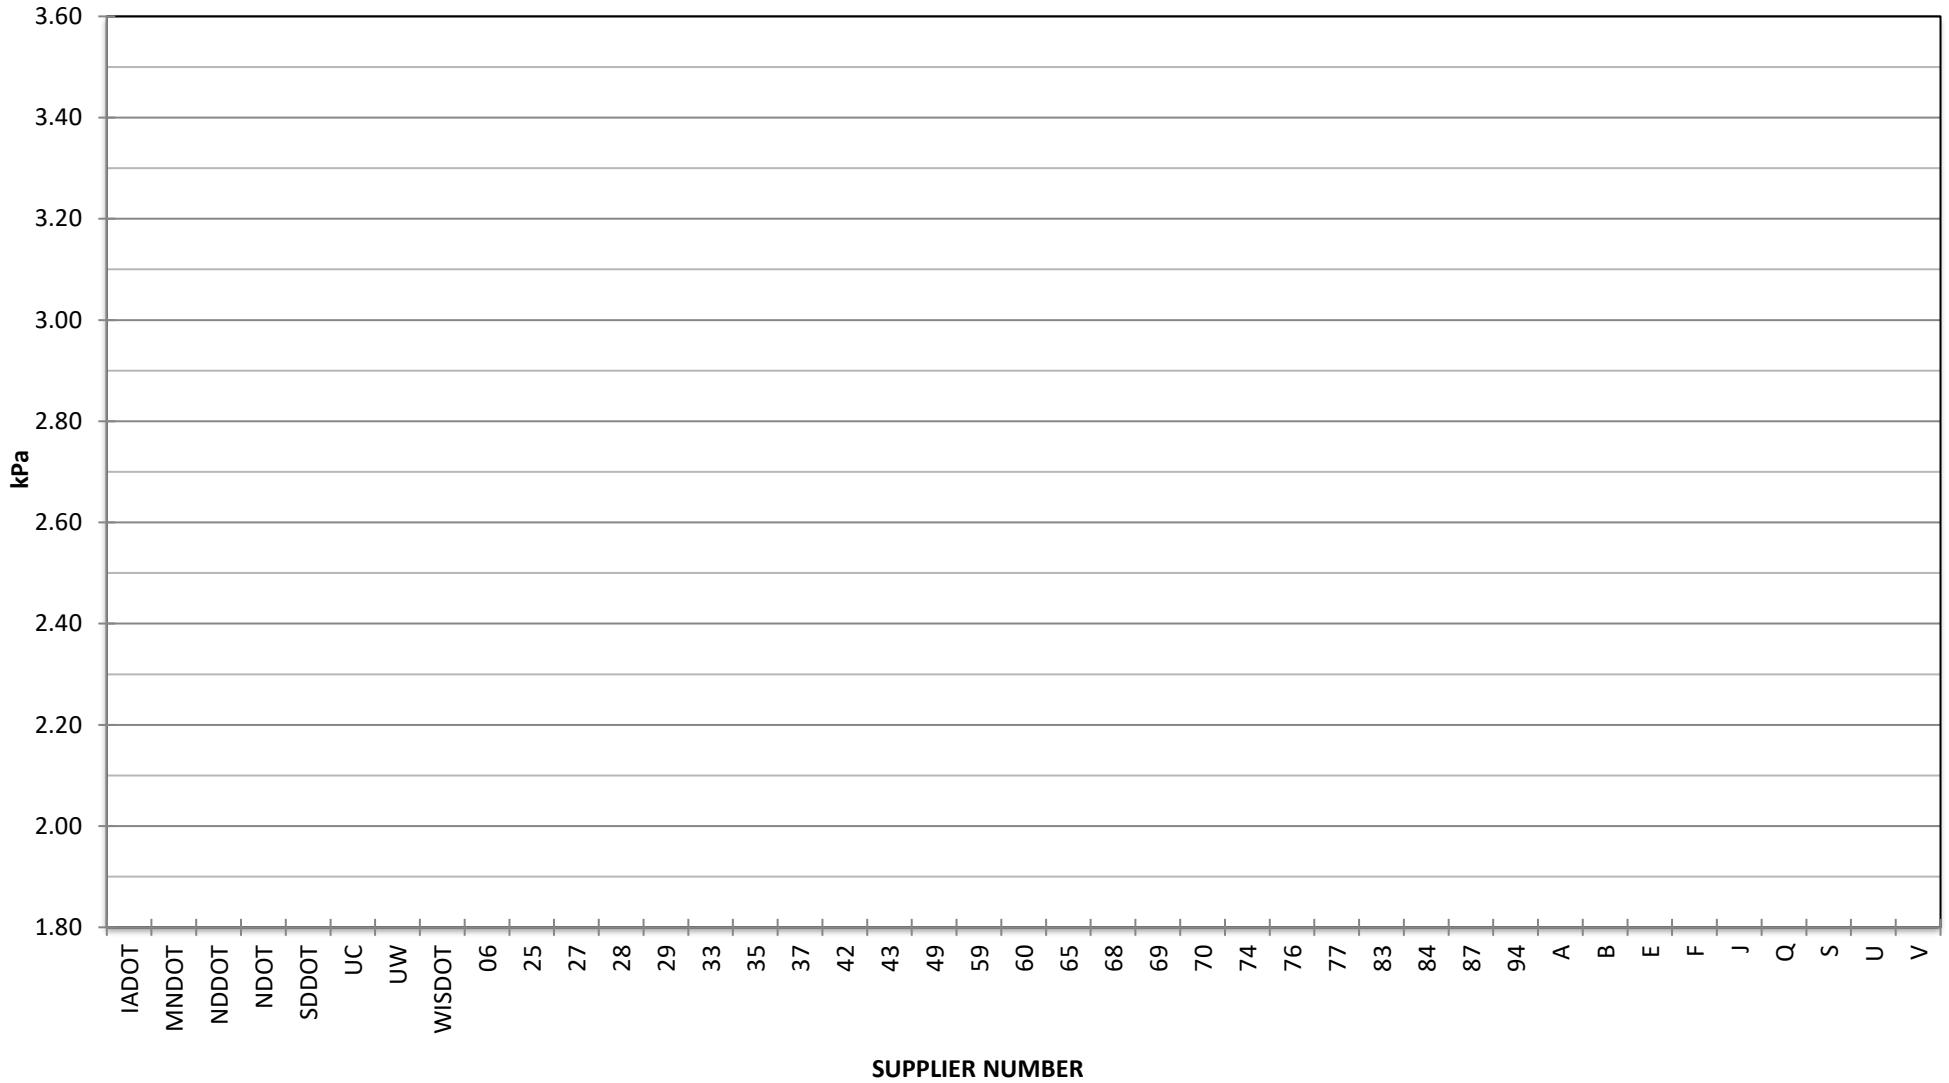


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2021-2
PG 58S-28**

DSR - PAV

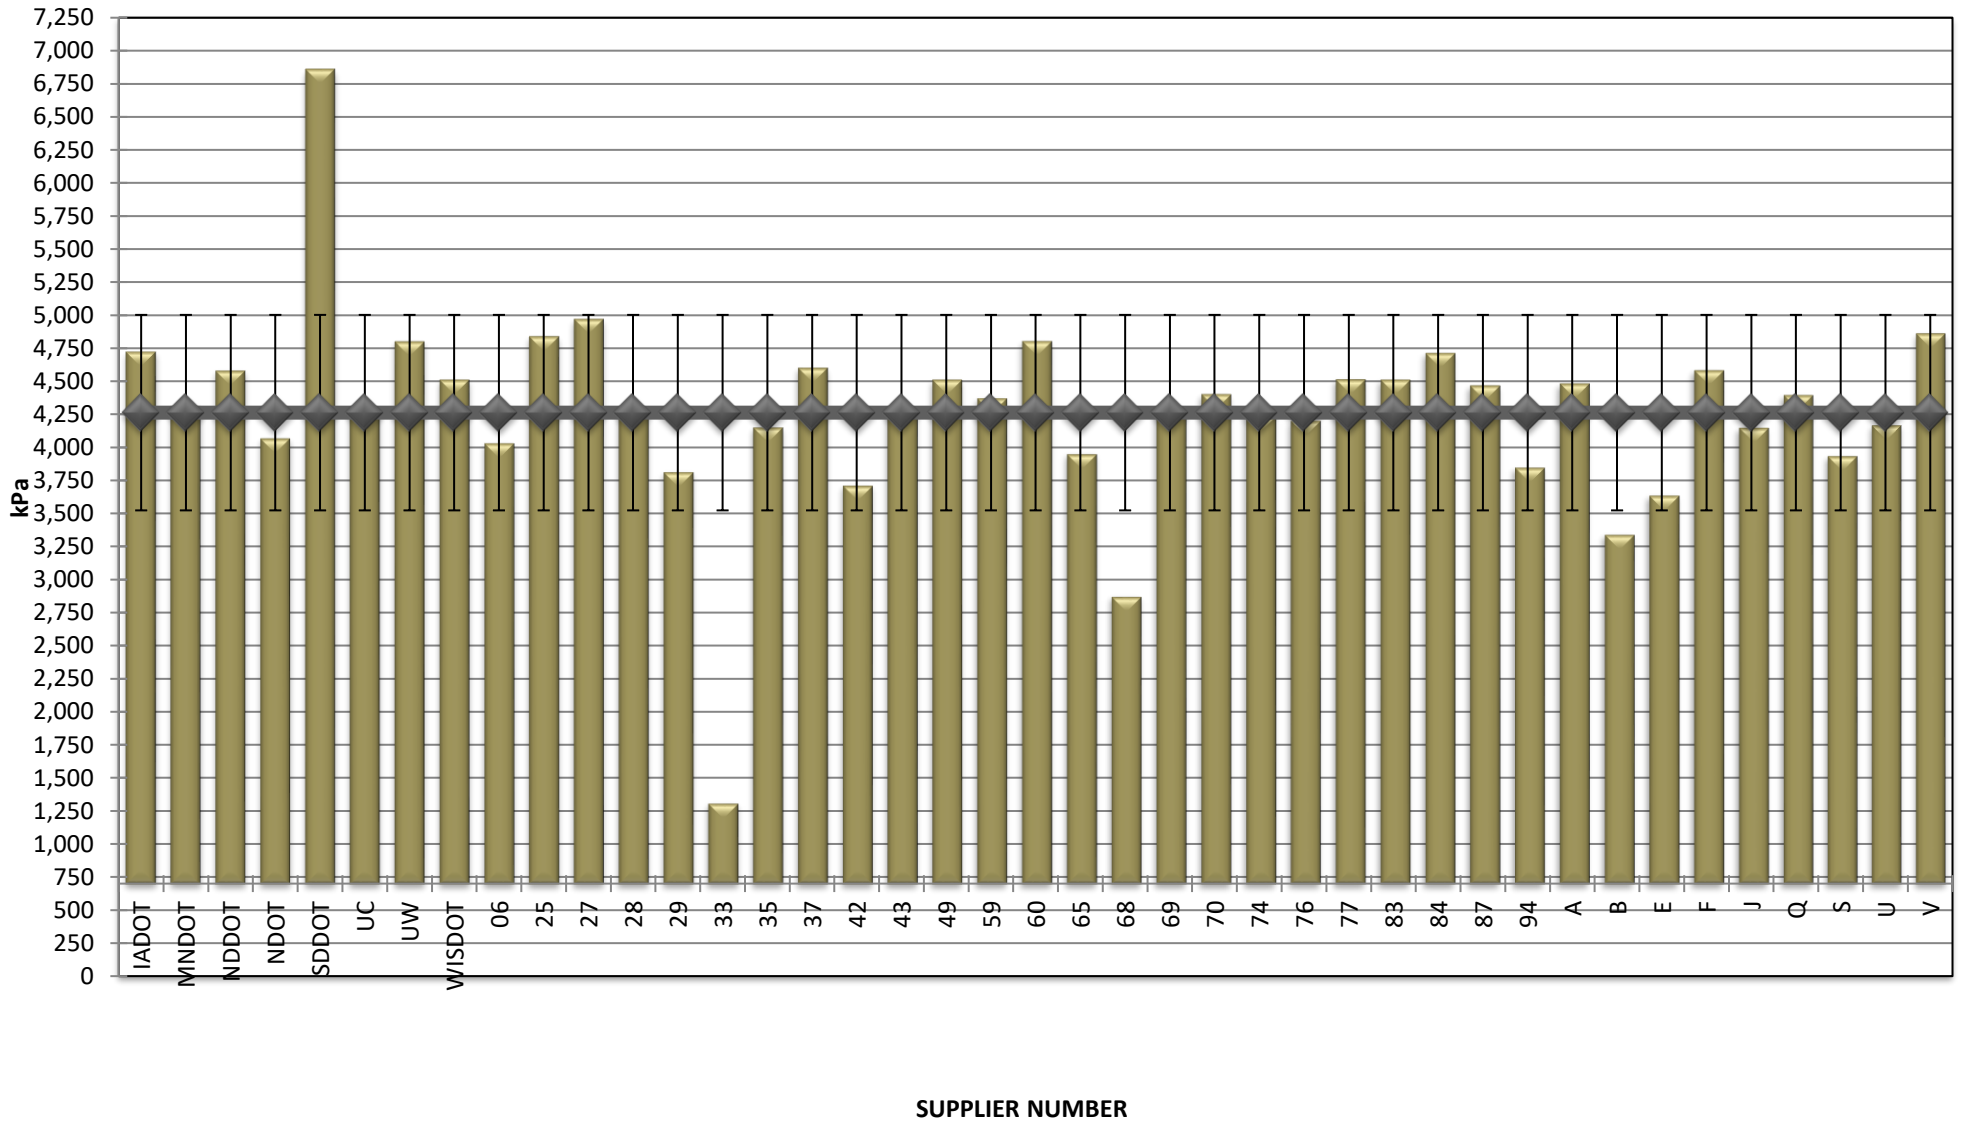


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2021-2
PG 58S-28**

RTFO MASS LOSS

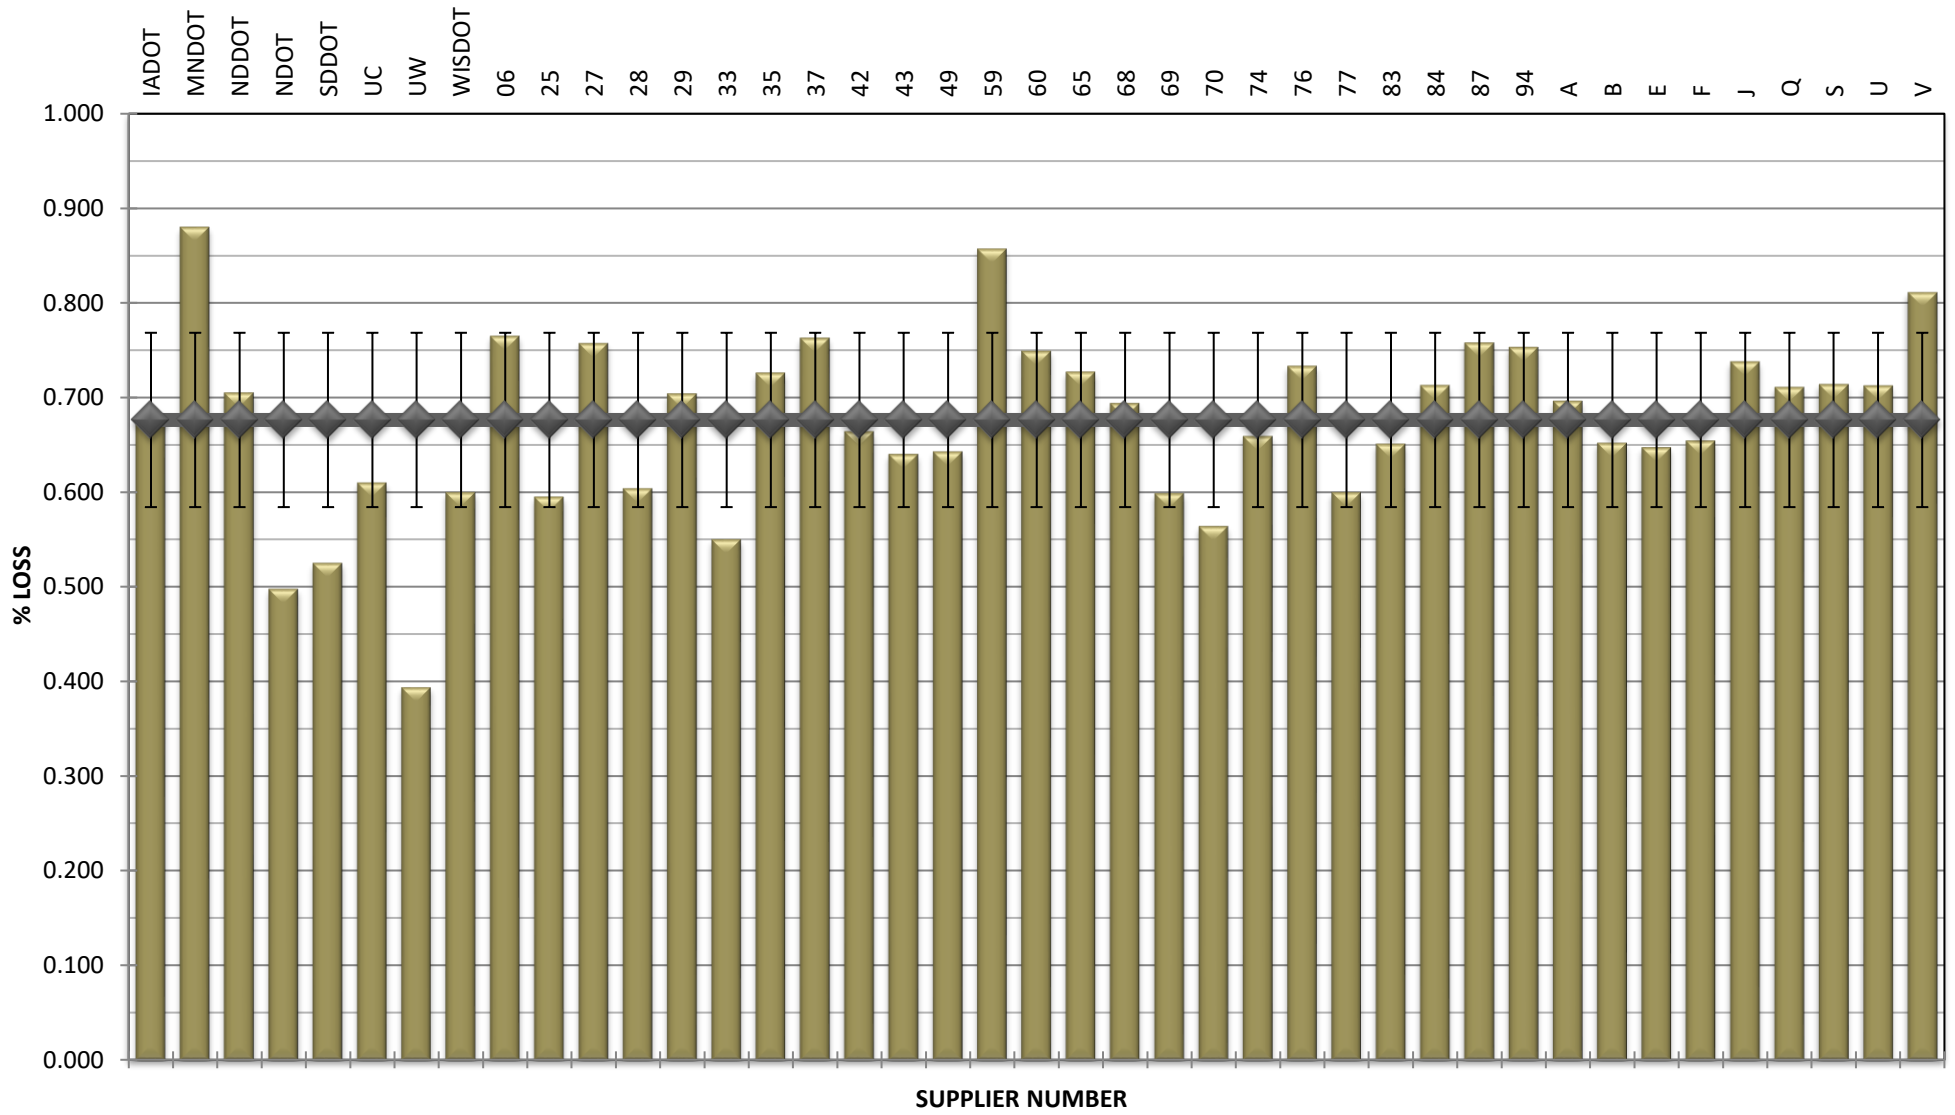


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2021-2
PG 58S-28**

BBR STIFFNESS

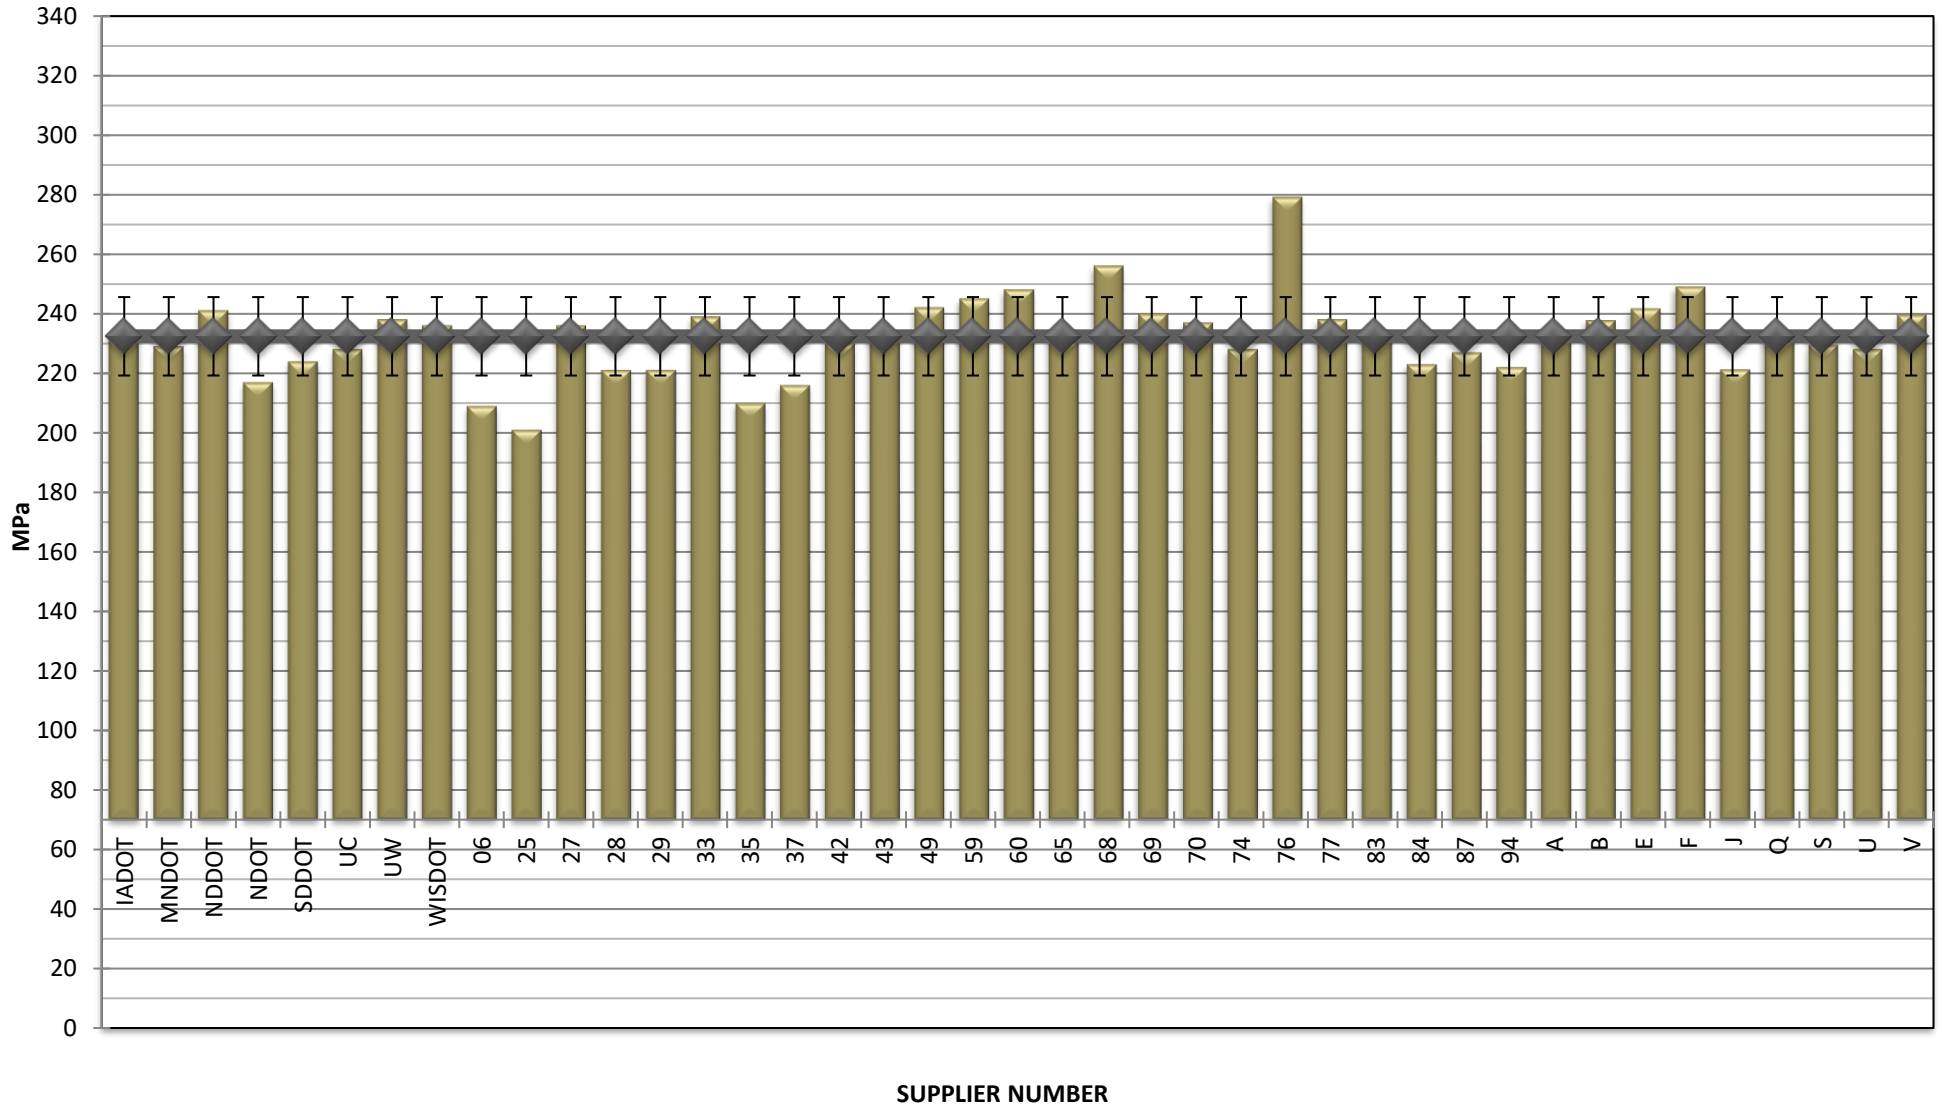


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2021-2
PG 58S-28**

BBR m-VALUE

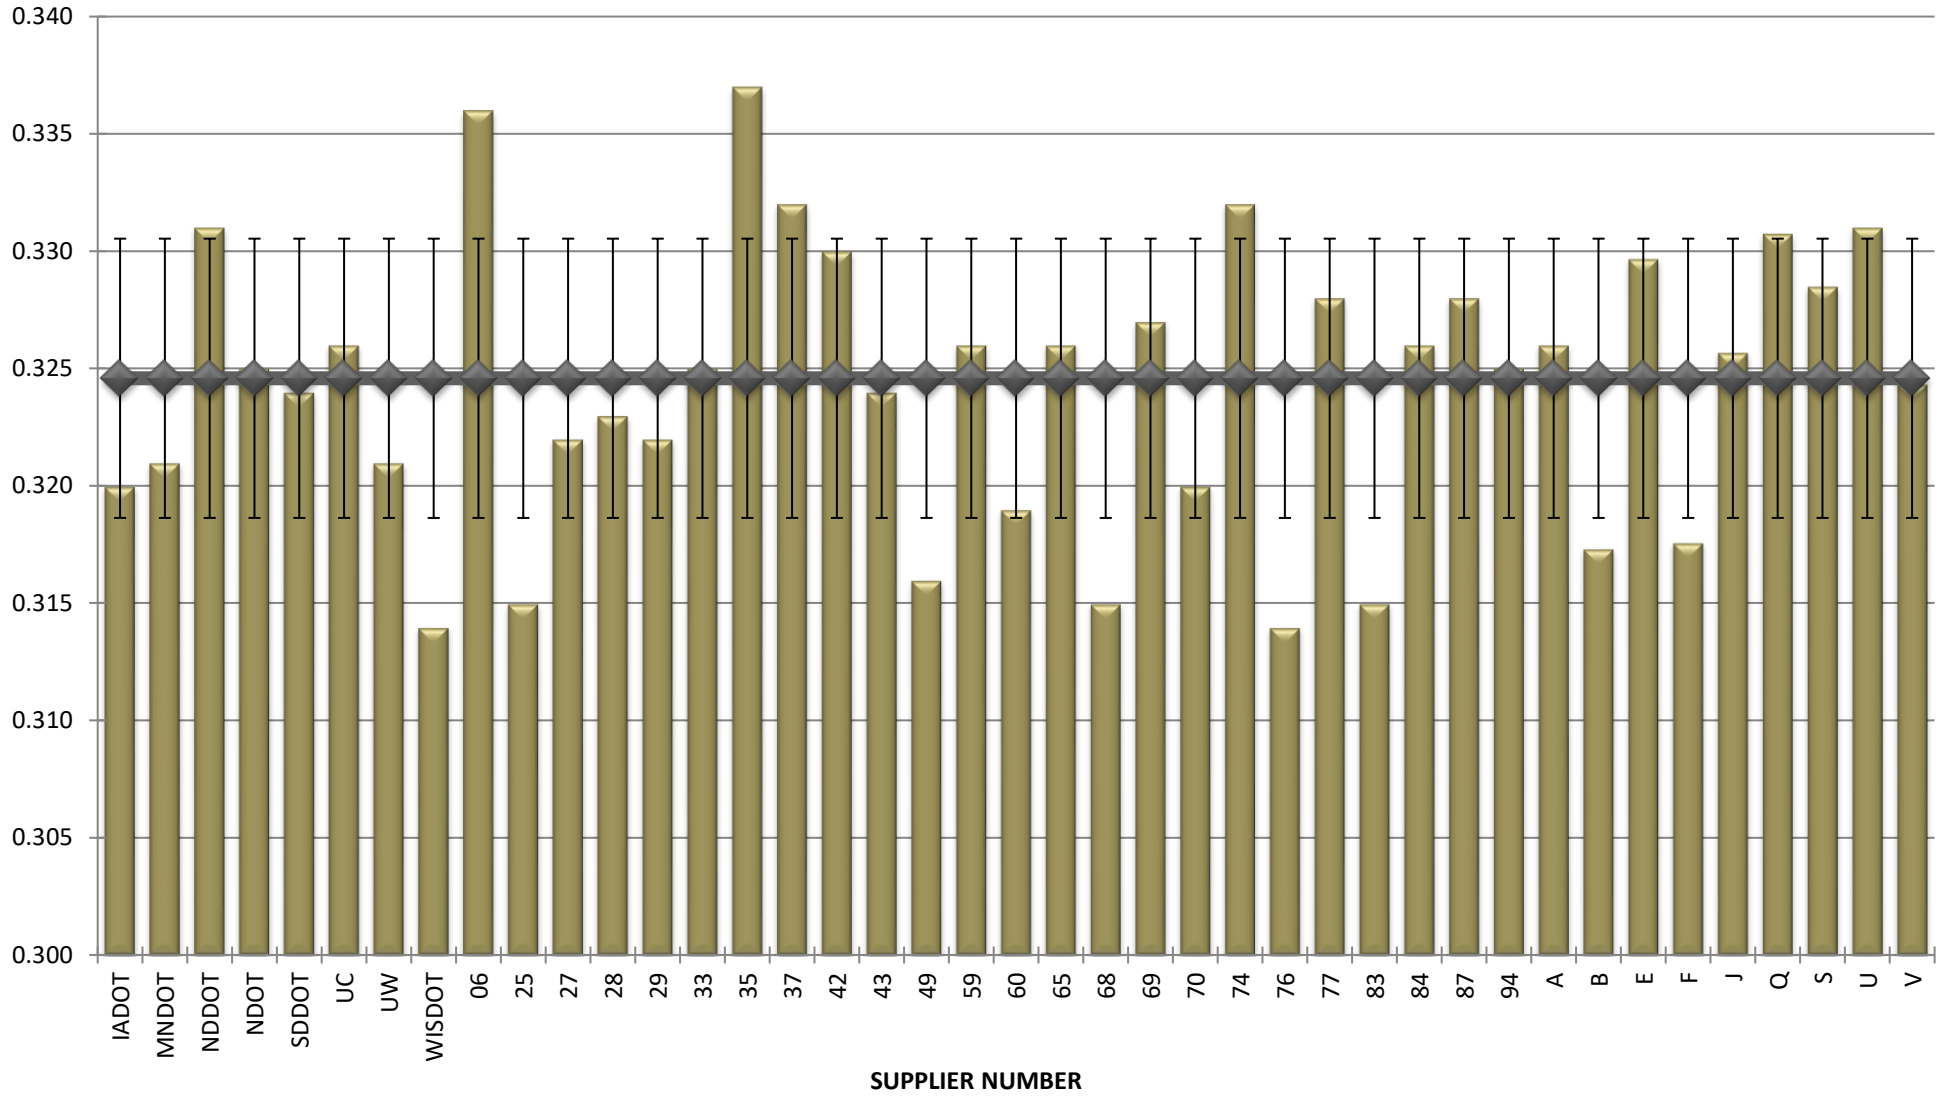


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2021-2
PG 58S-28**

Jnr @ 100 Pa

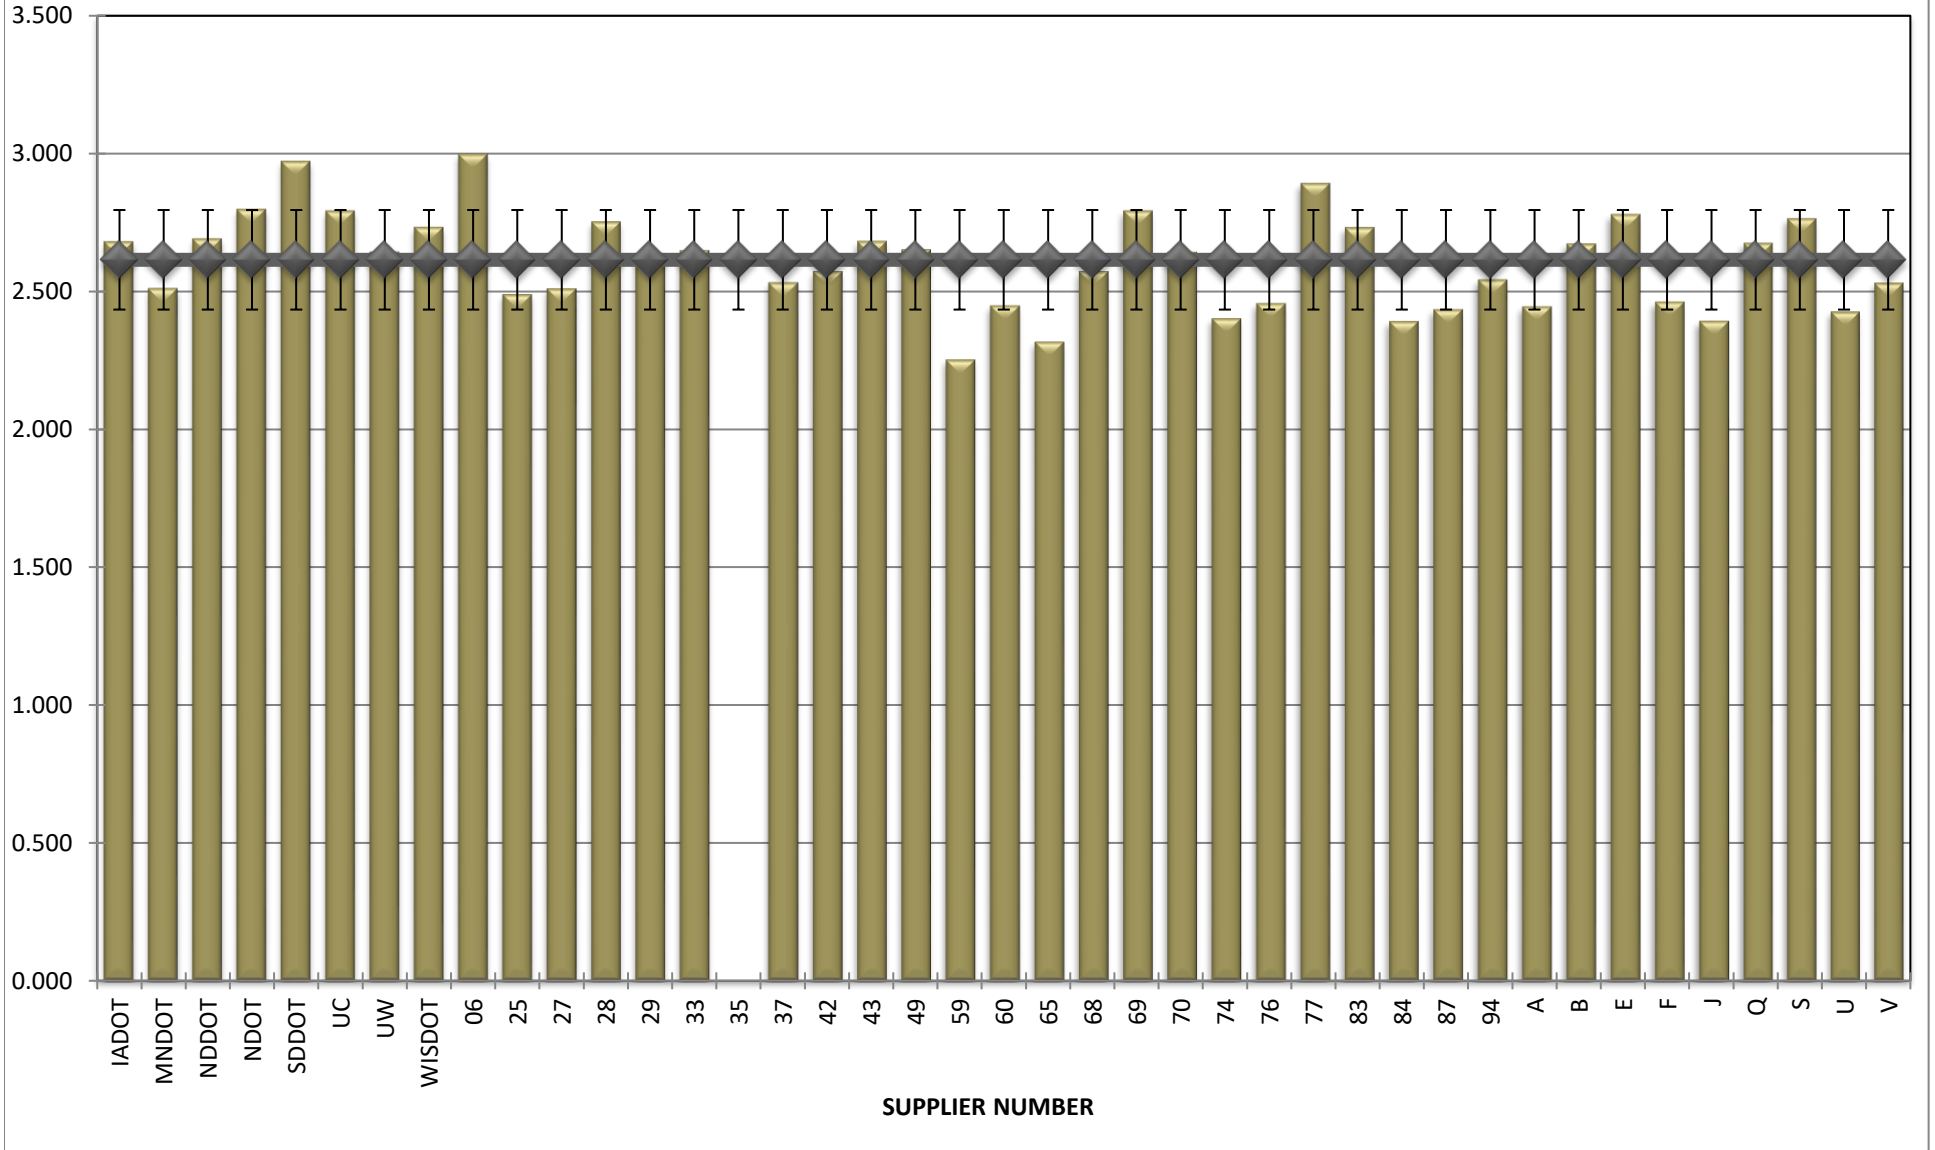


**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2021-2
PG 58S-28**

% Recovery @ 100 Pa

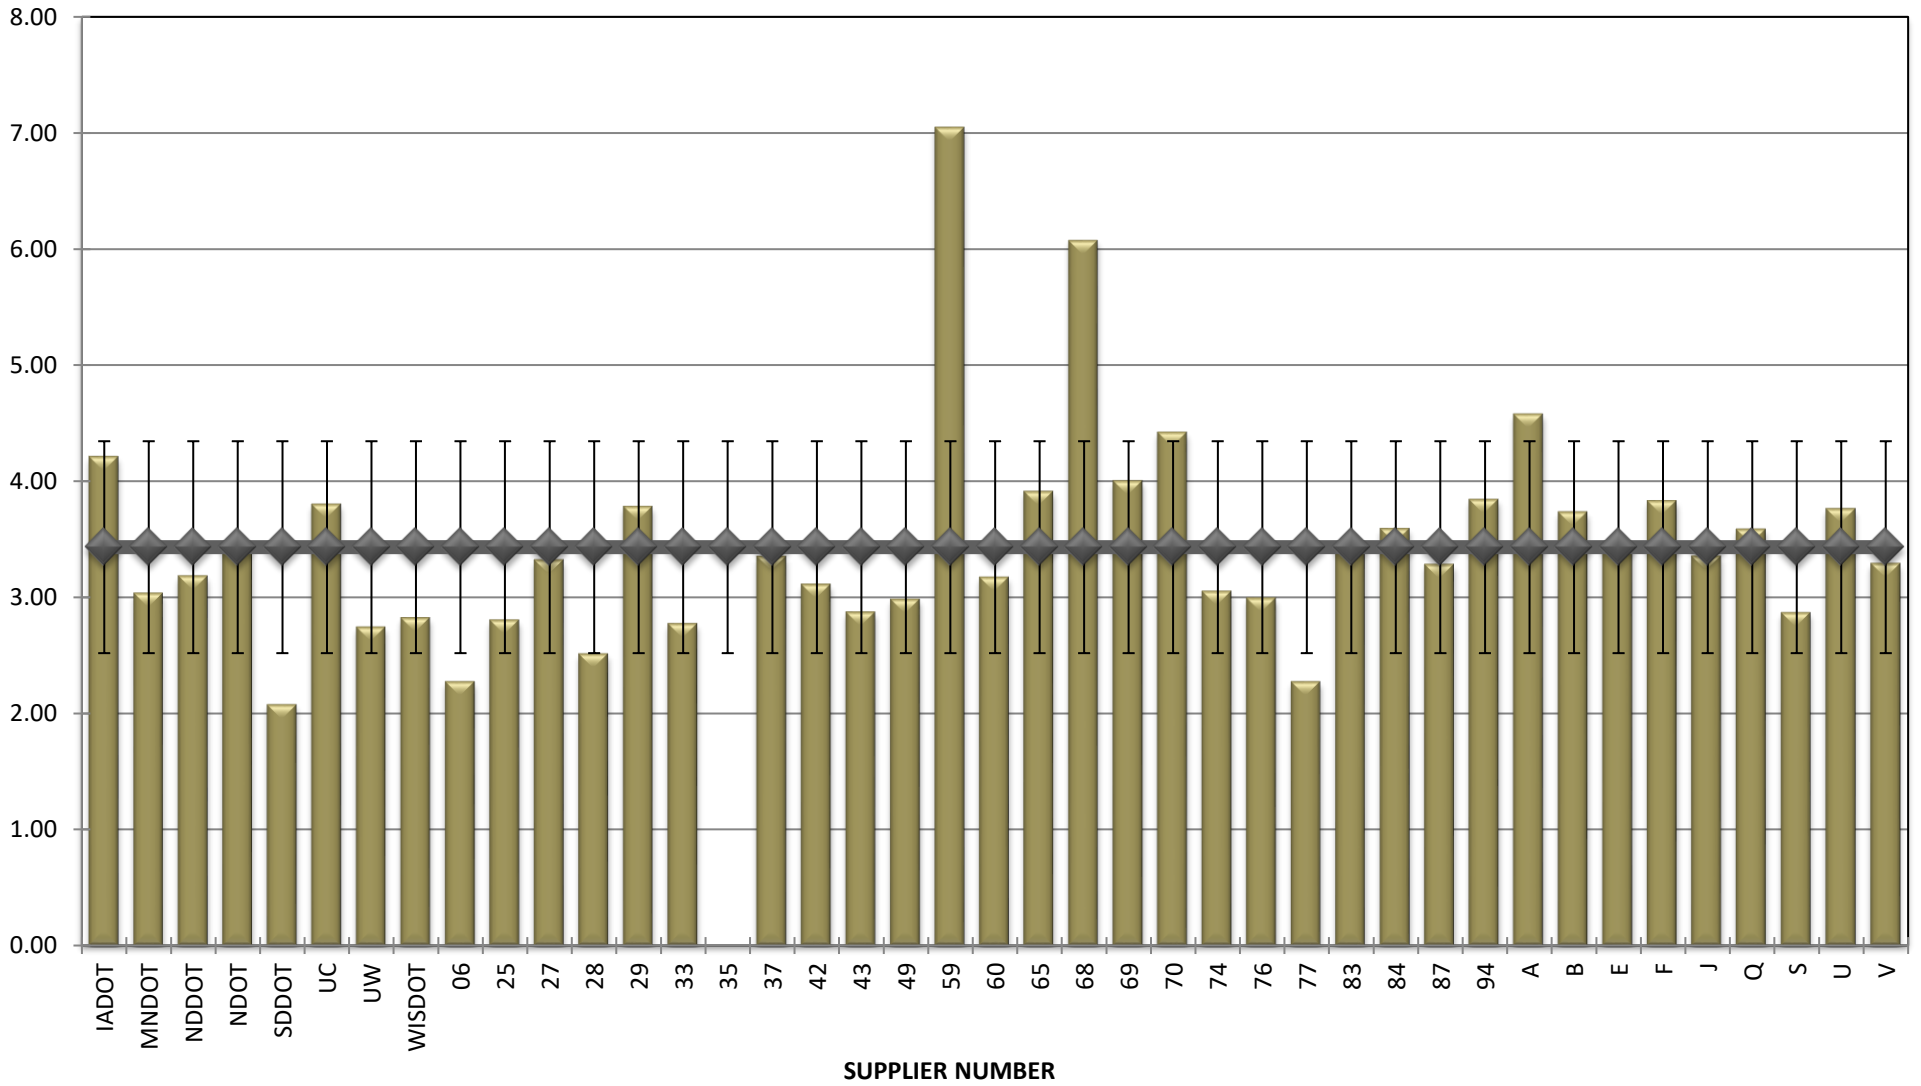

**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2021-2
PG 58S-28**

Jnr @ 3200 Pa

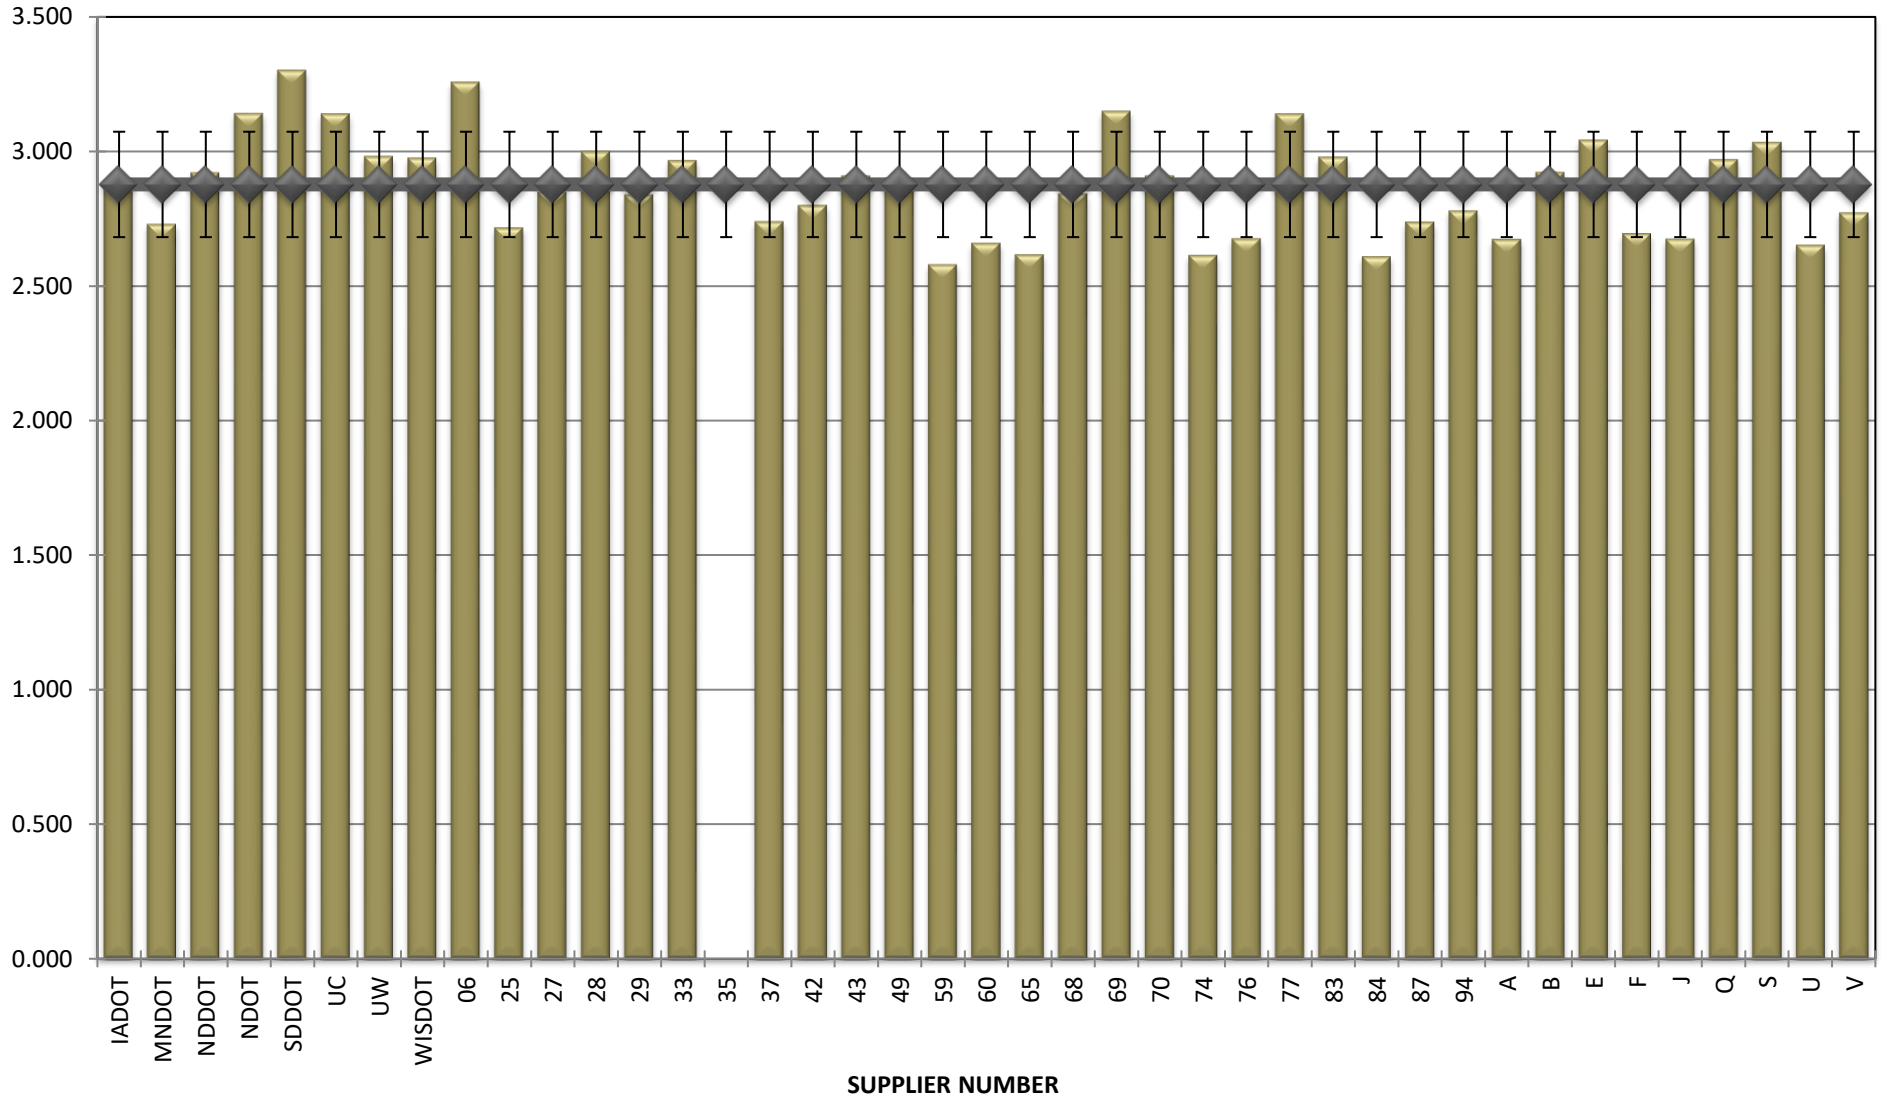

**COMBINED STATE BINDER GROUP ROUND ROBIN
SUMMARY B 2021-2
PG 58S-28**

% Recovery @ 3200 Pa

