

Analysis Software to Verify Mix Designs

Iowa DOT Asphalt Team

Brian Coree

Mike Heitzman

John Hinrichsen

Dan Redmond

Dan Seward


Todd Siefken

Mix Design Information

- Is the design information reasonable?

Gyratory Data					
% Asphalt Binder	3.85	4.35	4.85	4.87	5.35
Corrected Gmb @ N-Des.	2.347	2.370	2.389	2.390	2.415
Max. Sp.Gr. (Gmm)	2.532	2.509	2.490	2.490	2.476
% Gmm @ N- Initial	84.8	86.3	87.4	87.5	88.5
%Gmm @ N-Max	93.7	95.5	97.1	97.2	98.8
% Air Voids	7.3	5.5	4.1	4.0	2.5
% VMA	14.6	14.2	13.9	13.9	13.5
% VFA	49.8	60.9	70.9	71.2	81.7
Film Thickness	7.27	8.56	9.70	9.74	10.69
Filler Bit. Ratio	1.26	1.07	0.95	0.94	0.86
Gsb	2.641	2.641	2.641	2.641	2.641
Gse	2.687	2.682	2.682	2.685	2.687
Pbe	3.20	3.78	4.28	4.29	4.71
Pba	0.67	0.60	0.60	0.64	0.67
% New Asphalt Binder	100.0	100.0	100.0	100.0	100.0
Asphalt Binder Sp.Gr. @ 25c	1.036	1.036	1.036	1.036	1.036
% Water Abs	1.30	1.30	1.30	1.30	1.30
S.A. m^2 / Kg.	4.41	4.41	4.41	4.41	4.41
% + 4 Type 4 Agg. Or Better	100.0	100.0	100.0	100.0	100.0
% + 4 Type 2 or 3 Agg.	25.4	25.4	25.4	25.4	25.4
Angularity-method A	45	45	45	45	45
% Flat & Elongated	0.0	0.0	0.0	0.0	0.0
Sand Equivalent	82	82	82	82	82

Basic HMA mixture volumetrics

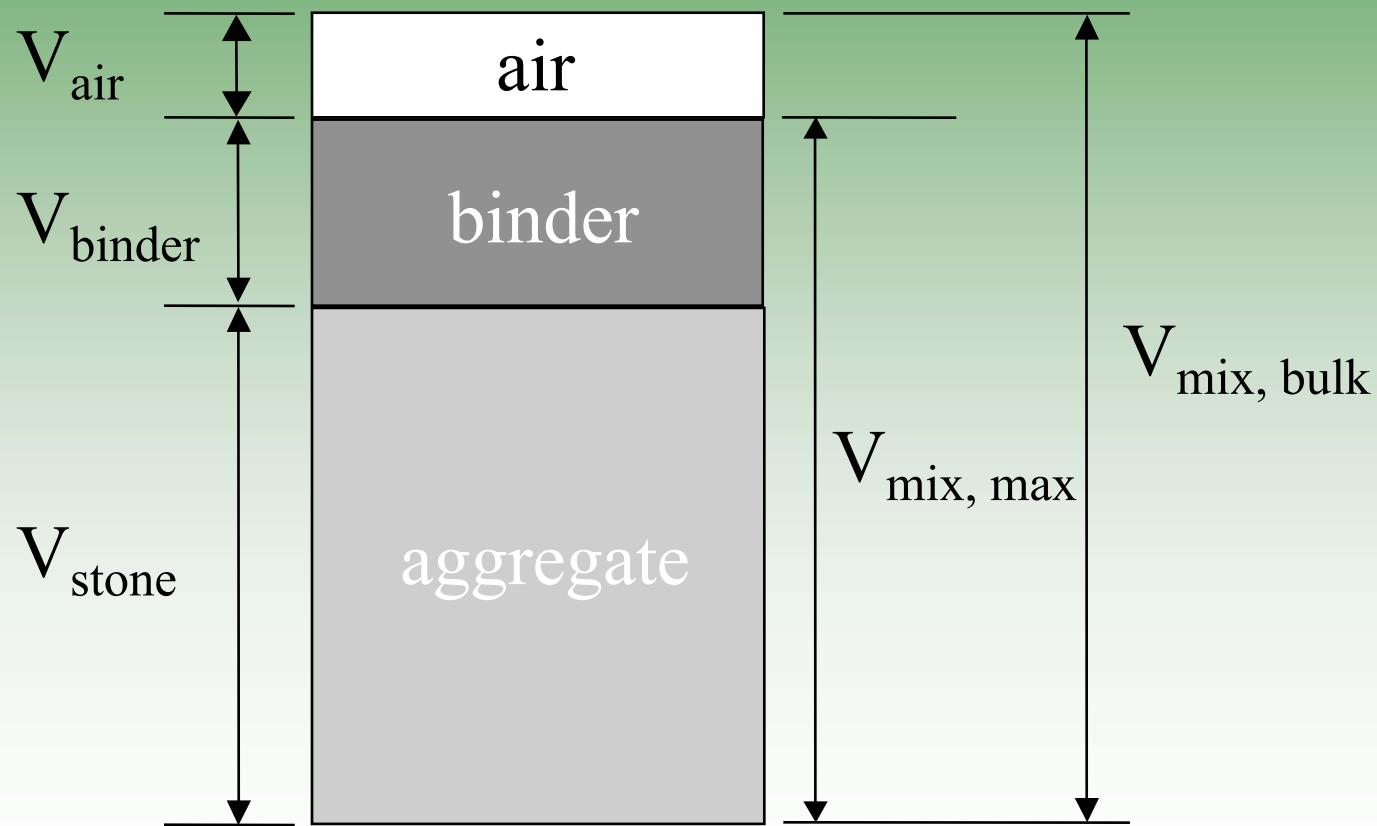

Volumetric Relationship of G_{mm}

$$y = Sx + b$$

$$\frac{100}{G_{mm}} = \left[\frac{(G_{se} - G_b)}{(G_{se})(G_b)} \right] P_b + \frac{100}{G_{se}}$$


Relationship of G_{se} & G_b

- The resultant value for the slope, S, varies very little within the normal range of the specific gravity of the binder and the effective specific gravity of the aggregate.


$$S = \left(\frac{(G_{se} - G_b)}{(G_{se})(G_b)} \right) = \text{slope} \approx 0.60$$

- Typical slope range from 0.58 to 0.62.


Generic Graphical Relationship

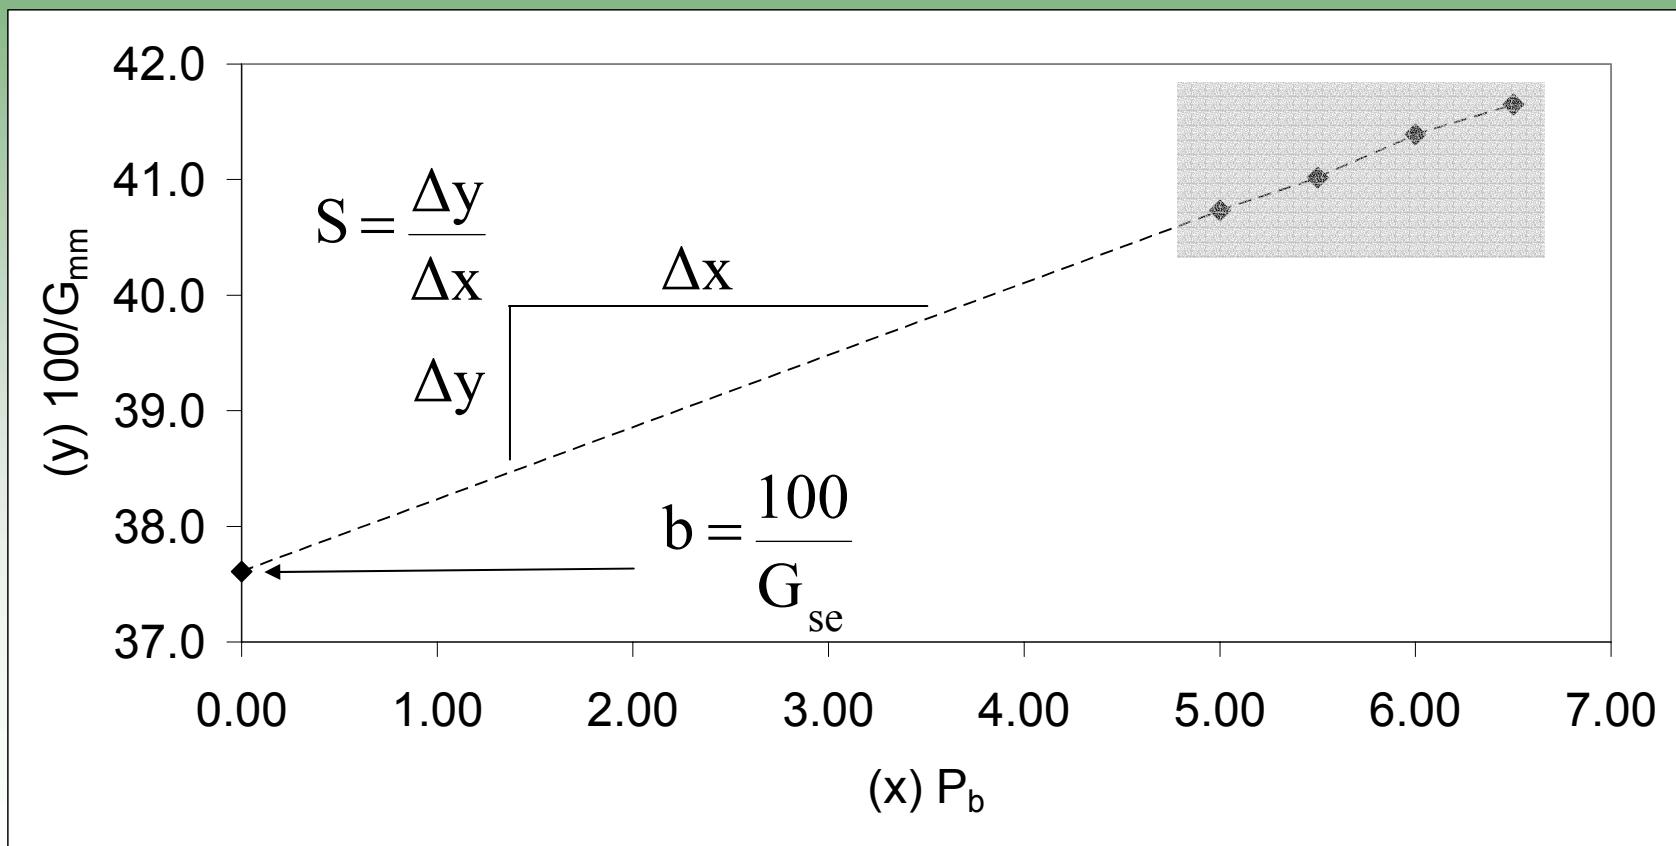


Typical 4-pt. mix design

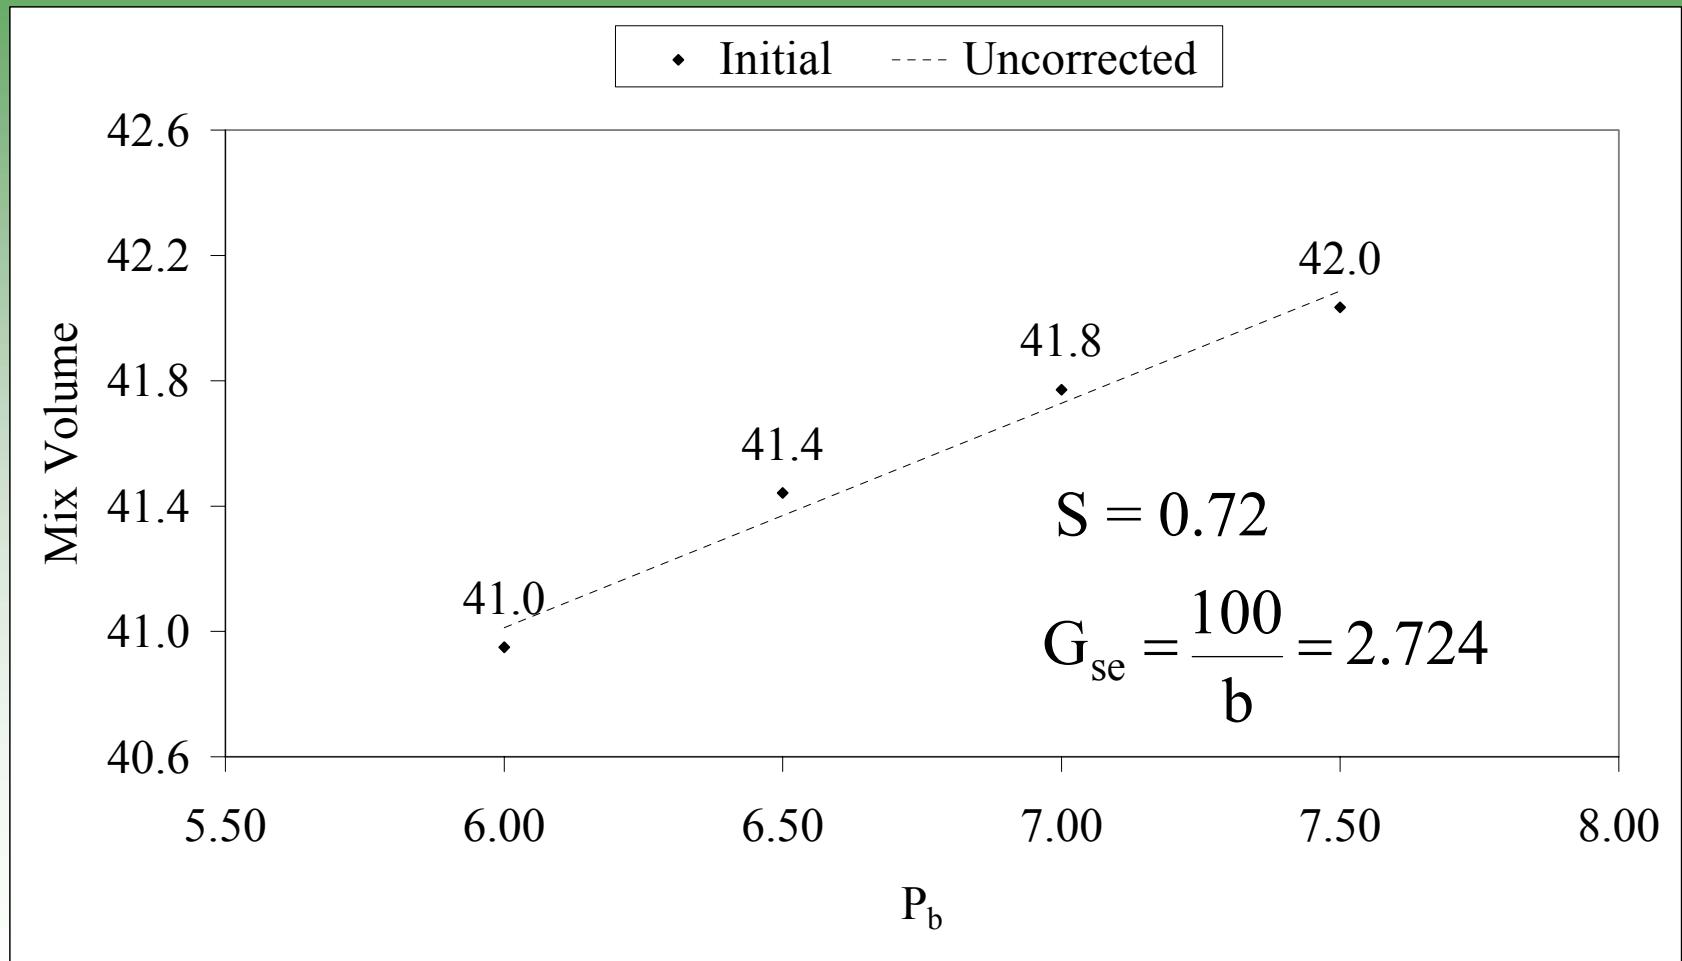

Adjusted 4-pt. mix design

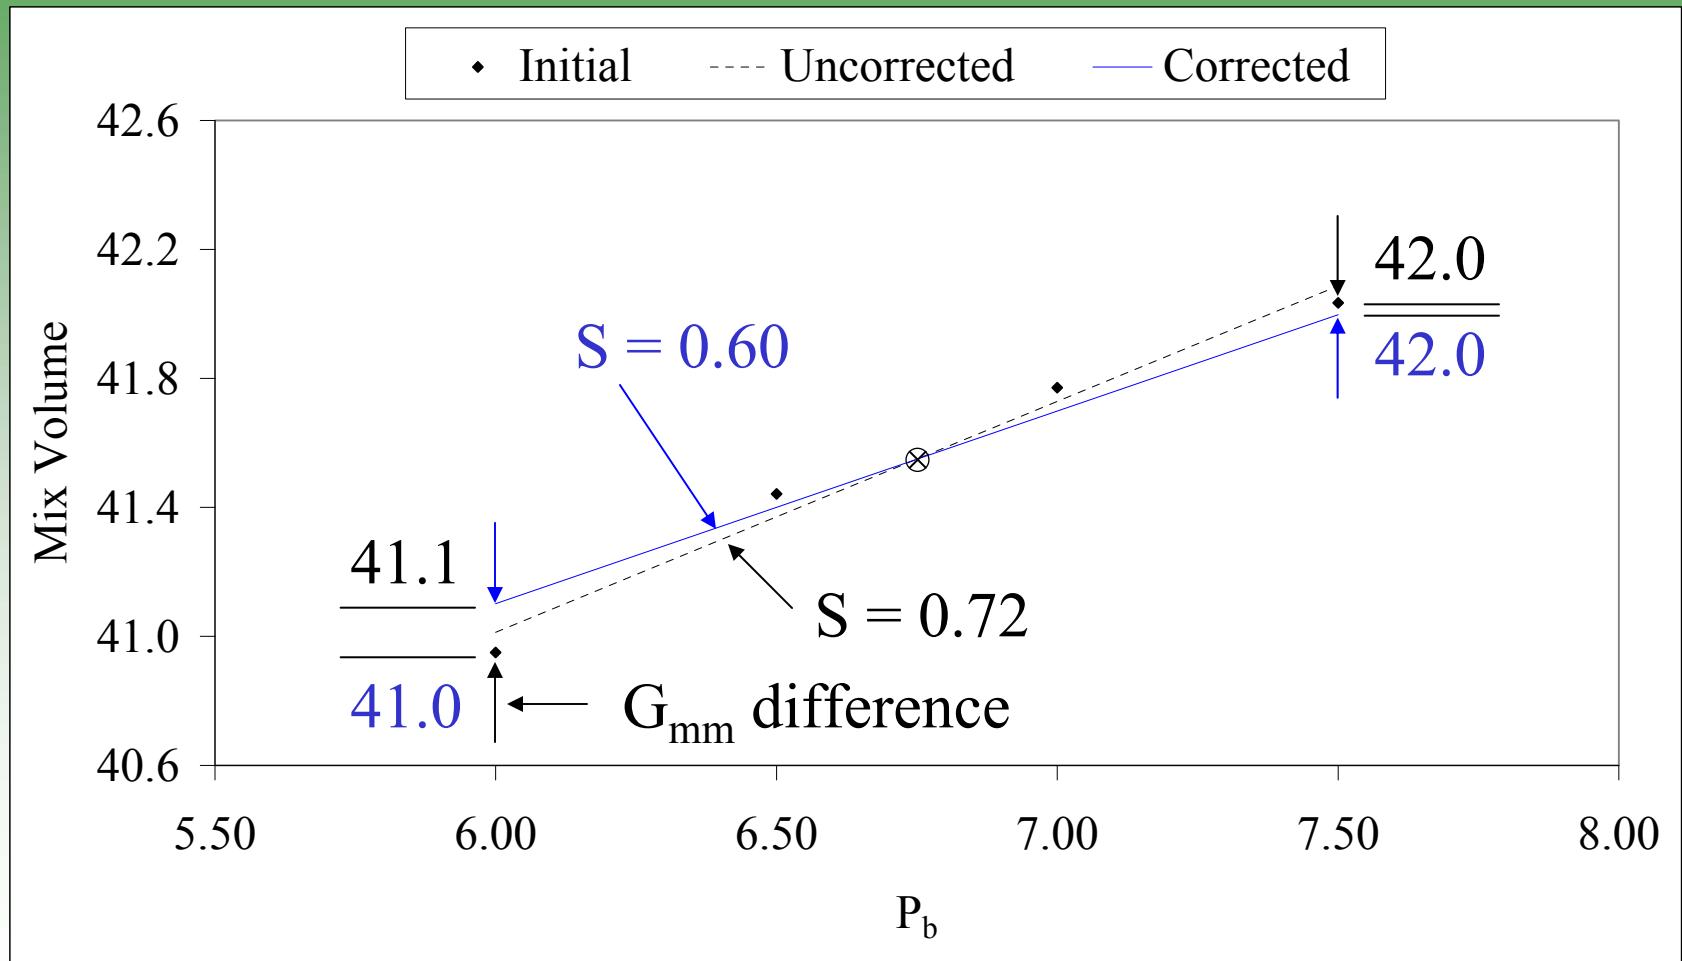

G_{mm} Diff. Distribution

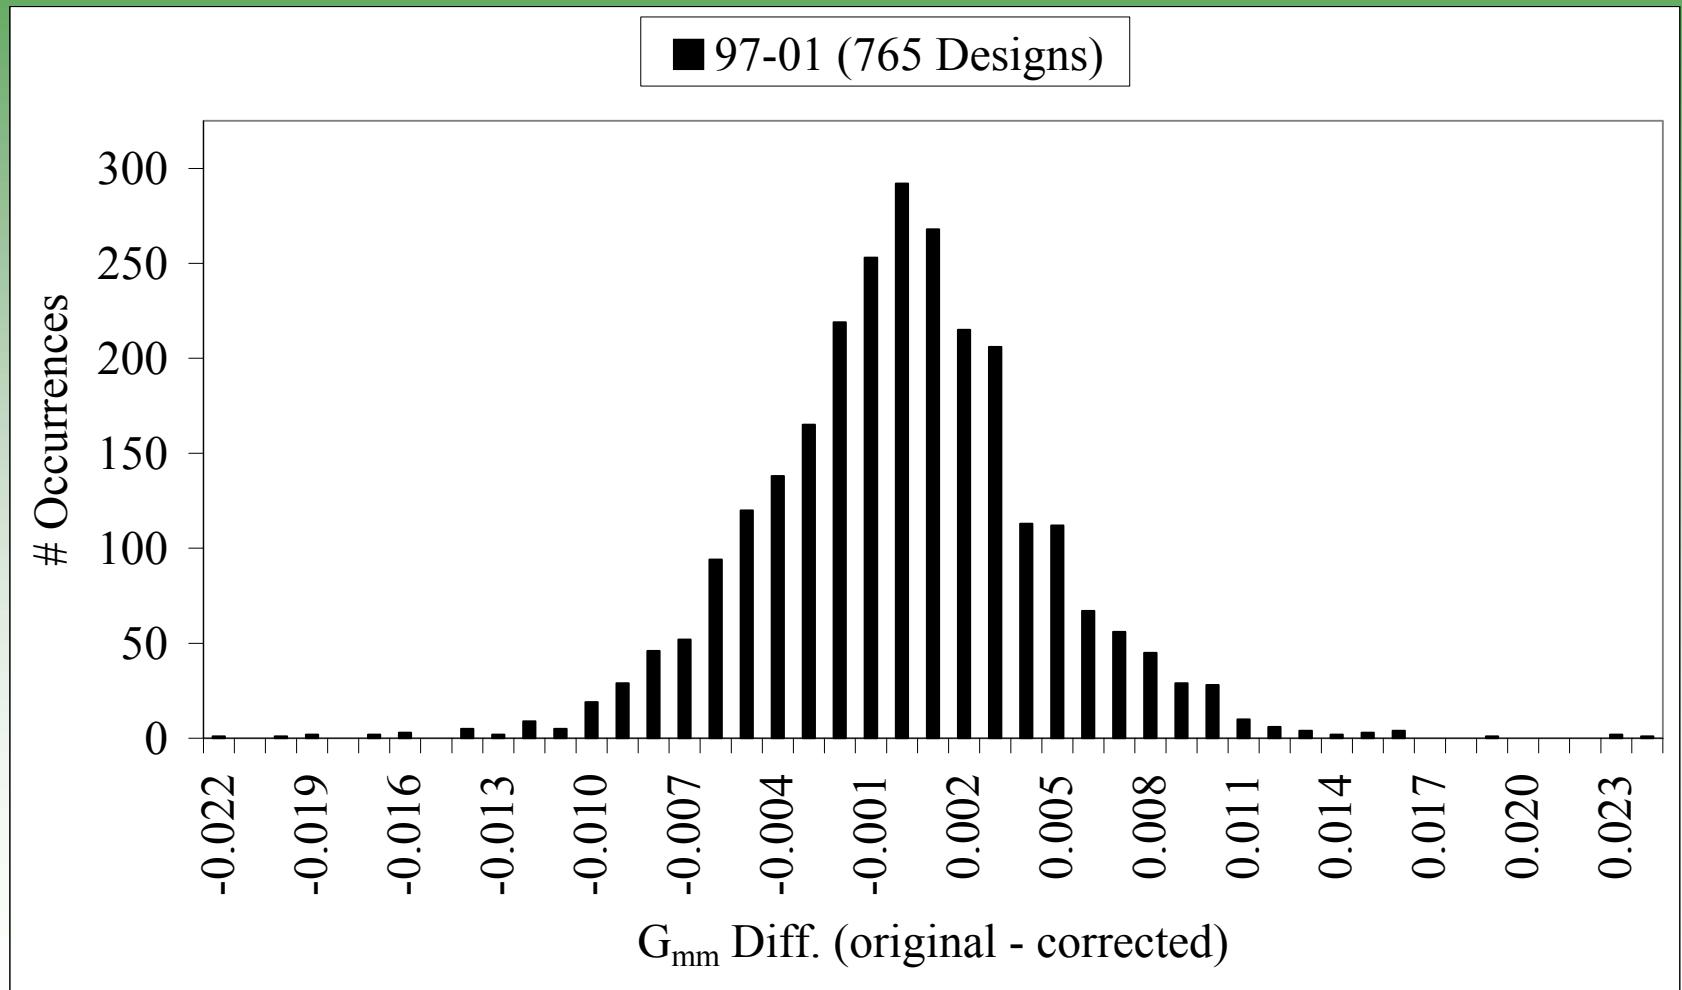


Statistical Analysis of G_{mm} Diff.

- The average and standard deviation are based on the individual comparisons of each design point.

G_{mm} Difference		1 Stdev		2 Stdev		3 Stdev	
Average	Stdev	Low	High	Low	High	Low	High
0.000	0.005	-0.005	0.005	-0.009	0.009	-0.014	0.014

Mix $G_{mm} | \text{Diff.} |$ Distribution

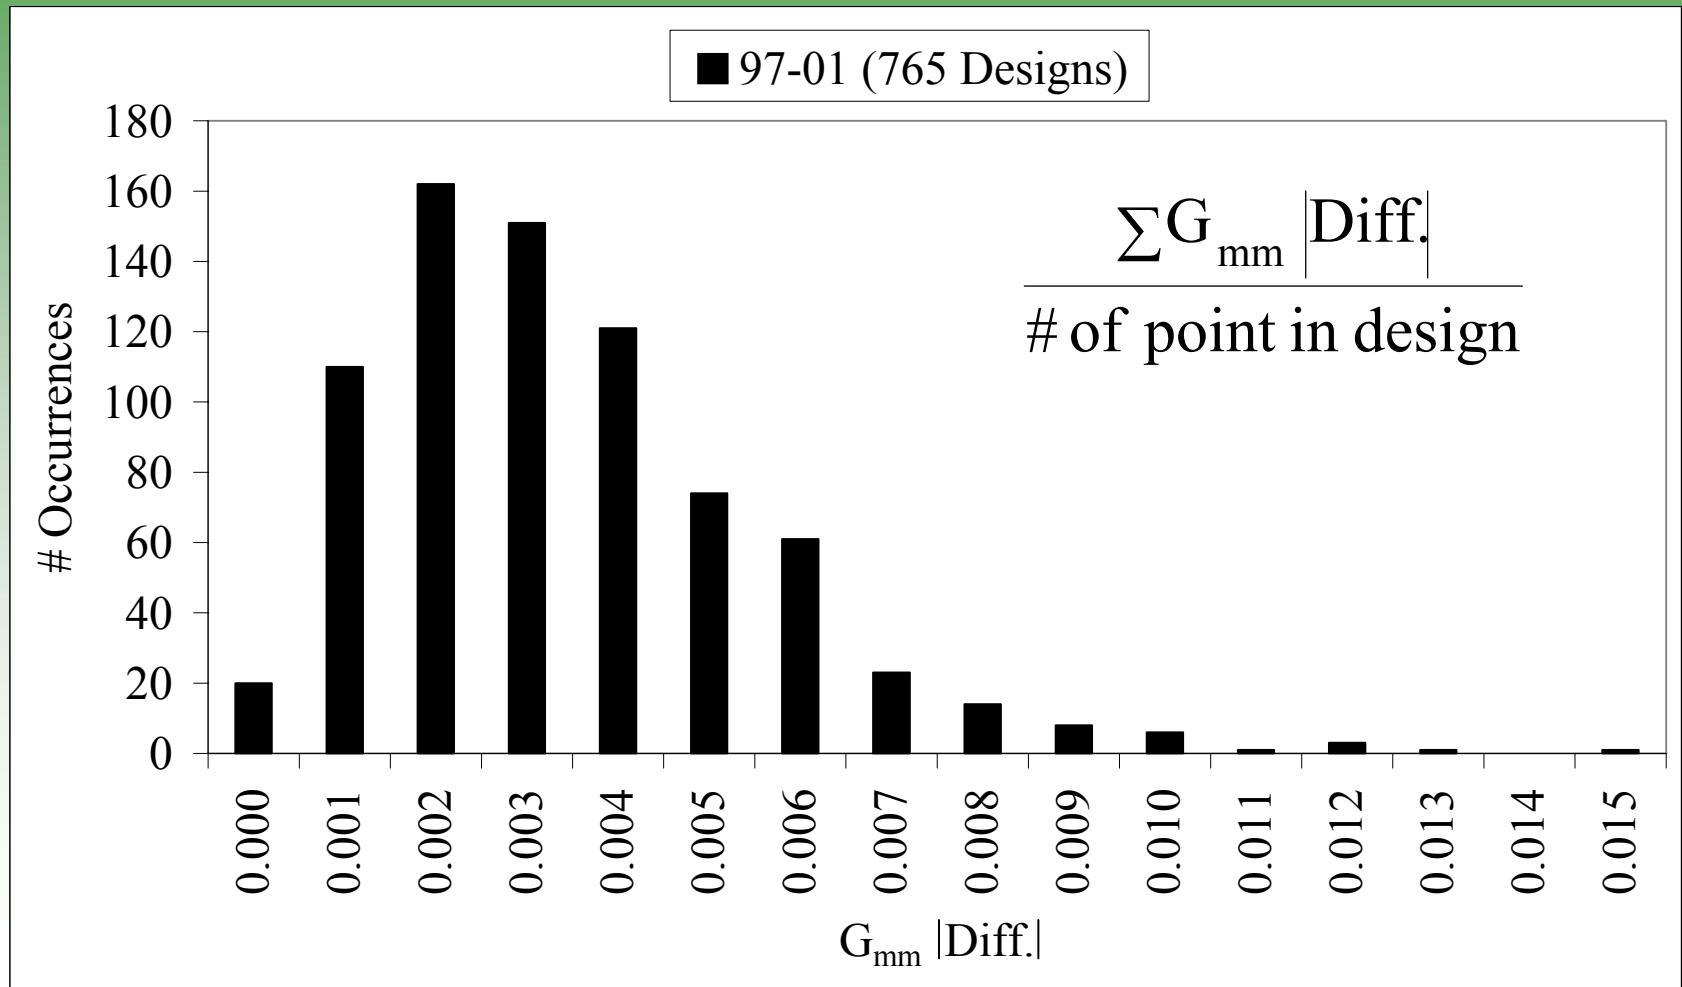


Statistical Analysis of Mix G_{mm} |Diff.| Distribution


- The average and standard deviation are based on the average G_{mm} difference of each design on an absolute basis.

G_{mm} Difference	1 Stdev	2 Stdev	3 Stdev
Average	Stdev		
0.003	0.002	0.006	0.008
			0.010

Adjusted 4-pt. mix design

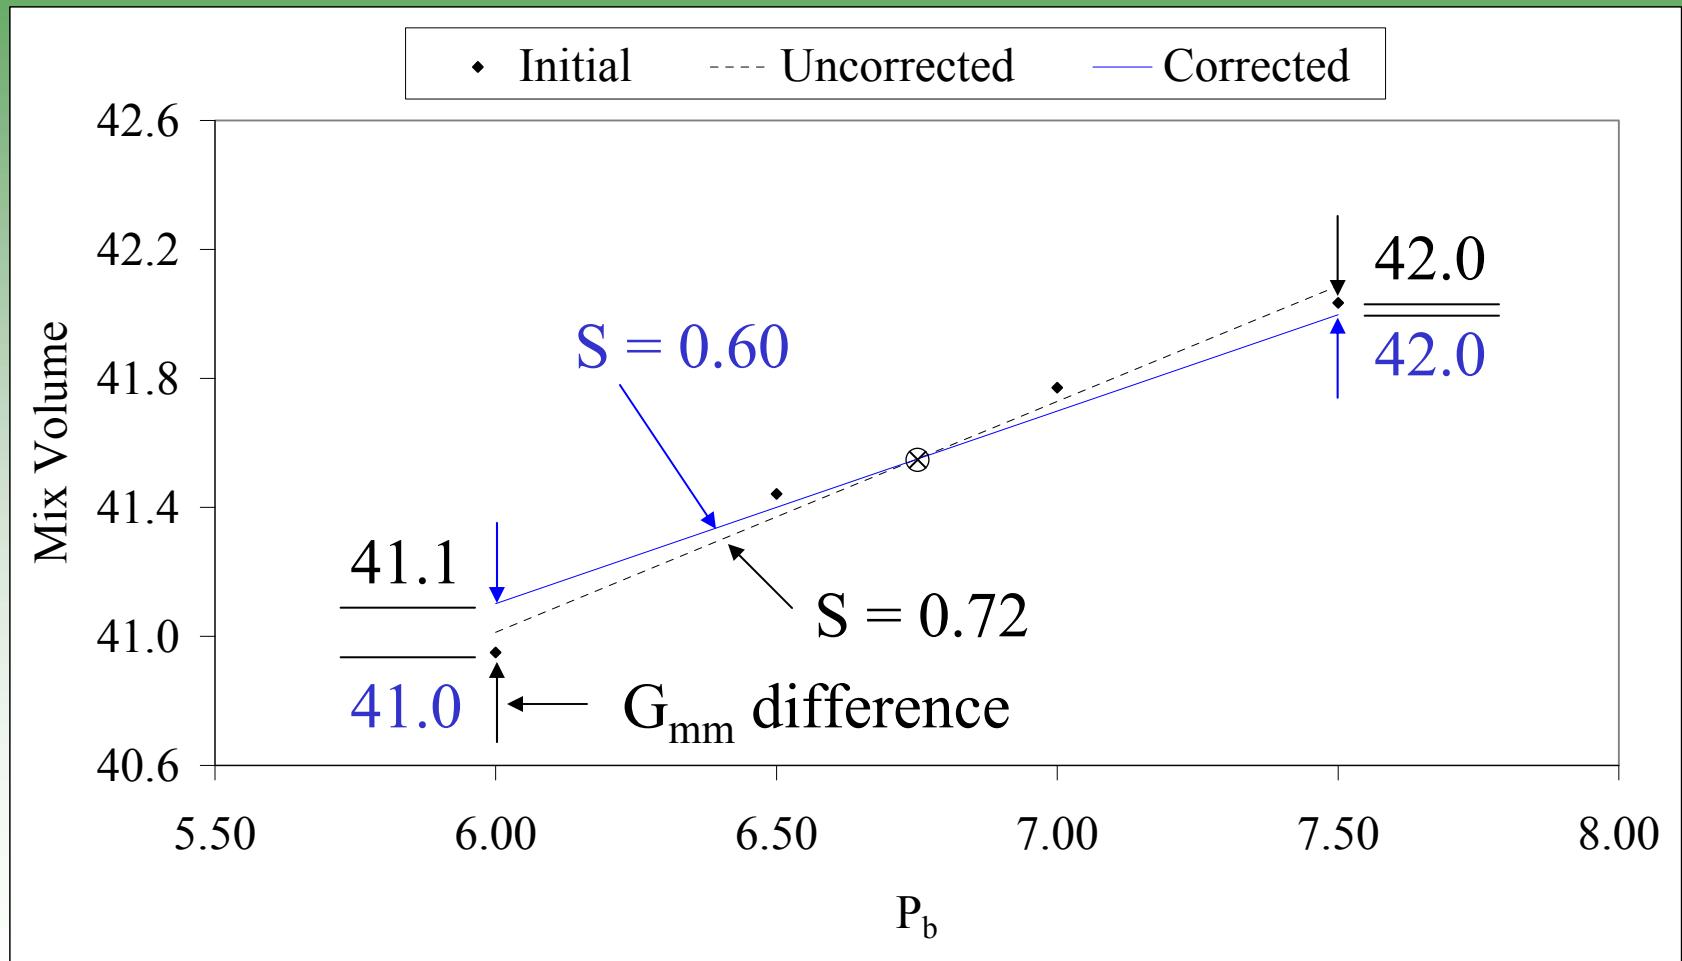


Mix G_{mm} Slope (S) Diff. Distribution

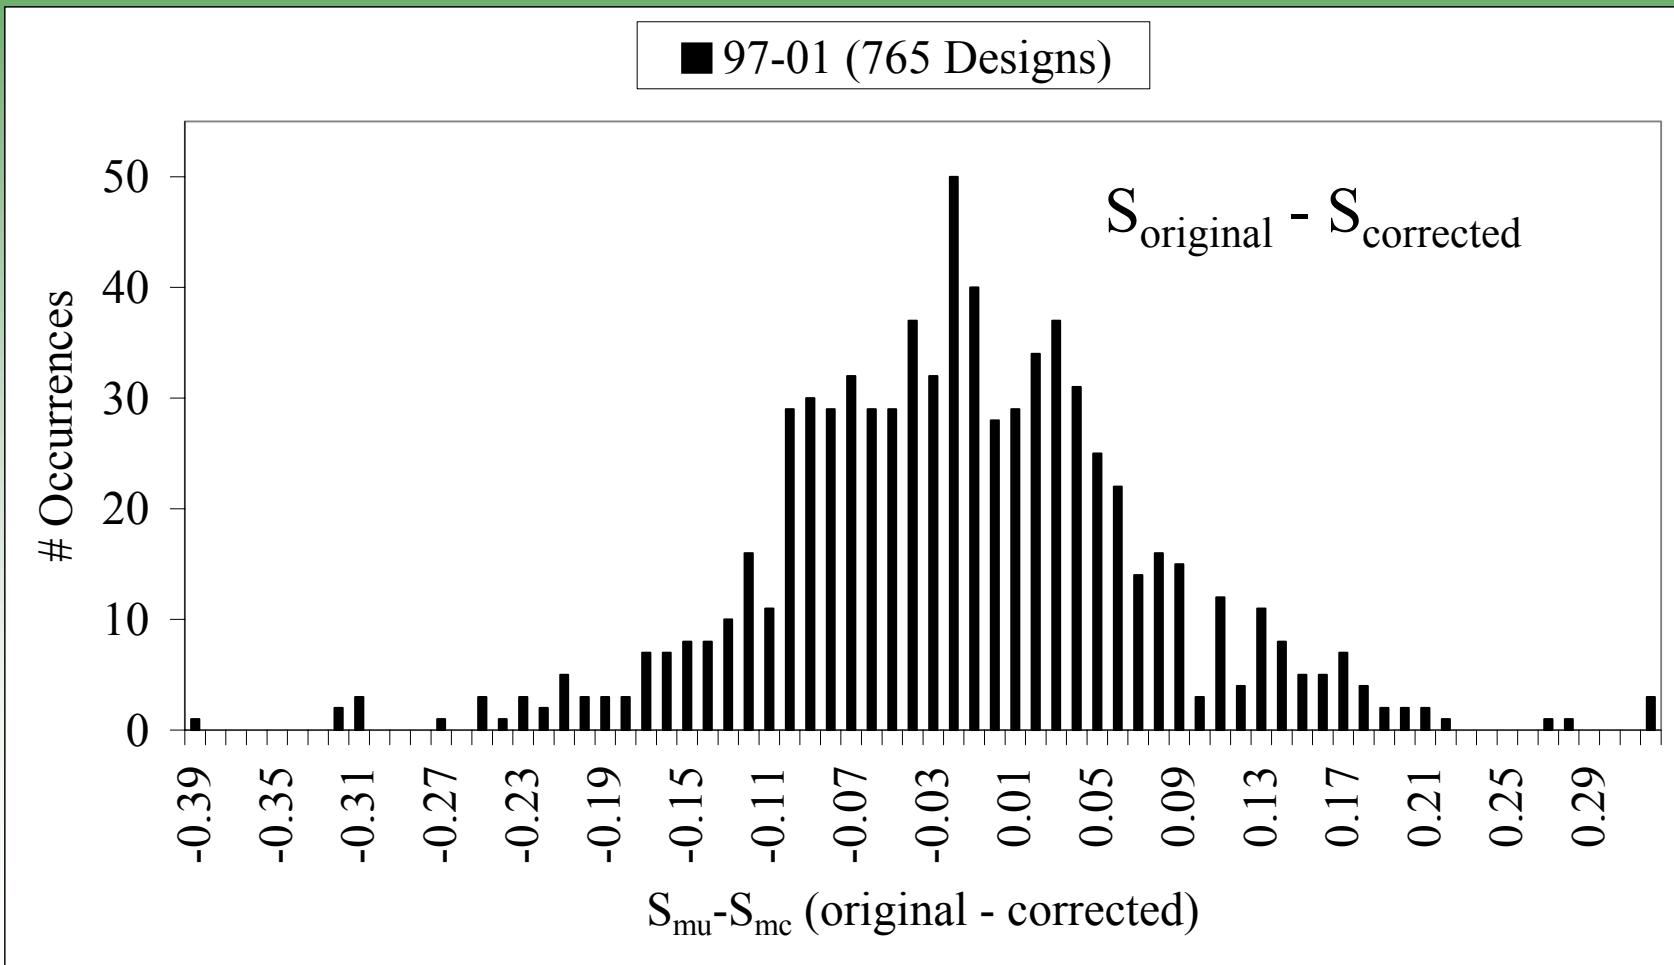


Statistical Analysis of the Mix G_{mm} Slope Diff.

S _{mu} -S _{mc}	S _{mu} -S _{mc}	1 Stdev		2 Stdev		3 Stdev	
Avg.	Stdev	Low	High	Low	High	Low	High
-0.02	0.092	-0.11	0.07	-0.20	0.17	-0.29	0.26

Mix G_{mm} |Diff.| vs. Mix G_{mm} Slope Diff.

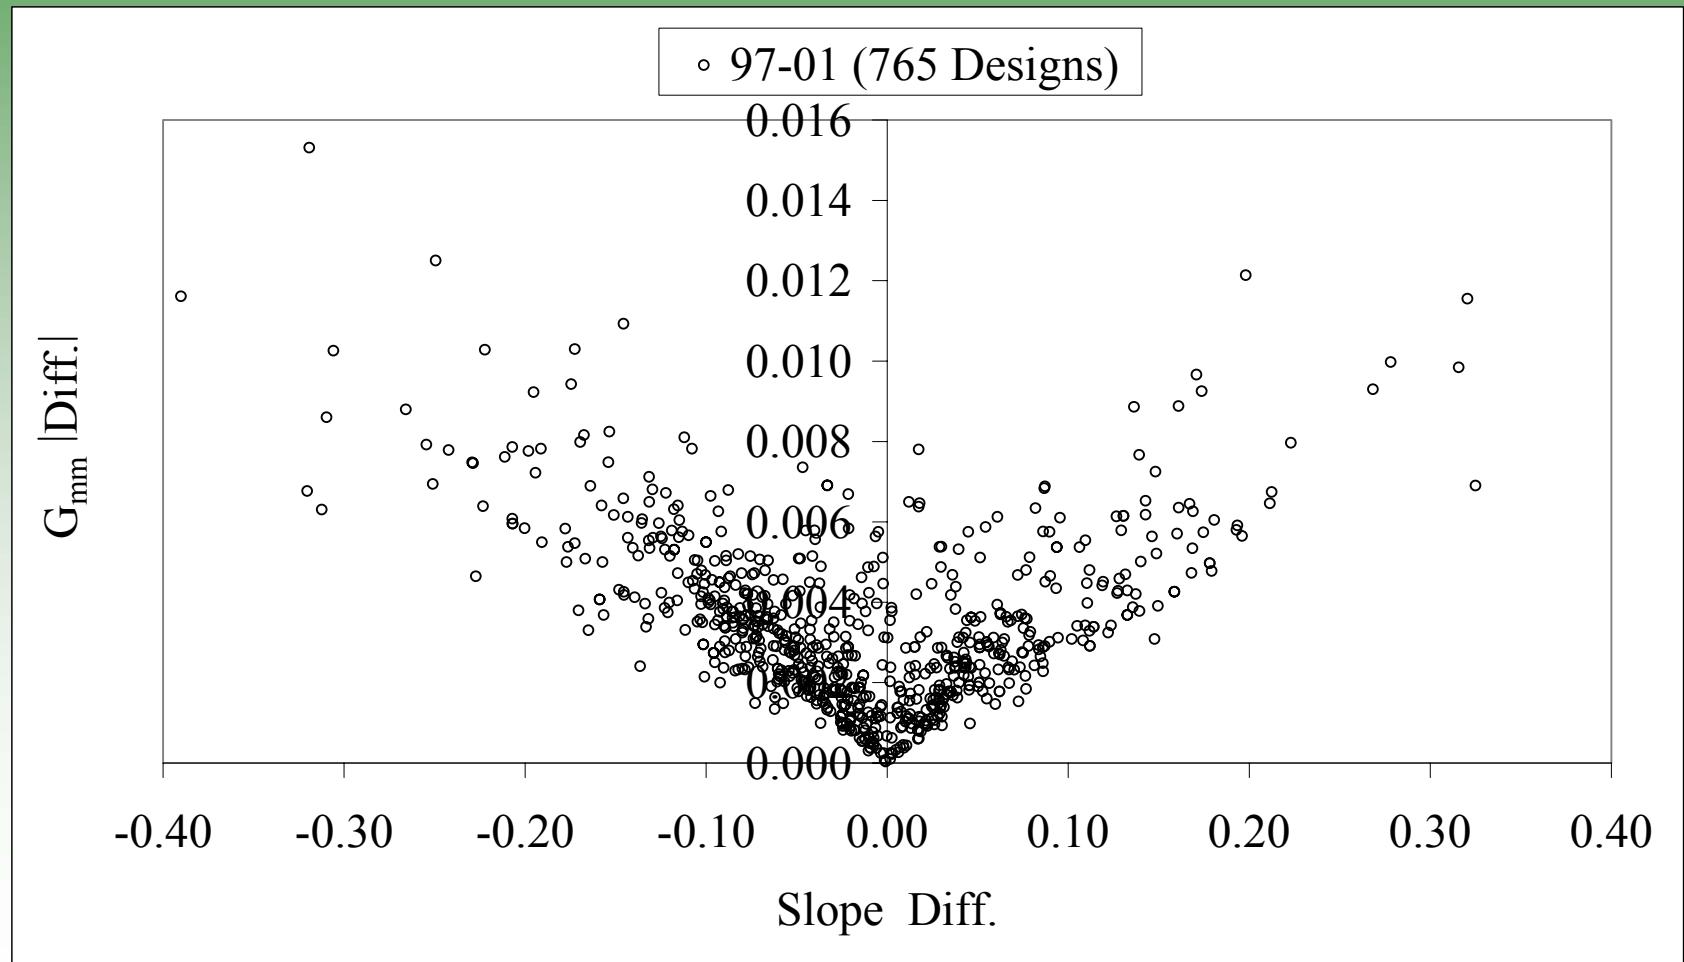


Mix G_{mm} |Diff.| vs. Mix G_{mm} Slope Diff.

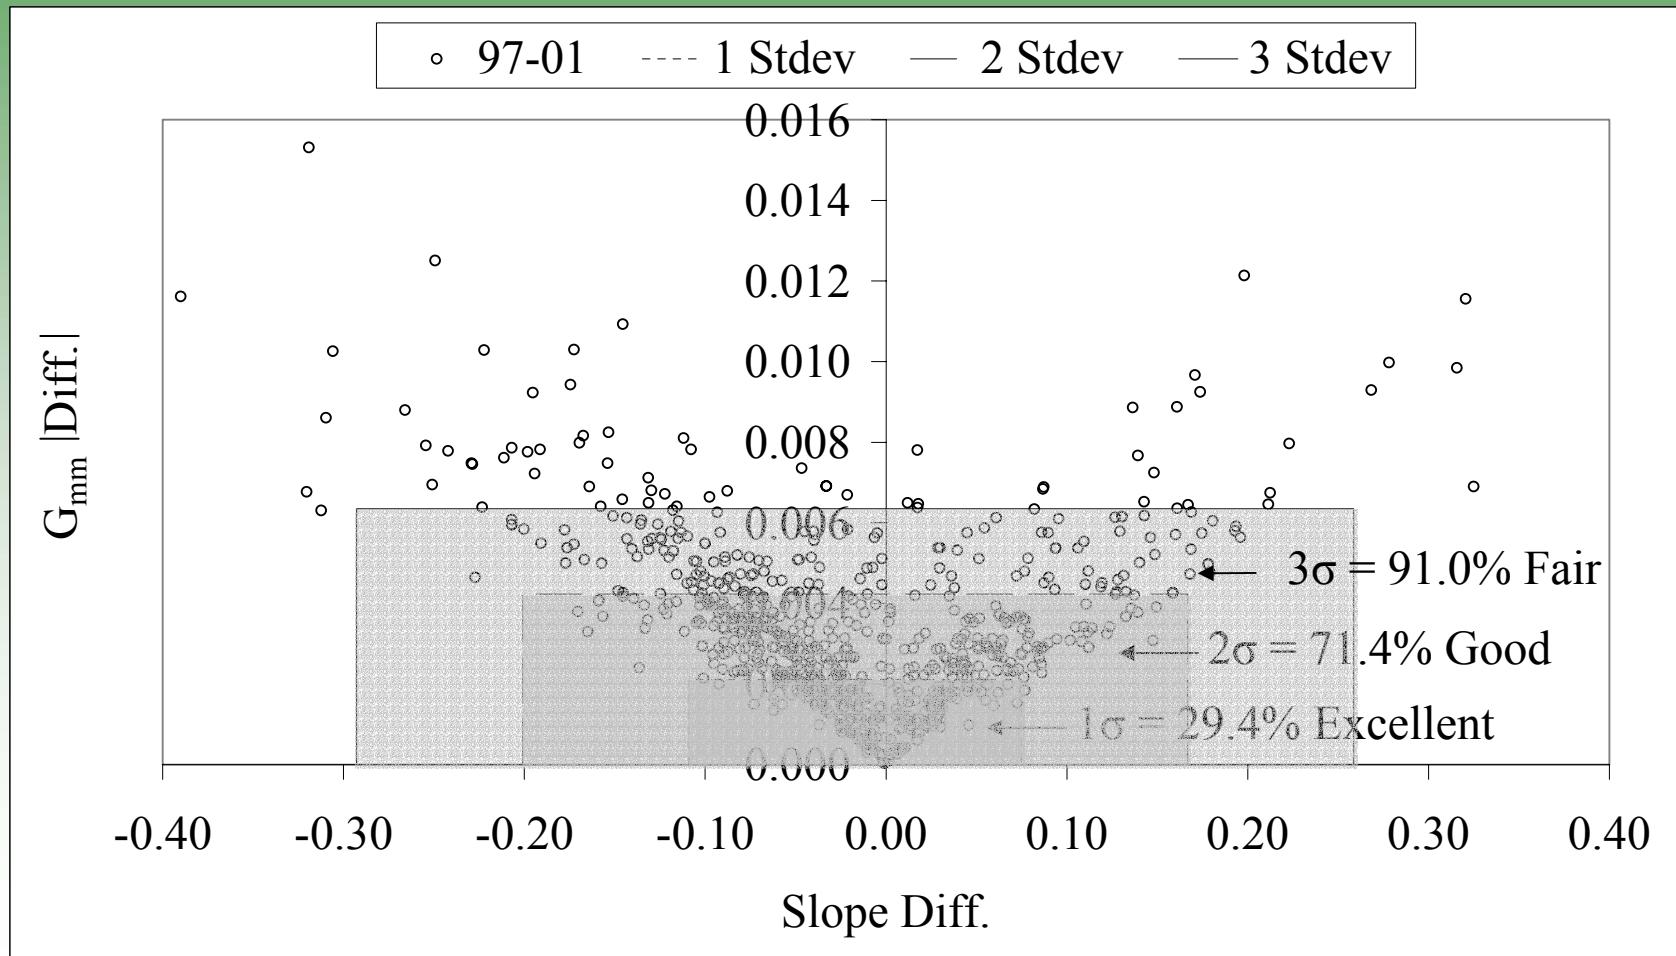


Case Study No. 1

Excellent Mix Design

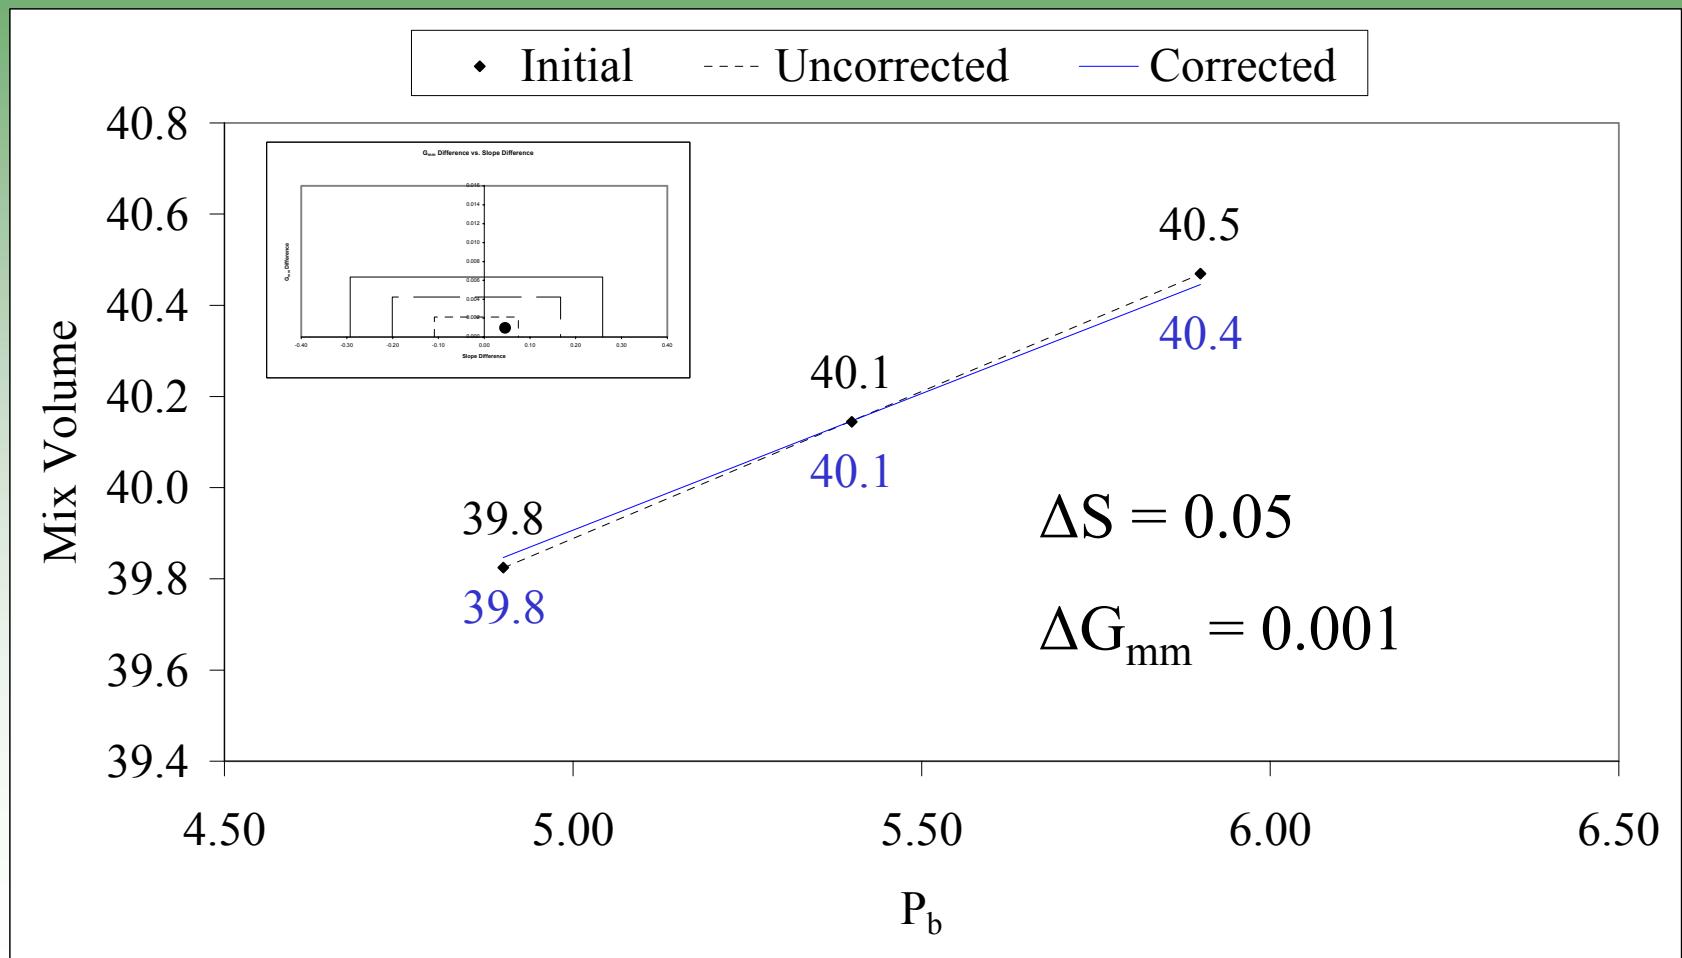


Case Study No. 2

Poor Mix Design

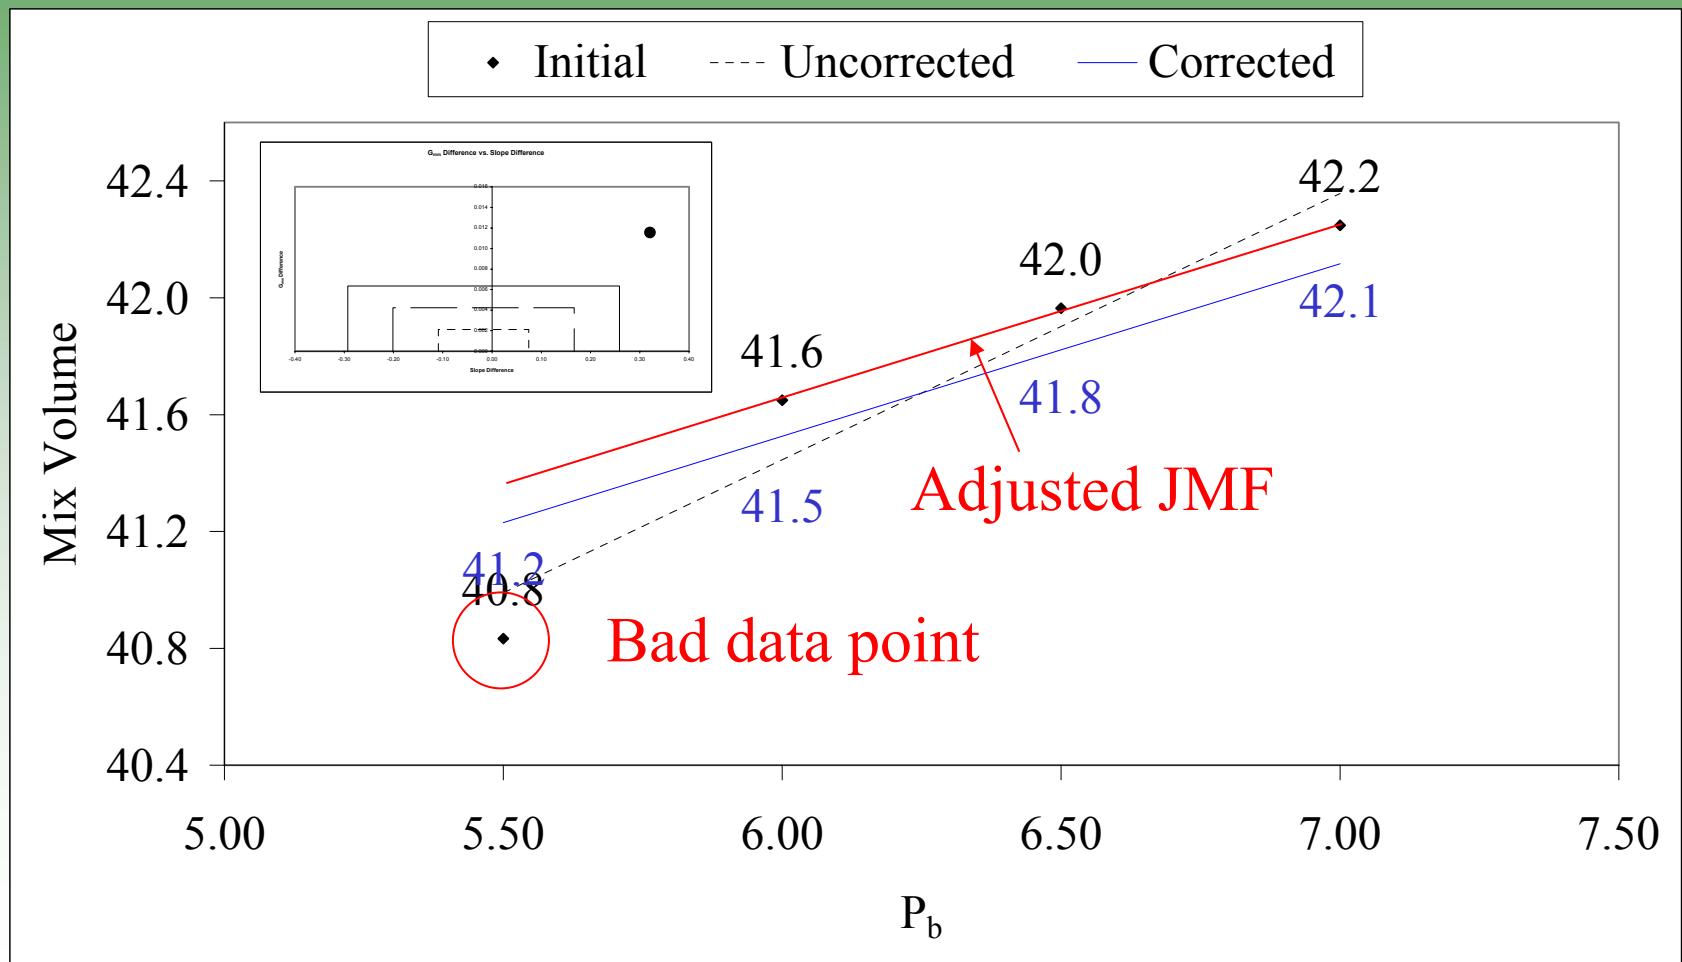


Case Study No. 3

Poor Mix Design

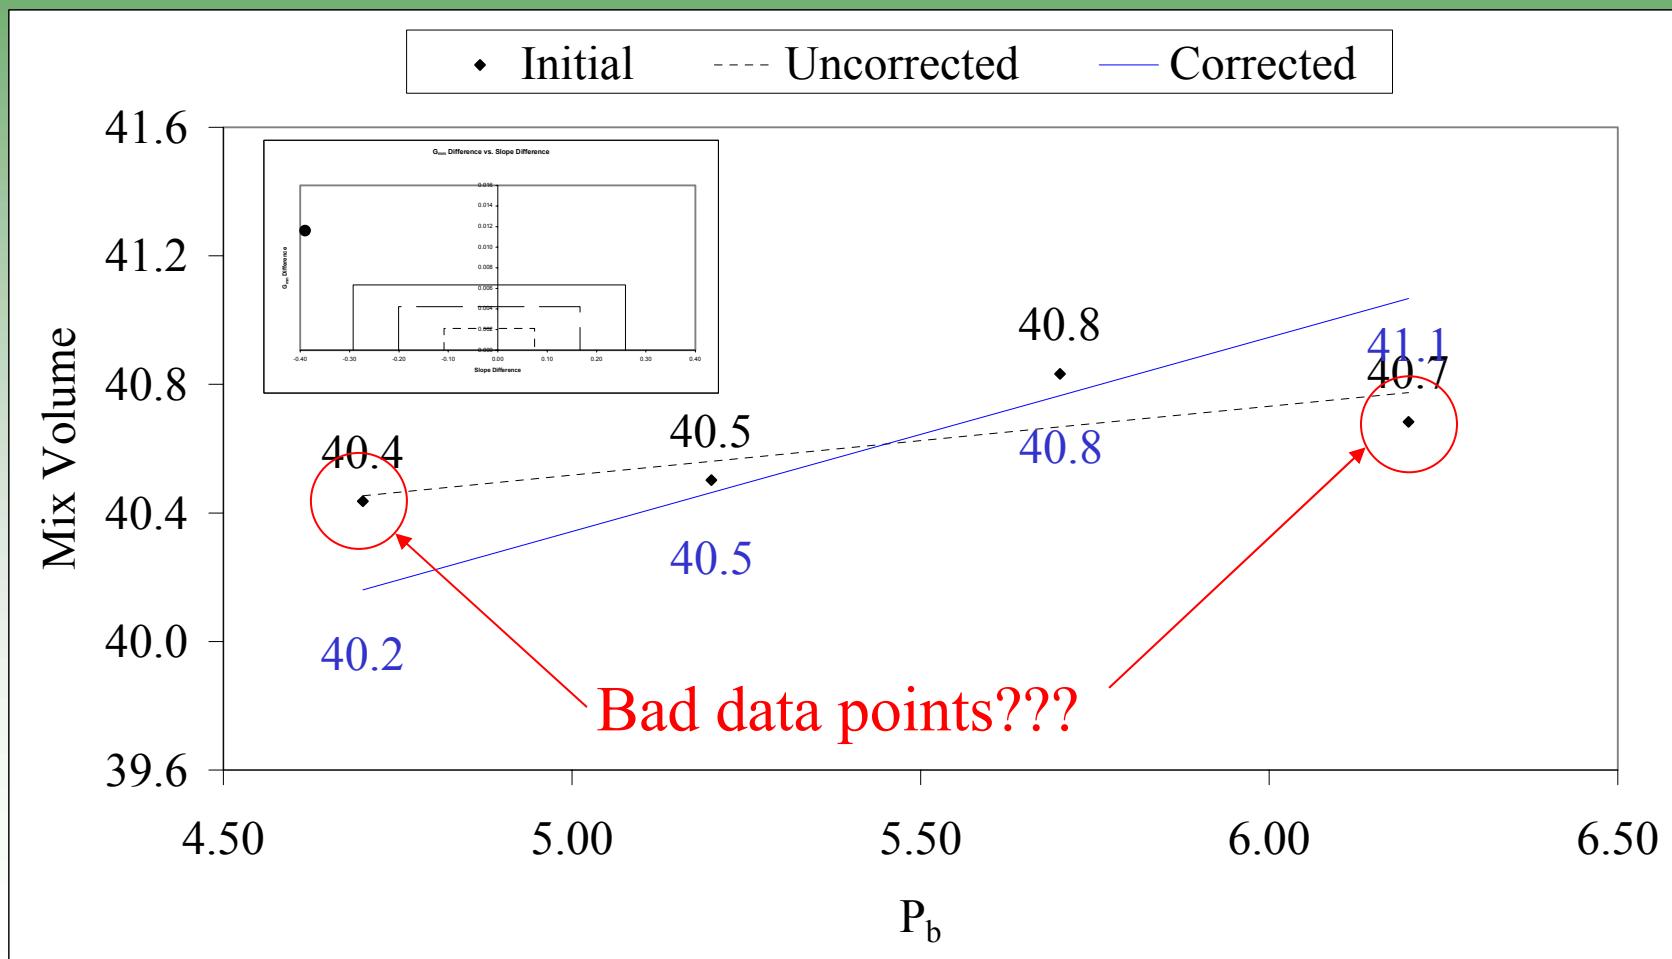

SHADES Mix Design Software

(Excel) Mix Check Tab

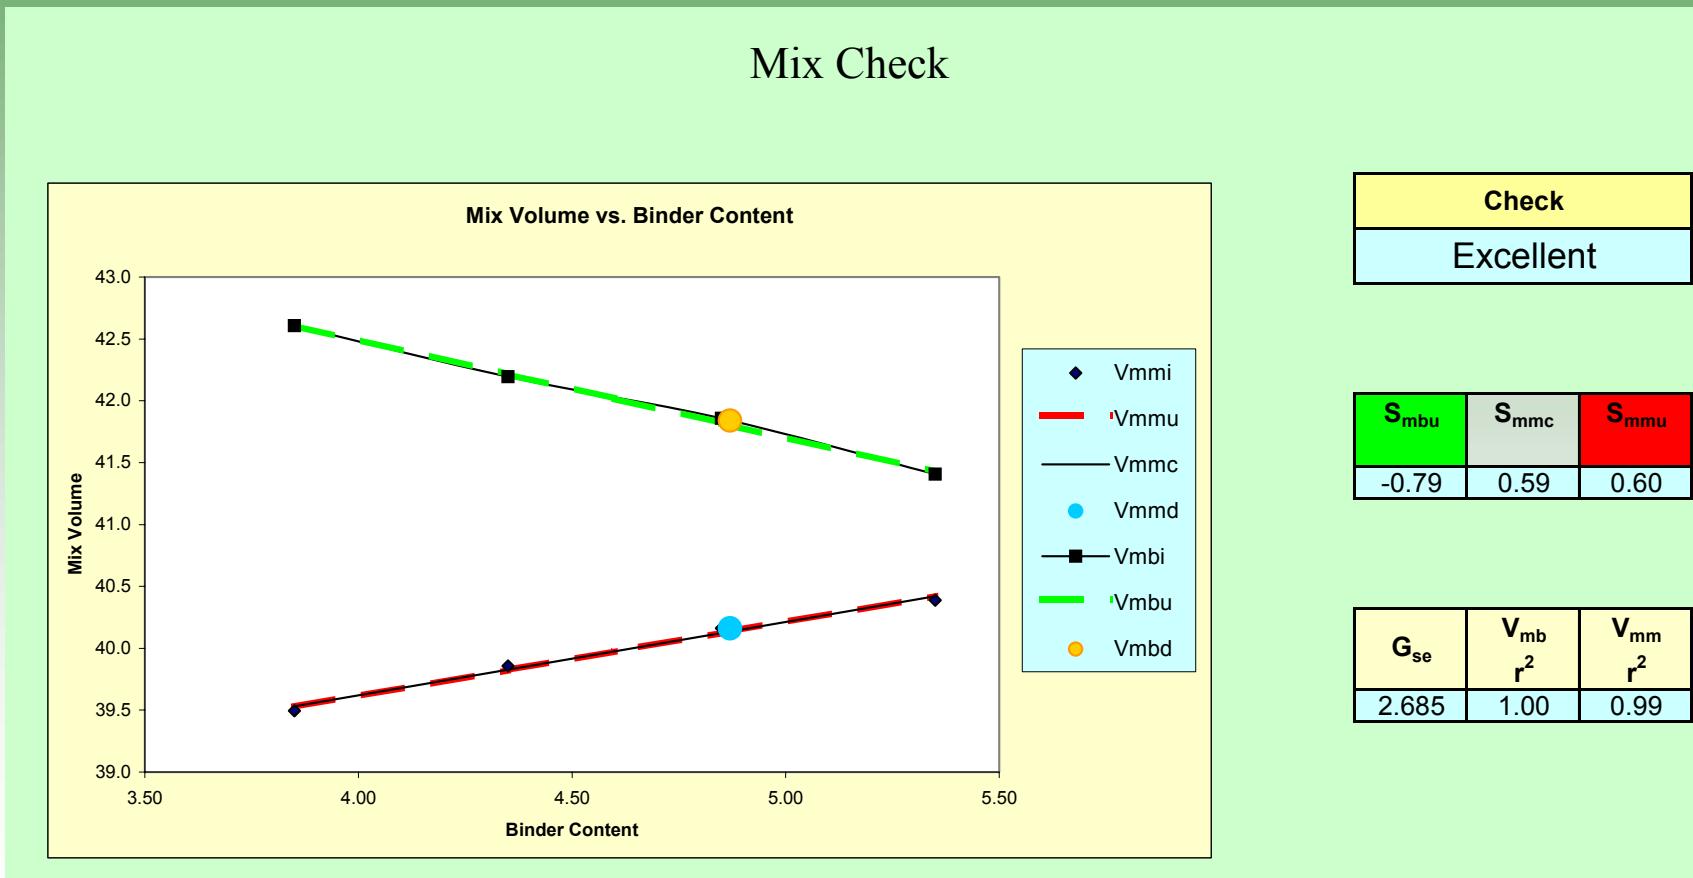

Summary of 2003 JMF Mix Check

	Excellent	Good	Fair	Poor
Designs Received	36.0%	54.0%	10.0%	0.0%

Summary of JMF Mix Check

1997-2001

	Excellent	Good	Fair	Poor
765 Designs Received	29.4%	42.0%	19.6%	9.0%

2003

	Excellent	Good	Fair	Poor
81 Designs Received	39.5%	50.6%	9.9%	0.0%